Journal of Materials Science, Volume 57, Issue 34, September 2022, pp. 16091 - 16146
DOI: 10.1007/s10853-022-07558-1

Review of advanced techniques for manufacturing biocomposites: non-destructive evaluation and artificial intelligence assisted modeling

J. Preethikaharshini[1], K. Naresh[2,3], G. Rajeshkumar[4], V. Arumugaprabu[5], Muhammad A Khan[6], K.A. Khan[2*]

[1]*Department of Applied Medical Biotechnology and Clinical Research, VELS Institute of Science and Technology, Chennai, Tamil Nadu, India.*

[2]*Department of Aerospace Engineering, Khalifa University of Science and Technology, Abu Dhabi-127788, United Arab Emirates.*
[3]*Department of Materials Science and Engineering, University of California, Irvine- 92697, United States.*
[4]*Department of Mechanical Engineering, PSG Institute of Technology and Applied Research, Coimbatore, Tamil Nadu, India.*
[5]*Department of Mechanical Engineering, Kalasalingam Academy of Research and Education, Tamil Nadu, India.*
[6] School of Aerospace, Transport, and Manufacturing, Cranfield University, UK

Corresponding author: kamran.khan@ku.ac.ae

Abstract

Natural fiber reinforced polymer composites (NFRPCs) are being widely used in aerospace, marine, automotive, and healthcare applications due to their sustainability, low cost and ecofriendly nature. The NFRPCs manufactured through conventional, and computer controlled intelligent manufacturing techniques may contain internal and external defects. Traditionally, the microstructure of NFRPCs at different stages of manufacturing was obtained using destructive techniques which have stringent sample size restrictions and may cause decrease in residual properties of composites due to destructive scanning. However, these complications can be overcome by using non-destructive evaluation (NDE) and artificial intelligence (AI) techniques. This review highlights the impact of NDE and AI on the improvement of emerging manufacturing systems. We have discussed the classification of biocomposites, their manufacturing techniques, recyclability and strategies to improve mechanical properties. Further, the use of different types of contact and non-contact NDE techniques in understanding the microstructural variations during manufacturing, machining and the parameters that effects the mechanical performance of NFRPCs

Published by Springer. This is the Author Accepted Manuscript.
The final published version (version of record) is available online at DOI:10.1007/s10853-022-07558-1. Please refer to any applicable publisher terms of use.

are discussed. The use of NDE images in developing the geometrical and computational models of NFRPCs are presented. We have highlighted the importance of AI technology in enhancing the quality of NDE images, improving the microstructural information before post-processing the data, and minimizing the analysis time, and identifying the defects and damages in NFRPCs. In the end, we presented the application of NDE techniques and AI technology in efficient generation of digital material twins of NFRPCs, which will be useful to design next generation biocomposites.

Keywords: Biocomposites; natural fiber; modern manufacturing techniques; non-destructive evaluation; machine learning; deep learning.

Table of Contents

1. Introduction
2. Bio-composites
    2.1. Comparison of natural and synthetic fibers
    2.2. Recycling and surface treatment of bio-composites
3. Processing and mechanical performance of NFRPCs
    3.1. Conventional manufacturing techniques
    3.2. Modern manufacturing techniques
        3..2.1 AFP and ATL techniques
        3.2.2 Working principle of AFP
        3.2.3 AM techniques
        3.2.4 Processing parameters in modern manufacturing techniques
        3.2.5 Remedies to overcome the challenges associated with modern manufacturing techniques
    3.3. Machining of NFRPCs
    3.4. Mechanical property characterization of NFRPCs
4. Destructive and non-destructive evaluation techniques and generation of digital twins
    4.1. Types of non-destructive evaluation techniques

4.2. XCT aided models in NFRPCs

4.3. XCT aided real and virtual geometry-based simulations in generating digital twins

5. Artificial Intelligence approach in polymer composites

5.1. Machine learning

5.2. Deep learning

5.2.1 Convolution neural network

6. Future perspectives

7. Conclusions

1. Introduction

NFRPCs possess several advantages over synthetic fiber reinforced polymer composites (SFRPCs), which include low cost, environment friendly, biodegradability, recyclability, sustainability, reductions in CO_2, etc., [1, 2]. In particular, bamboo fiber reinforced composites absorb approximately up to 12 tons of CO_2 per hectare per annum, which are highly renewable construction materials and protect the pollution generated from the construction industry and fight against global warming [3]. Therefore, these composites have been widely used in civil construction applications [4] and offer a reduction in industrial waste as compared to the use of steel, aluminum, cement, etc. [5]. The production of natural fibers requires low energy, for example, the production of flax fiber requires approximately 9.55 MJ/kg compared to synthetic glass fibers (approximately 54.7 MJ/kg) [6]. Chandgude and Salunkhee [7] reported that the energy required for the production of carbon and glass fibers are 355000 and 31700 MJ/t, respectively, while the production of hemp, flax and sisal fibers requires 4170, 2752 and 2488 MJ/t, respectively. In the last decade, the production rate of NFRPCs has increased for manufacturing various interior and exterior automotive structural parts such as Audi, BMW, Toyota, etc., door

panels, outdoor furniture, etc., [8, 9]. It was reported in recent literature that the compound annual growth rate has been estimated at approximately 11.8% for NFRPCs during the period 2016 to 2021 [10, 11].

The structural and environmental performance of conventional and biocomposite panels have been recently compared under various conditions [12]. It was reported that NFRPCs exhibited promising environmental and structural performance, and encouraged the use of NFRPCs in automotive and aerospace applications [13]. However, there are several limitations of natural fibers, such as lower water absorption resistance, poor weather resistance, high moisture sensitivity, poor thermal stability and fire resistance, low melting temperature, etc., [14]. As a result, sometimes burning of fibers can be occurred during manufacturing. Therefore, it is recommended to use curing temperatures lower than 200°C in manufacturing NFRPCs [15]. More importantly, most of the natural fibers are inherently incompatible with the resin due to their hydroxyl functionality of fiber cell walls, which ensures that the fibers are hydrophilic [16]. However, usually, most of the polymers (thermoset, thermoplastic and elastomer) are hydrophobic [17, 18]. Therefore, wetting of fibers is difficult in that case, which lead to poor interfacial bonding between fiber and matrix and also causes several defects. All these factors affect the mechanical performance of composites.

Several authors have proposed different approaches to overcome the above-discussed limitations of NFRPCs. Recently, Vigneshwaran et al. [15], Zhang et al. [19] and Prabhakar et al. [20] reported novel strategies to improve the thermal stability and fire resistance of NFRPCs via chemical treatments or treatment with coupling agents of fibers. To improve the mechanical properties of NFRPCs, it was suggested to use a compatible fiber/matrix system, optimum weaving pattern, high aspect (length to diameter ratio), the volume fraction of the fiber [21], and low bulk

factors in prepregs to avoid fiber waviness, etc., [22]. However, there is a certain limit in choosing a high fiber volume fraction based on the rule of mixtures, beyond that value, poor interfacial bonding occurs, owing to low matrix volume fraction which leads to higher percentage of voids and brittle failure of the structure [23]. Therefore, it is important to perform the microstructural studies without destroying the specimens during investigation.

In the past, several researchers [24, 25, 26] investigated the failure mechanisms of SFRPCs using non-destructive evaluation (NDE) techniques. Performing NDE techniques in understanding the failure mechanisms of NFRPCs is difficult and challenging owing to lower density of fibers, which are closer to the density of polymers [27, 28]. Moreover, NFRPCs are susceptible to defect formation during manufacturing and machining, owing to high surface roughness and lower failure strain compared to SFRPCs [29, 30]. For example, delamination is the commonly occurred failure while drilling composites [31], it increases with the increase of feed rate while it decreases with the increase of speed and point angle [32]. Nasaar et al. [33] reported that various delamination parameters of NFRPCs can be measured using NDE techniques.

In conventional composite manufacturing techniques, there is a large tendency to form voids through the hand lay-up technique followed by the compression molding technique, however, the possibility of voids through the filament winding technique would be lower. However, identifying the optimum fiber roving angle is essential in the filament winding technique to minimize the voids. Therefore, it is essential to investigate the NFRPCs using NDE techniques to control the quality and to fully access the structural integrity [34].

There are certain limitations of NDE techniques, such as several artifacts can be occurred during data acquisition using NDE techniques, therefore, several filters and algorithms have to be used to enhance the quality of obtained data [35]. Also, the data of most NDE techniques are huge

(several gigabytes) [36, 37], and contain several thousands of images to process [35, 37, 38]. Artificial intelligence (AI) technology can be used to improve the processing of NDE images. The automated defect classification is possible using machine and deep learning algorithms, which minimizes the size of the data and reduces the post-processing time [39, 40]. Caglar et al. [41] reported that the computational time for permeability predictions of fibrous microstructures was reduced to less than 10 seconds through the deep learning convolutional neural network algorithms, from several 1000 seconds of their counterparts through 3D flow simulations.

Modeling and simulation of NFRPCs are useful to minimize the number of experiments and labor costs and to enhance the product quality and performance of composites [42, 43, 44]. NDE techniques are useful to provide the input data for modeling and simulation of NFRPCs [45]. Moreover, the digital twins of NFRPCs manufactured through modern manufacturing techniques can be generated with the help of NDE techniques [35, 46] and used to validate the experimental results [47]. Strohrmann and Hejek et al. [48] validated the finite element analysis (FEA) results of tensile properties of LINEO FlaxPreg T-UD 110 with digital image correlation and found good agreement. Joffre et al. [45] validated the FEA results of moisture induced swelling (relative humidity of 80%) properties of wood fiber with the X-ray computed tomography results and found excellent agreement.

In this review article, the classification of biocomposites, manufacturing of natural and synthetic fiber, and their recyclability have been discussed. Next, several conventional and modern manufacturing techniques are described. Further, the use of different types of contact and non-contact NDE techniques in understanding the microstructural variations during manufacturing, machining and testing of NFRPCs are discussed in detail. The comparison of NDE-aided geometrical models data with the numerical simulation (finite element analysis and computational


fluid dynamics) results of NFRPCs are presented. Also, the importance of artificial intelligence (AI) technology in enhancing the quality of NDE images and minimizing the analysis time, is discussed. In the literature, there is no such review available that discusses in detail the application of NDE techniques and Artificial intelligence technology in NFRPCs. Therefore, new research directions in the field of NFRPCs related to Industry 4.0 which include AM, robotics, big data, the internet of things, AI, etc., can be identified through this review article. These details are essential to utilize currently available new technologies for designing and manufacturing high-quality and eco-friendly structural components.


2. Biocomposites:

In a composite material if one constituent (fiber or matrix) is bio-based then it is called as bio-composites [2]. Biocomposites can be divided into two groups, as shown in Fig. 1(a). (i) Green composites, in which both fiber and matrix are biodegradable [49] and (ii) Partly eco-friendly, in which either fiber or matrix would be bio-degradable. Partly eco-friendly composites are classified into two groups. (i) Natural fibers (flax, hemp, ramie, pineapple, banana, etc.) reinforced with petroleum based non-biodegradable polymers (epoxy, polyester, vinyl ester, etc.) and (ii) synthetic fibers (aramid, carbon, glass, etc.) reinforced with biodegradable polymers (polylactic acid (PLA), Polyhydroxybutyrate (PHB), polycaprolactone (PCL), poly butylene succinate (PBS), etc.) [50].

The classifications of synthetic and natural fiber composites are shown in Fig. 1(c). Natural fibers can be classified into three groups, based on animal, plant and mineral fibers [51]. Fig. 1(c) shows the sub-classifications of these three groups. These fibers are reinforced with thermoset and thermoplastic polymers [21]. Recently, several plant and animal fibers inspired structures are manufactured for various applications, e.g: bamboo-inspired structures are used for leg applications, as shown in Fig. 1(d). The plant fibers consist of cellulose, hemicellulose, lignin and

pectin [52]. The chemical structure of plant fiber constituents is shown in Fig. 1(e) [53]. The degradation temperature range of cellulose, hemicellulose and lignin is approximately between 260ºC to 350ºC, 200ºC to 260ºC and 160ºC to 400ºC, respectively [54]. Hence, lignin has a higher degradation temperature compared to cellulose and hemicellulose [55], therefore, it can be used as a filler along with flame retardants for enhancing the thermal stability of NFRPCs [56]. The glass transition temperature and viscoelastic properties of NFRPCs can be studied as a function of temperature and frequency using a dynamic mechanical analyzer [57], and the thermal stability of NFRPCs can be studied using a thermogravimetric analyzer [58].

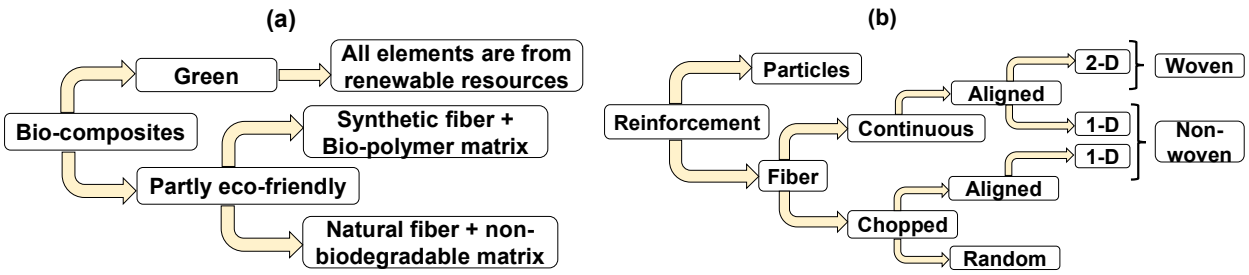

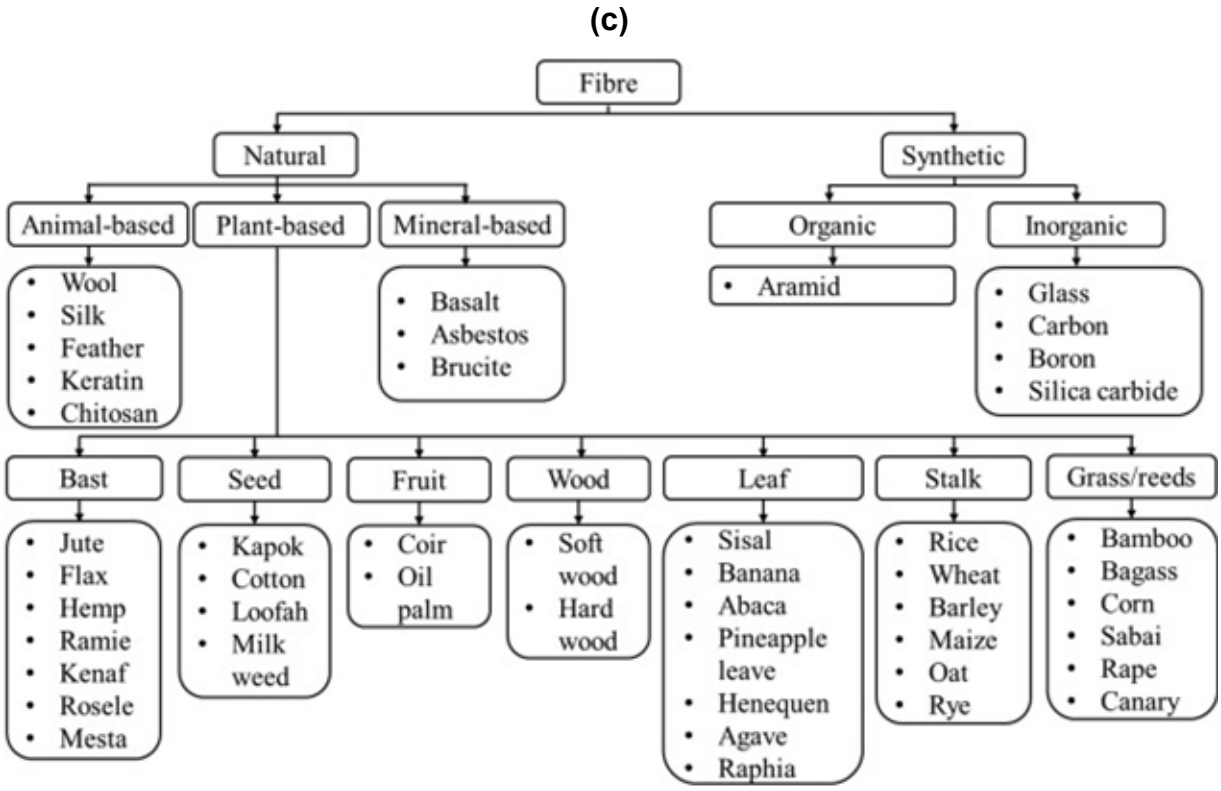

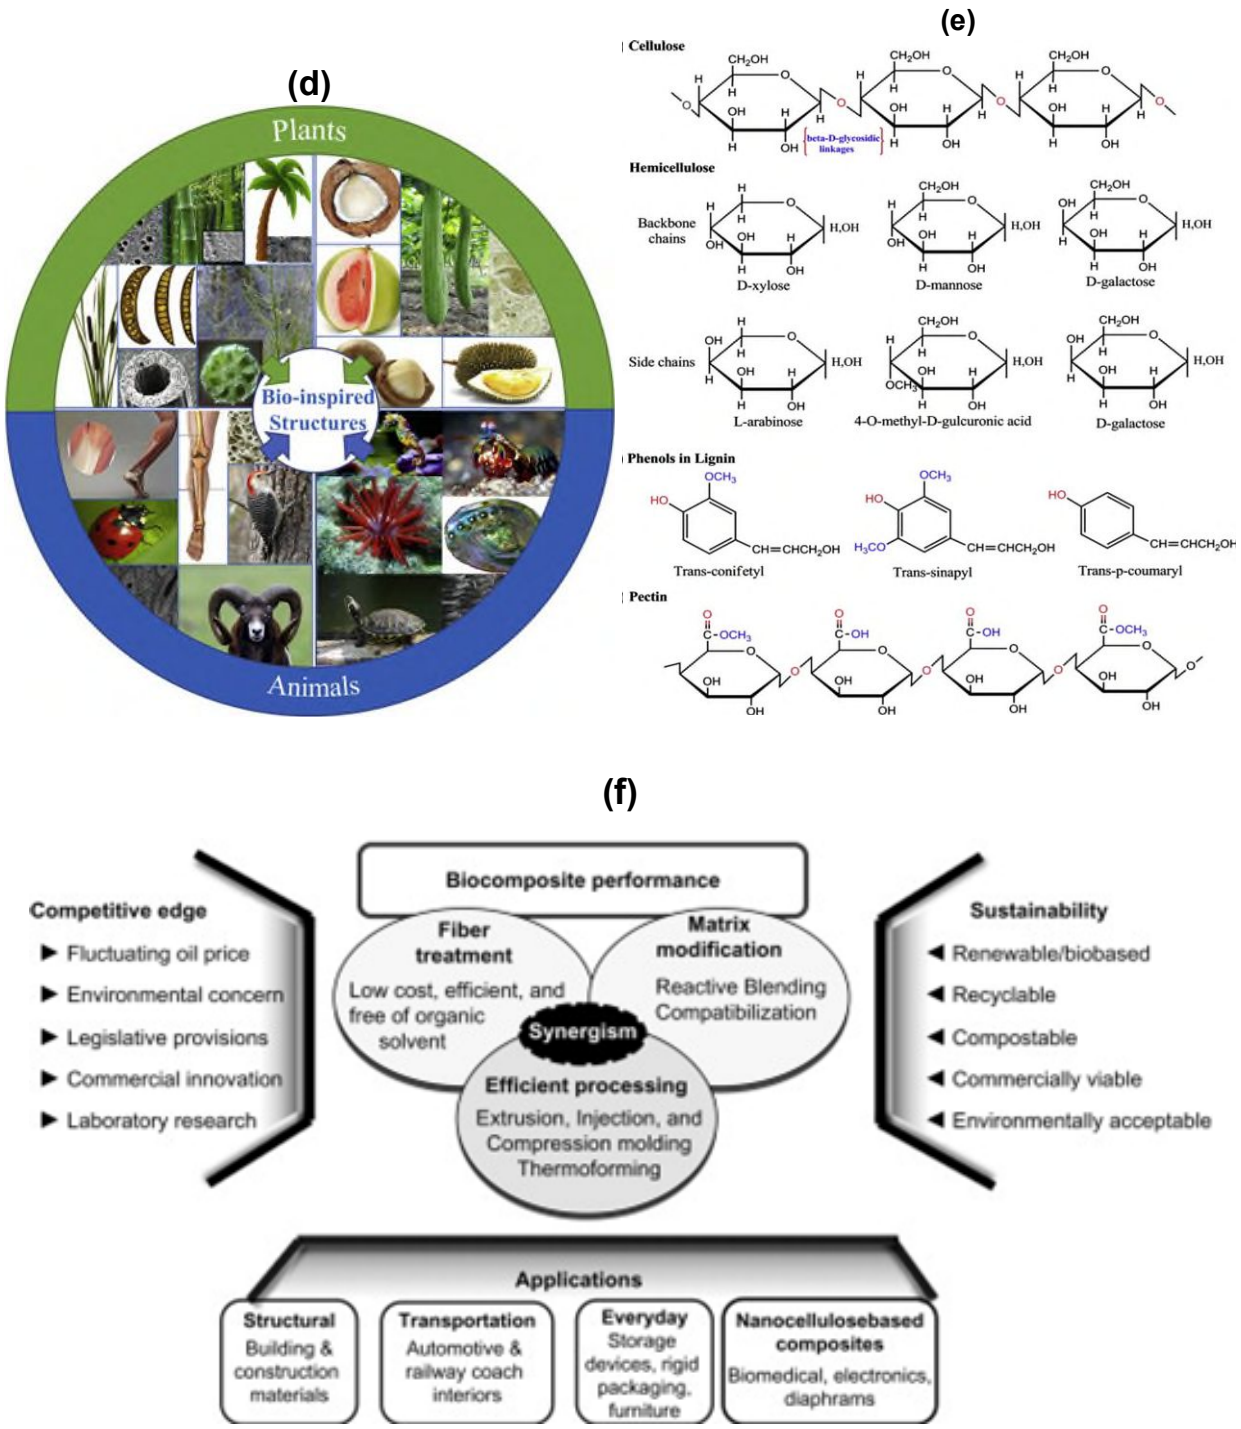


Fig. 1 Classifications of biocomposites (a) and classification of reinforcement in NFRPCs based on its dimensions (b) Adapted from MDPI [59], Copyright MDPI 2018; classifications of natural and synthetic fibers (c) Adapted with permission from Elsevier [60], Copyright Elsevier 2021; bio-inspired structures from plant and animal fibers (d) Adapted with permission from Elsevier [61], Copyright Elsevier 2020; chemical structure of plant fiber constituents (e) Adapted with permission from Elsevier [53], Copyright

Elsevier 2015; Performance and Applications of biocomposites (f) Adapted with permission from Elsevier [62], Copyright Elsevier 2015.

The bio-based biodegradable polymers are manufactured from renewable sources, which require lower Energy and produce low carbon emissions compared to petrobased non-biodegradable polymers [63, 64]. Therefore, these polymers are being increasingly considered in many medical and engineering fields [65, 66]. Recently, several researchers using bio-degradable polymers for reinforcing fibers, in that PLA is a promising thermoplastic bio-polymer, it is extracted from renewable resources, such as corn, sugar beets, etc., [67]. More details about PLA based NFRPCs can be found in recent papers [56, 68].

2.1 Comparison of natural and synthetic fibers:

Fig. 2(a) and (b) show the comparison of cost per weight, density, environmental compatibility and work safety of natural and synthetic fibers. From these figures, it is observed that natural fibers are cheaper and safer to handle than synthetic fibers. In addition, the density of natural fibers and NFRPCs is lower than E-glass fiber and its composites [2, 69]. Therefore, these materials can be used for numerous applications [70, 71], as shown in Fig. 2(c).

Basalt fiber is a promising fiber among the other natural fibers that possess superior physical and mechanical properties [72]. Basalt fiber is a natural rock fiber, it has higher aluminum oxide and iron oxide content compared to E-glass fiber [73]. As a result, the former has greater chemical degradation resistance and superior mechanical, thermal, impact and vibrational properties compared to the latter [74, 75]. Moreover, the cost of basalt fiber is several times lower and %elongation and impact resistance are higher than that of carbon fiber [76]. Therefore, basalt fiber bridges the gap between E-glass fiber and carbon fiber, and potential to replace E-glass fiber in almost all aerospace, automotive and marine structural applications [72, 76]. However, the

density and cost of flax fiber are lower than the basalt fiber [77], even though the mechanical performance of basalt fiber is superior to that of flax [78]. Therefore, recently, several other researchers performed life cycle assessments on the production and transportation of flax fiber, and reported that flax fiber is the emerging and potential material to replace E-glass fiber in the automotive and aerospace sectors [79].

In general, many other natural fibers possess lower physical and mechanical properties compared to synthetic fibers. Moreover, the natural fibers are easily aged compared to synthetic fibers, when exposed to environmental effects such as moisture and ultraviolet (UV) absorption, temperature and other climate effects, etc., which affect the durability and life span of natural fibers [72, 80]. Therefore, to improve the low desirable properties of both natural and synthetic fibers, the hybridization approach can be used by stacking both the fibers in a polymer matrix [70] or by adding nanofillers in the NFRPCs [74, 76]. The mechanical properties of natural fiber reinforced polymer nanocomposites are higher than GFRP and almost closer to CFRP, as shown in Fig. 2(d). In particular, graphene-oxide, carbon nanotubes, polyethylene terephthalate char and MMT clay are compatible with polymer matrices [81, 82, 83, 84]. These nanofillers can be added in NFRPCs to enhance mechanical and thermal performance. More details about this hybridization approach on various physical and mechanical properties of NFRPCs and SFRPCs are discussed elaborately in recent articles by Gupta et al. [85] and Vigneshwaran et al. [15]. In that way also, natural fibers are playing a vital role in reducing global warming by decreasing the non-biodegradability of synthetic fibers and polymers.

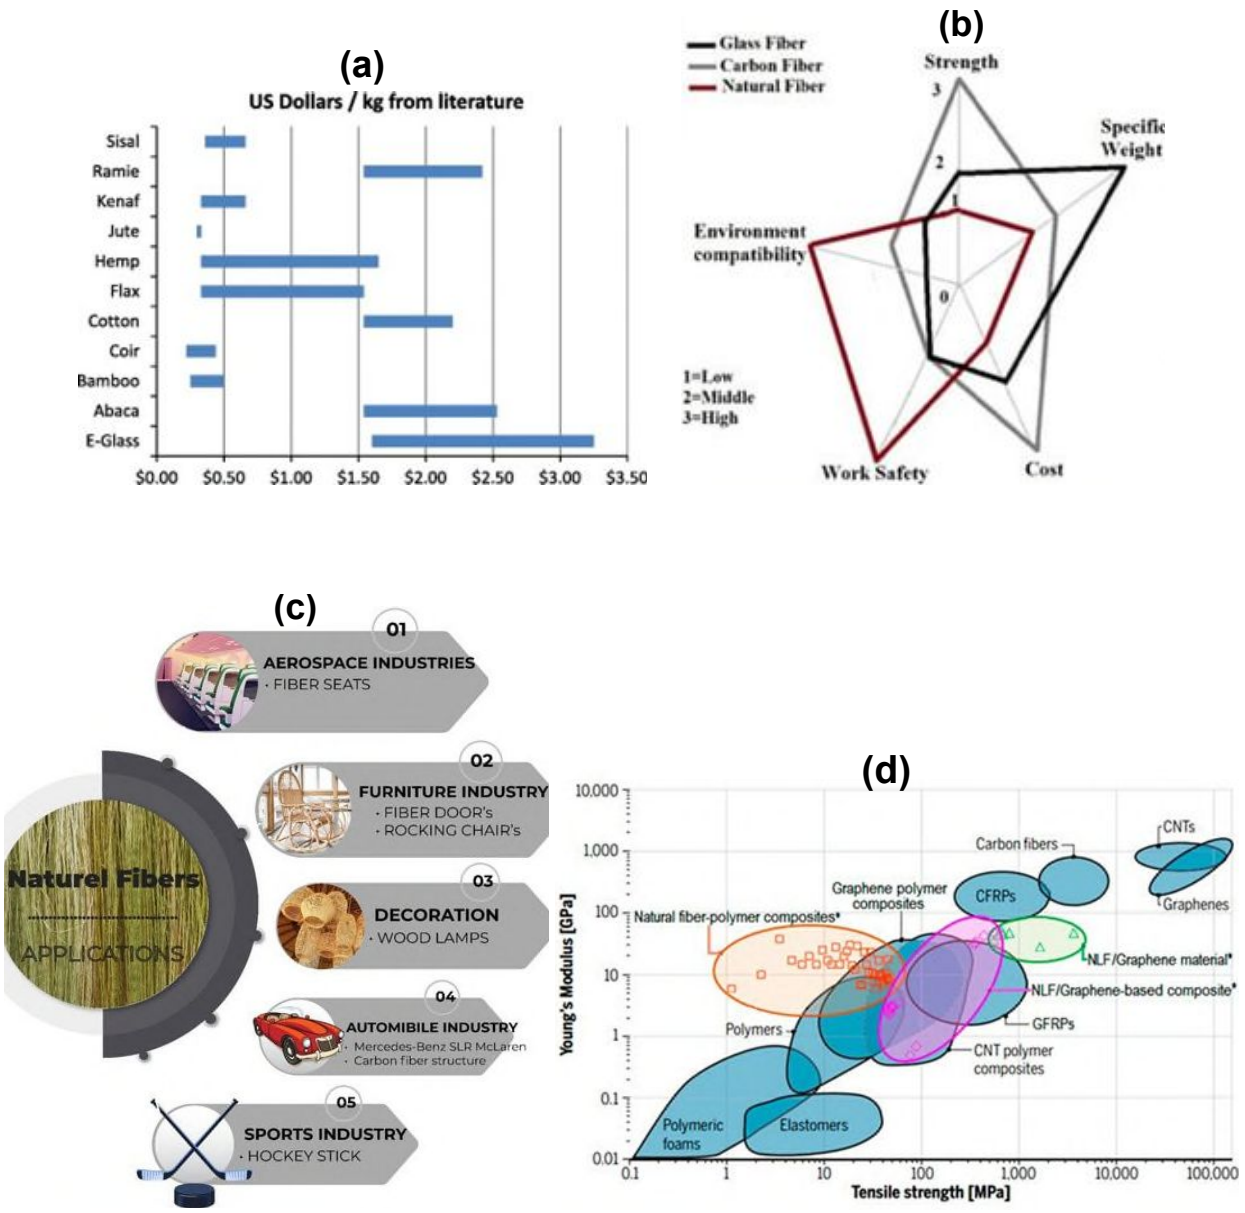


Fig. 2 Comparison of cost per weight, density, environmental compatibility and work safety of natural and synthetic fibers (a, b) Adapted with permission from [86, 87], Copyright Elsevier 2012, Copyright MDPI 2021; Applications of natural fibers and their composites (c) Adapted from MDPI [88], Copyright MDPI 2021; Comparison of mechanical properties of natural and synthetic fibers and their composites (d) Adapted from MDPI [89], Copyright MDPI 2020.

2.2 Recycling and surface treatment of biocomposites

The polymer matrix can be divided into petrobased (non-biodegradable and biodegradable) and biobased (non-biodegradable and biodegradable), as shown in Fig. 3(a). Comparison of the

mechanical properties of these polymers is shown in Fig. 3(b). The thermoset polymers (epoxy, polyester, vinyl ester, etc.,) are non-biodegradable whereas several thermoplastic polymers are biodegradable. From Fig. 3(b), it is observed that the elongation at break (%) of thermoset polymers is lower and Young's modulus is higher compared to most thermoplastic polymers. Among the biodegradable polymers, PLA and PHB have higher Young's modulus and lower elongation at break (%) compared to PBS and PCL. The energy requirement and CO_2 emission are lower with biobased polymers compared to petrobased thermoplastic polymers, as shown in Fig. 3(c).

Recyclability is possible with wood and non-wood natural fiber reinforced thermoplastic polymer composites [90, 91, 92], as shown in Fig. 3(d). This is one of the advantages of using thermoplastic polymers over thermoset polymers. Recently, Manral et al. [21] reported in detail about the processing of natural fiber reinforced thermoplastic polymer composites. Biocomposites can be recycled approximately four to six times until their mechanical properties decrease. The decrease in mechanical properties upon recycling is due to polymer degradation, fiber shortening, decrease in viscosity, poor fiber-matrix adhesion, etc., [93]. Choosing appropriate fiber and matrix materials is necessary to maintain or enhance the mechanical properties of these composites after several reprocessing cycles. It was reported recently [94, 95] that coriander straw fiber and polypropylene (PP) and high density polyethylene (HDPE) matrices are the best materials to maintain the mechanical performance for several reprocessing cycles. Through the chemical treatment of fibers or by adding coupling agents in NFRPCs, the mechanical performance of NFRPCs increases after multiple reprocessing cycles, which resolve the compatibility issues between fiber and matrix [96]. There are different types of chemical treatment (Sodium hydroxide, Acetic acid, Silane, Benzoyl peroxide, Potassium permanganate, Stearic acid, Cellulose powder,

etc.) and surface treatment (plasma, vacuum ultraviolet irradiation, ozone, corona, γ –Ray and laser) methods of natural fibers are available [96, 97]. In general, lignin, pectin, waxy substances, and natural oils are covering the external surfaces of natural plant fiber cell walls, these can be removed through the chemical treatment of fibers. Sodium hydroxide (NaOH) is being widely used chemical treatment to bleach or clean the plant fiber surface [98, 99]. Also, through the process of alkalization, the NaOH reacts with cellulose for changing the fine structure of the native cellulose I to cellulose II. As a result, the surface roughness of the fiber is enhanced, i.e., this network of fibrils exhibits a greater surface area than regular cellulose fibers [100]. Moreover, to increase the adhesion between the natural fibers and the polymer matrix, silane and alkali treatments can be used. These treatments reduce the hydroxyl (OH) functional groups present on the fiber surface, as shown in Fig. 3(e). Therefore, incompatibility issues between fiber and matrix can be resolved and the void content can be reduced [101, 102]. Further details about different chemical treatments used to treat different types of natural fibers are elaborately reported in a recent review article by Ighalo et al. [103].

Surface treatment of fibers helped to improve the mechanical properties [99]. For example, the flexural strength and modulus of Sugarcane bagasse/PP composites increased by 4 and 14%, respectively, after surface treatment of Sugarcane bagasse fiber with the combination of NaOH and silane. The failure strain of hemp/PP composites increases (22%) after six cycles, by adding maleic anhydride grafted polypropylene (MAPP). Similarly, the flexural modulus of Kenaf/PP composites increases (20%) after two cycles, by adding MAPP in it [92]. More details about challenges and opportunities in the recycling of NFRPCs are discussed recently by Zhao et al. [93].

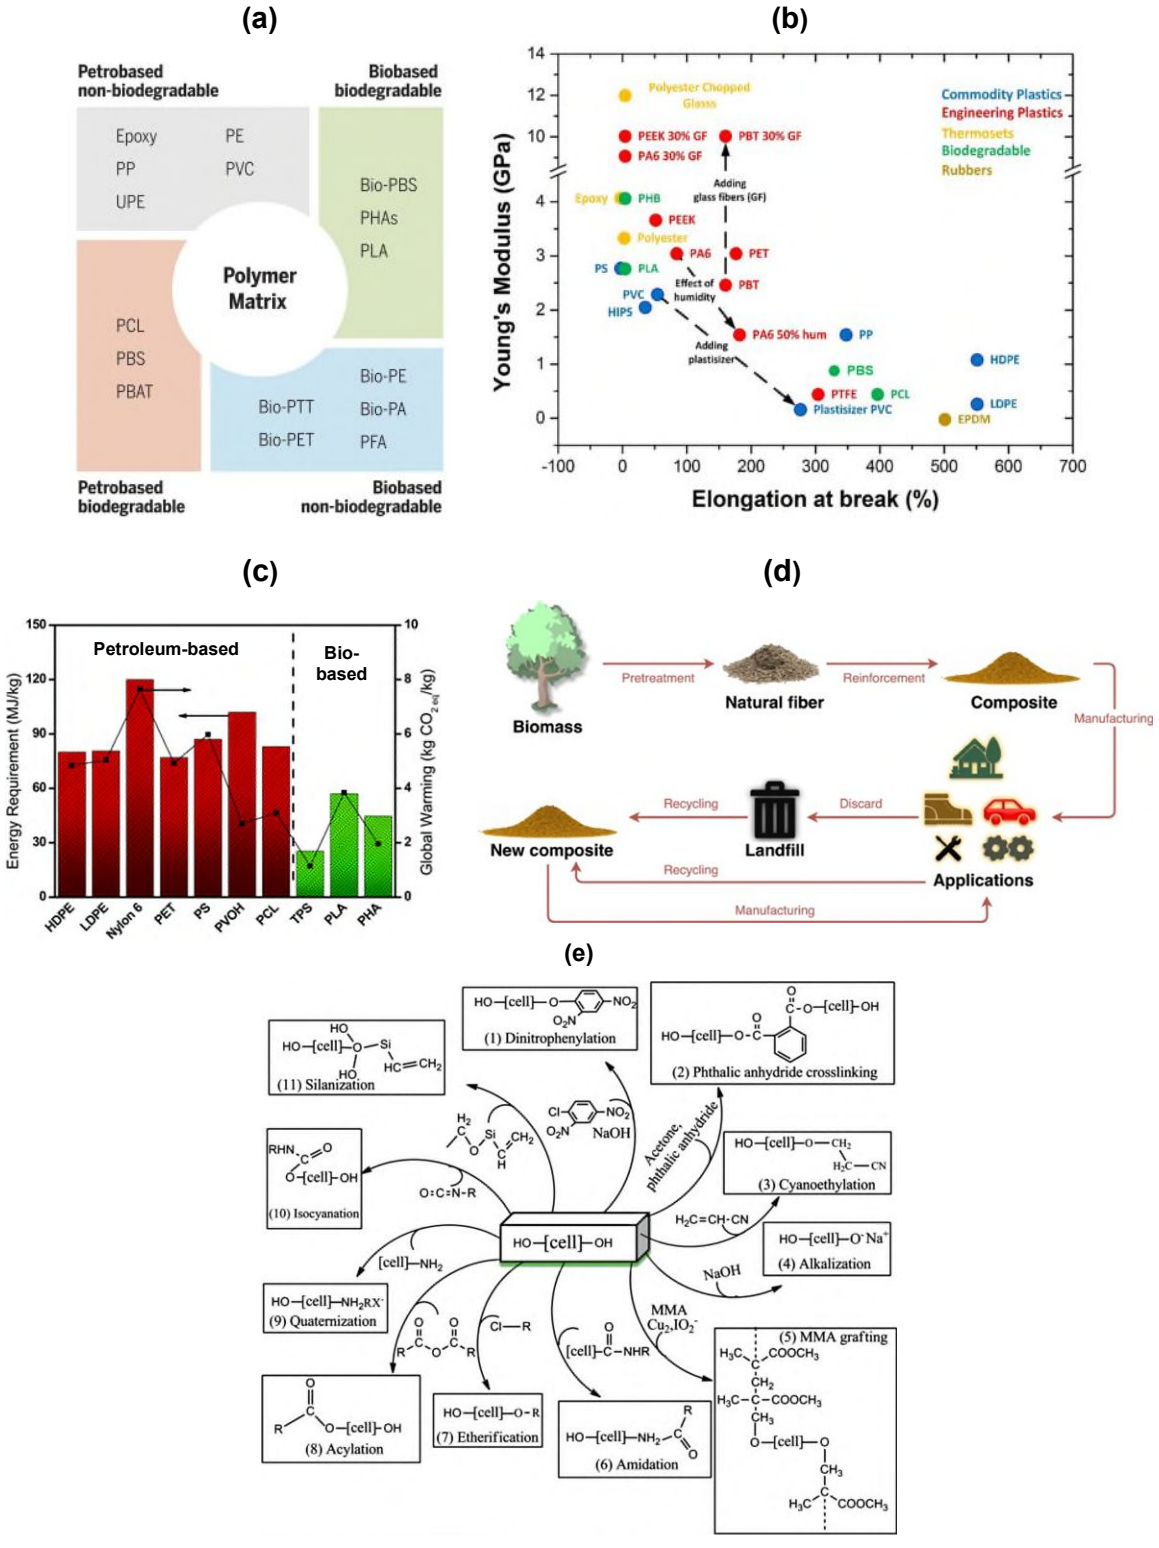


Fig. 3 Different types of petro- and bio-based polymers (a) Adapted from Science [104], Copyright Science 2018, Young's modulus and Elongation at break (%) of different polymers (b) Adapted from MDPI [105], Copyright MDPI 2015; comparison of Energy requirement and carbon emission of petro- and bio-based polymers (c) Adapted from RSC [63], Copyright RSC 2020; recycling of NFRPCs (d) Adapted with

permission from Elsevier [93], Copyright Elsevier 2022; and chemical treatment of natural fibers (e) Adapted with permission from Elsevier [53], Copyright Elsevier 2015.

3. Processing and Mechanical Performance of NFRPCs

The mechanical performance of NFRPCs depends on many parameters such as raw materials, manufacturing techniques and cure cycle process parameters, etc. Choosing raw materials (fiber and matrix) and their properties for a particular application is the essential first step in the processing of NFRPCs [23]. The second step in the processing of NFRPCs is choosing the manufacturing technique. The third step is choosing appropriate cure cycle parameters, e.g., degree of cure, pressure, temperature, etc.

There are several manufacturing techniques available for the fabrication of NFRPCs based on the size and shape of the component, which can be categorized as conventional and modern manufacturing techniques. There are several conventional techniques (hand-lay-up followed by autoclave or out-of-autoclave) [106, 107] which have been used from several decades in fabricating NFRPCs. However, in recent years, modern manufacturing techniques such as automated fiber placement (AFP) and automated tape lay-up (ATL) followed by autoclave or out of autoclave [35, 108], additive manufacturing (AM), etc. [109] have been increasingly used. The component can be fabricated based on the shape of the mold in conventional manufacturing techniques. However, mold is not required in modern manufacturing techniques, these are computer-aided intelligent manufacturing techniques [110]. here, based on the dimensions of the 3D solid model (.standard file format (.STL) file), the component can be printed [111].

3.1. Conventional manufacturing techniques

There are two types of conventional manufacturing techniques, namely out-of-autoclave (OoA) and autoclave techniques [112]. OoA technique can be classified as hand lay-up, spray lay-up, filament winding (FW), compression molding (CM), injection molding (IM), liquid molding (resin infusion (RI) or vacuum assisted resin infusion (VARI) and resin transfer molding (RTM)), vacuum bag only (VBO) prepregs process, pultrusion, etc., [2]. Pultruded products have high stiffness and high fiber volume fraction (closer to 70%) compared to other OoA techniques [113]. In the OoA technique, the first two techniques are open molding processes while the remaining techniques are closed molding processes. The cost of these OoA techniques is relatively cheaper than the autoclave technique. The higher cost and energy required for processing (~21.9 MJ/kg) and size restrictions of the component are the major drawback of the autoclave technique, even though the lowest void content can be obtained [7]. In these conventional manufacturing techniques (OoA and autoclave techniques), the hand-lay-up process is used for stacking the fabric layers with the resin. Further, the manufacturer's recommended cure cycle can be used in curing the samples using either any of the OoA techniques or the autoclave technique [35]. Moreover, the mechanical performance of components fabricated using these techniques rely on post-cure time. Table 1 shows the main process parameters which control the void content in components manufactured using conventional techniques.

Table 1 Main process parameters and applications of conventional techniques

Conventional manufacturing techniques	Main process parameters	Energy (MJ/kg)	Applications	References
Hand layup	Applied pressure, curing time, post-curing temperature and time, etc.	-	All thermoset and thermoplastic	[114]

Spray layup	Spray gun pressure, the mixing ratios of fiber and resin, etc.	15	Chopped strand mat and short fiber reinforced thermoset	[7, 115]
FM	Winding angle, revolution per minute of the mandrel, etc.	3	Thermoset pipes, tubes, shafts, etc.	[74, 76, 116]
CM	Pressure, isothermal dwell temperature, dwell period, etc.	-	Small size thermoset and thermoplastic.	[8, 117, 118, 119]
IM	Injection speed and pressure, temperature, holding pressure, etc.	-	Short fiber reinforced thermoplastic	[21]
RI and VBO prepreg processes	Vacuum pressure, debulking time, dwell temperature and dwell period, etc.	10	Large size thermoset and thermoplastic	[120, 121, 122].
RTM	Pressure, temperature, etc.	15	Small size thermoset	[17, 115]
Pultrusion	Pressure, pull speed, temperature, etc.	3.1	Large size thermoset and thermoplastic	[7, 123, 124]
Autoclave	Pressure, temperature, dwell period, etc.	21.9	Small size thermoset and thermoplastic	[35, 121]

3.2. Modern manufacturing techniques:

Automated or modern manufacturing techniques can be classified as automatic fiber placement (AFP), automatic tape lay-up (ATL) and tailored fiber placement (TFP), additive manufacturing (AM), etc., [108]. More complex geometrical components can be fabricated using these techniques without the requirement of mold, which is the major advantage of these techniques over conventional manufacturing techniques [125, 126]. Chansoda et al. [127] compared the tensile properties of wood-based PLA manufactured using compression molding and AM techniques, and found that the tensile strength values of AM manufactured components are higher, while the compression molded components exhibited higher elongation at break (%) values. Numerous studies related to manufacturing and property characterization of NFRPCs are available with AM techniques [11, 128, 129, 130, 131] and, limited studies have been found with AFP related to NFRPCs [132, 133, 134]. Different advantages and limitations of the AFP technique over conventional techniques are shown in Fig. 4.

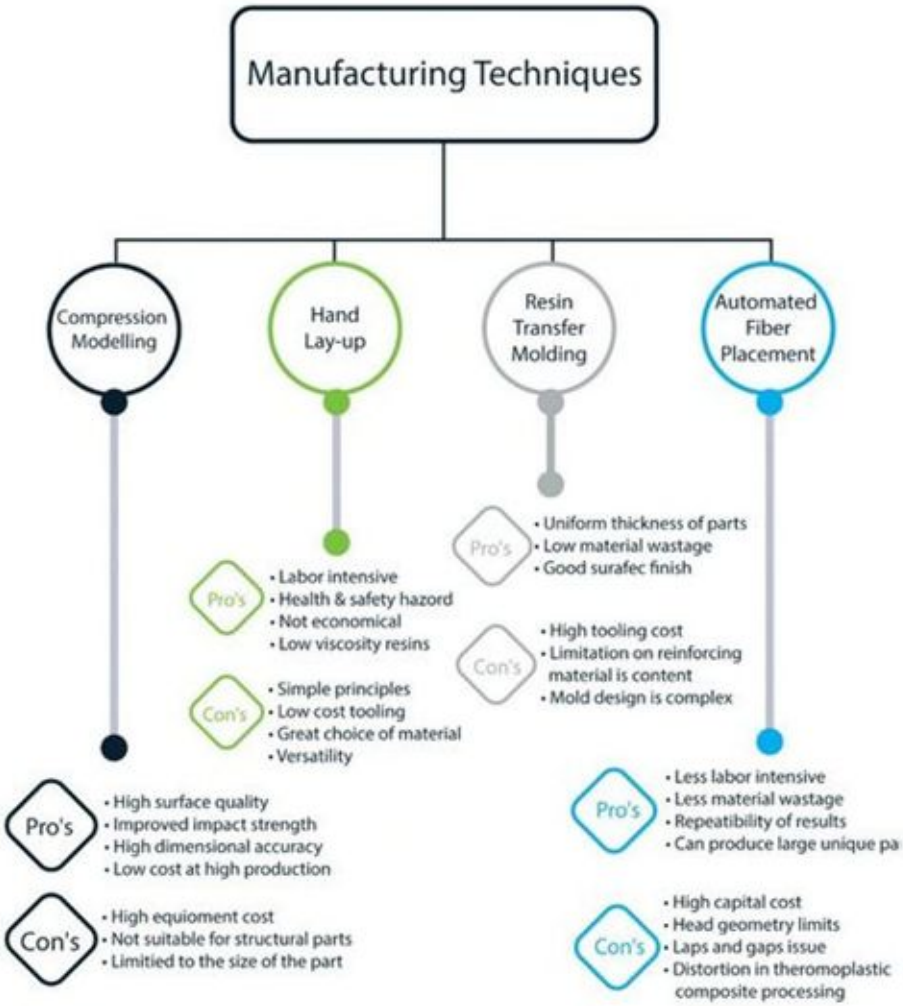


Fig. 4 Comparison of conventional techniques with AFP technique. Adapted from MDPI [88]. Copyright MDPI 2021.

3.2.1 AFP and ATL techniques


AFP and ATL techniques operate with the help of standard industrial robots [135]. The number of publications related to AFP and ATL is limited until 2010. However, Lukaszewicz et al. [108] and Kim et al. [136] reported about AFP and ATL techniques, after that, these techniques are growing enormously. The application of ATL is different from AFP. The former is mainly useful for flat surfaces with small curvature while laying defects (tape folds or tears) can occur when dealing with complex surfaces with high curvature [137]. Therefore, compared to the ATL

technique, AFP provides better structural performance in manufacturing concave or double curvature and variable angle tow laminates with curvilinear fiber paths, owing to the multiple degrees of freedom of its fiber placement head [138]. More importantly, almost all AFP systems can deposit composites approximately at the rate of 6000 cm/min, however, even these can go up to 7500 cm/min, by optimizing the process parameters [87]. Because of these many merits, AFP is being widely used in fabricating numerous large spacecraft structural applications, such as satellites, solid rockets, etc., [139], in addition to primary aircraft structural applications, such as wing, fuselage, etc., [35].

3.2.2 Working principle of AFP

Fiber sliding and fiber bridging are the major problems associated with the conventional filament winding technique, owing to manually operating and changing the fiber orientation angles by humans [140, 141]. These problems can be overcome with the AFP. Fig. 5(a and b) shows the Industry 4.0 stepwise workflow to anticipate defects in AFP manufactured composites, which include mold design, process planning, manufacturing, and inspection based on CAD (computer-aided design)/CAM (computer-aided manufacturing). Mold design includes creating the drawing using CAD software and then importing the file into AFP software [142]. Process planning includes placement path planning and post-processing, in this stage, layup strategies, desired fiber orientation paths and optimizing the position and attitude of the AFP head can be carried out for checking each axis and outputting the motion control file. Further, the AFP head follows the motion paths through the motion simulation software. The motion simulation software reduces material wastage by adjusting the parameters at the right time and continuously optimizes the AFP head paths [143]. The key advantage of running the simulation virtually is to ensure there is no collision or damage to the AFP head and tooling, which could be detrimental.

In general, consolidation of composites using AFP or ATL alone would not provide better results. Instead of that, these techniques can be used only for laying the fibers and then consolidation of composites can be performed using the autoclave or OoA techniques for obtaining better performance. Christophe et al. [133] reported that NFRPCs can be fabricated using the AFP technique. However, the low void content and high fiber volume fraction were obtained using AFP followed by compression molding technique (Fig. 5(d)) as compared to AFP alone (Fig. 5(c)). Sanandiya et al. [134] fabricated a large-scale wind turbine blade made up of fungal-like adhesive material using infused AFP and AM techniques, as shown in Fig. 5(e).

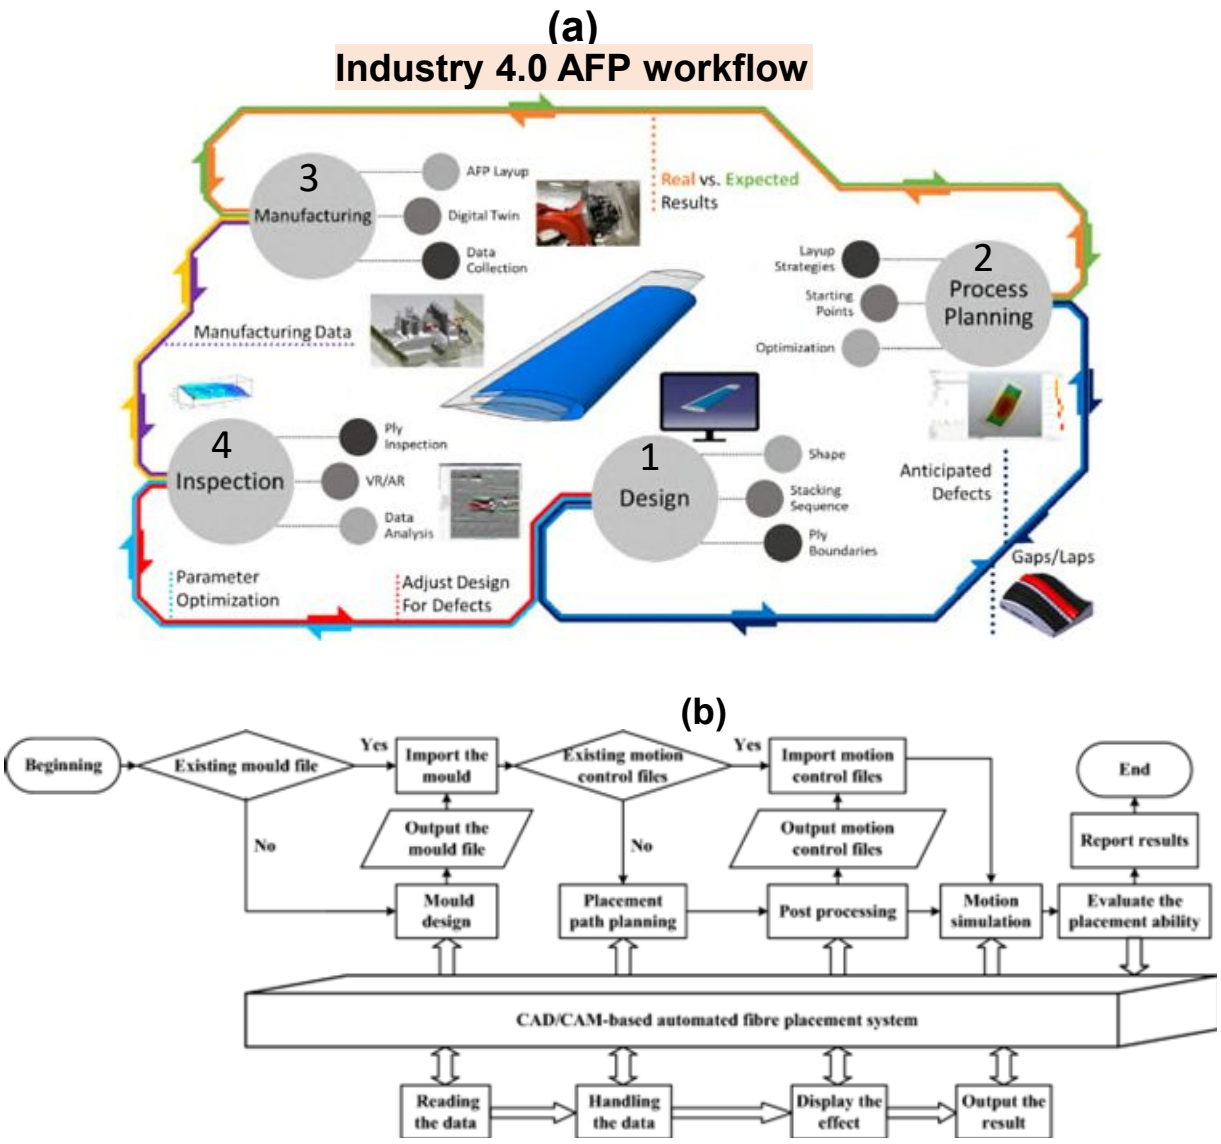

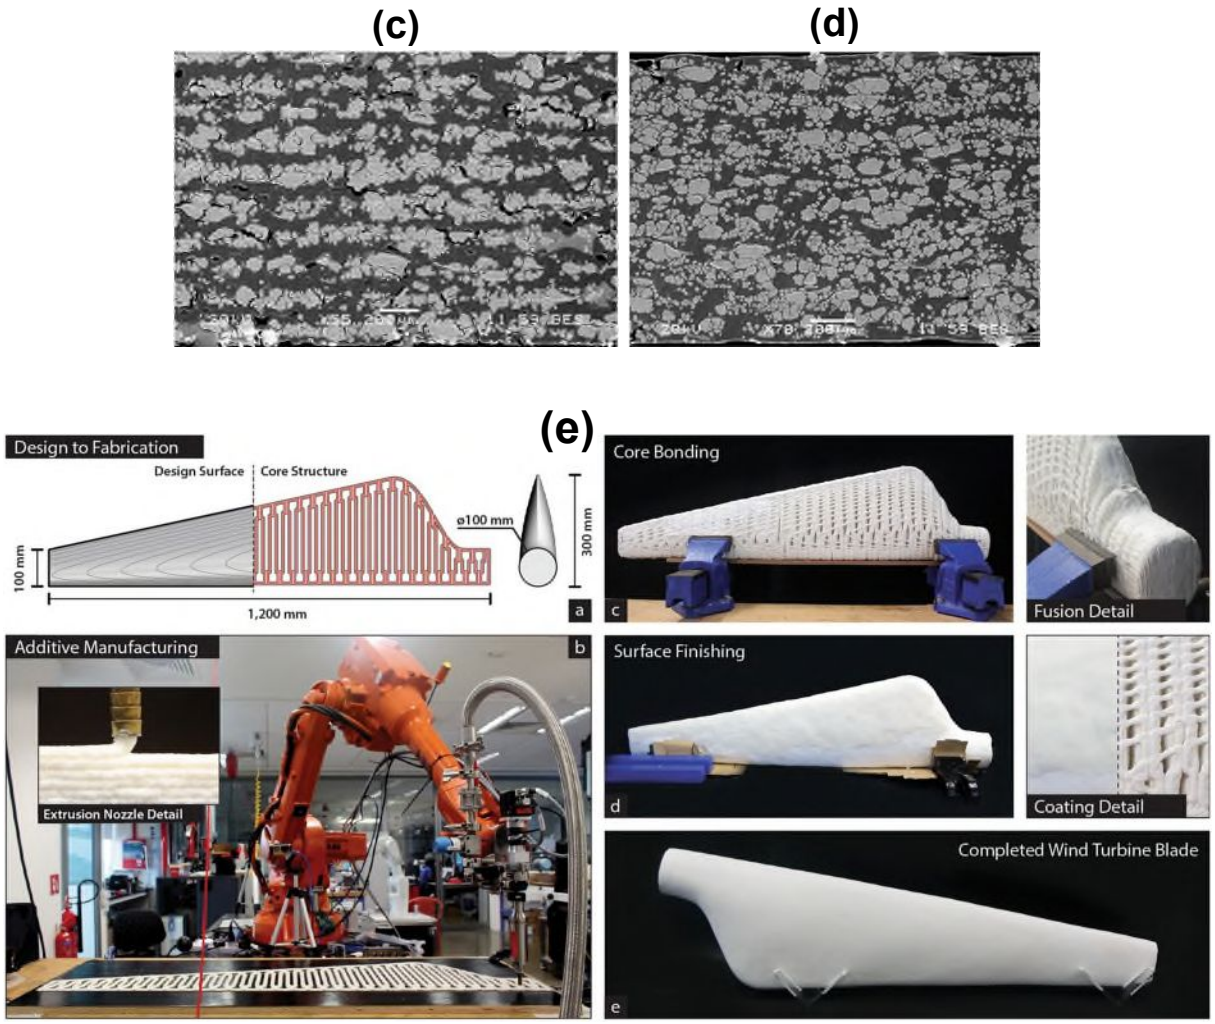


Fig. 5 Working principle of AFP manufactured composites based on CAD/CAM (a) Adapted with permission from Elsevier [144], Copyright Elsevier 2021 and Adapted from Springer [137] (b); Flax/PP composites manufactured using AFP (c) and AFP + Compression molding (d) Adapted from Elsevier [133], Copyright Elsevier 2016; Large scale wind turbine biocomposite blade made up of fungal-like adhesive material(s) (FLAM) using AFP (e) Adapted from Scientific reports [134], Copyright Scientific reports 2018.

3.2.3 Additive Manufacturing techniques

Different types of AM techniques, such as fused deposition modeling (FDM) or fused filament fabrication (FFF), stereolithography (SLA), digital light processing (DLP), two-photon polymerization (TPP), powder bed fusion (PBF), selective laser melting (SLM), binder jetting (BJ), selective laser sintering (SLS), laminated object manufacturing (LOM), sheet lamination

(SL), material jetting (ML), liquid deposition modeling (LDM), etc., [145, 146], are shown in Fig. 6(i)(a) and (b). These techniques fabricate the component based on the dimensions of the 3D solid model (.standard file format (.STL) file [11, 147]. FDM is suitable for thermoplastic composites while photo-curing AM techniques (SLA, TPP, direct ink writing, etc.) can be used in UV-curable thermosets. Also, the accuracy and resolution of photo-curing techniques are higher and mechanical properties are lower compared to FDM [148]. The working principle, advantages and disadvantages of these different types of AM techniques are reported in detail [11, 149]. Different types of fibers and matrix materials are suitable to use in different AM techniques for various applications, which are reported in detail by Fidan et al. [150]. AM market has been growing continuously in the past decades and has reached 21 billion U.S. dollars in 2021, as shown in Fig. 6(i)(c).



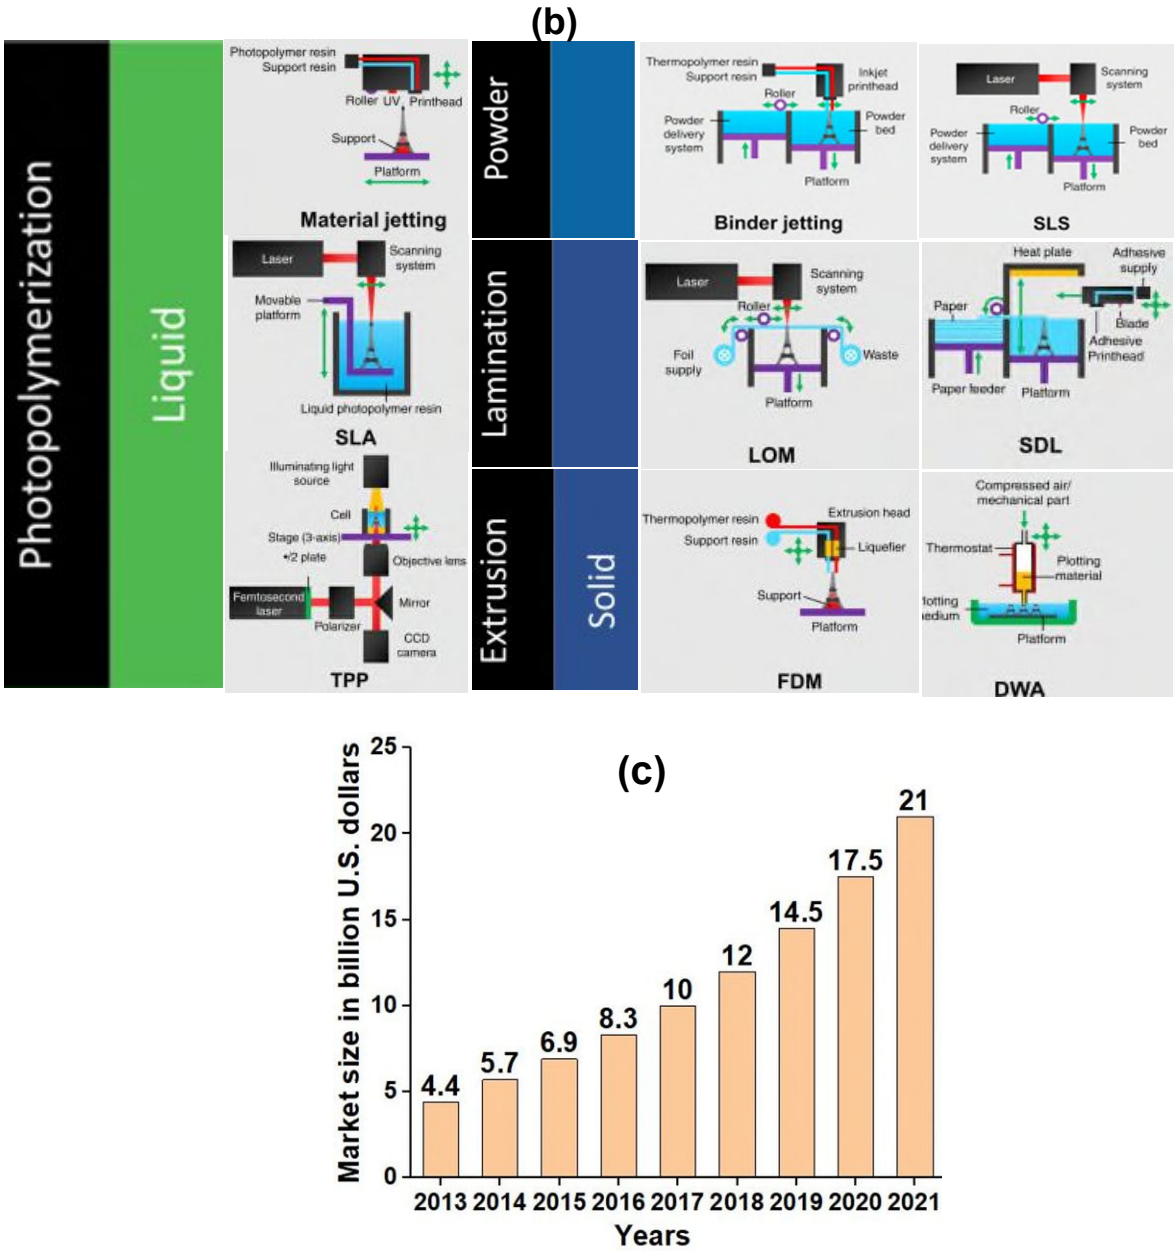


Fig. 6(i) Applications and types of AM techniques (a, b) Adopted from [151, 152]; AM Market size (c) Adopted from MDPI [153], Copyright MDPI 2022.


3.2.4 Processing parameters in modern manufacturing techniques


Modern manufacturing techniques contain higher processing parameters compared to conventional manufacturing techniques [35, 154]. For example, in AFP and ATL techniques, the processing parameters include but are not limited to temperature, compaction force or pressure,

fiber placement head, lay-up speed, etc., [155, 156]. The process parameters in AM techniques include but are not limited to print speed, nozzle and bed temperature, printing pattern, build orientation that includes flat, on-edge and upright, etc., [149, 157], as shown in Fig. 6(ii) (a). Optimizing these process parameters are time-consuming, moreover, the quality of the final product relies not only on printing parameters but also on factors related to preparatory parameters and machining [158, 159]. As a result, the possibility of defects owing to these several process parameters is high in additive manufacturing techniques [160]. Moreover, owing to the layer-by-layer printing process, the possibility of forming voids is higher in AM techniques [125, 161]. Further challenges (thermal degradation, water or moisture absorption, distribution of fibers in the resin, fiber breakage, uneven surface finish, etc.) associated during and post-manufacturing of NFRPCs using AM techniques are reported in recent articles [11, 111, 162]. These all are the main reasons for the limited studies available in fabricating of NFRPCs. Among the various AM techniques, the FDM technique is one of the most widely used techniques in fabricating NFRPCs in literature [130]. This is owing to low cost, easy operating procedure and low material wastage and shortening the design-manufacturing time [163]. However, the cost and operating procedure of FDM printed components rely on the type of thermoplastic polymer used for fabrication [147]. Different types of thermoplastic polymers can be used in FDM based on the application of the component, as shown in Fig. 6(ii)(b). However, still, several challenges are existing in the processing and development of high-temperature polymer feedstocks for FDM [125].

On the other hand, the processing of natural fiber reinforced thermoplastic composites using the injection molding technique is easy and the quality of the component is more reliable compared to the FDM technique [61]. Moreover, the specimen fabrication time is very less in this technique compared to the FDM technique. Therefore, the injection molding technique is the best

suitable one for mass production applications [126]. However, the major drawback is the higher capital investments, which require both extruder and injection molding machines to fabricate composites, as shown in Fig. 6(ii)(c). Also, complex geometrical components are difficult to fabricate using this technique, it demands separate molds.

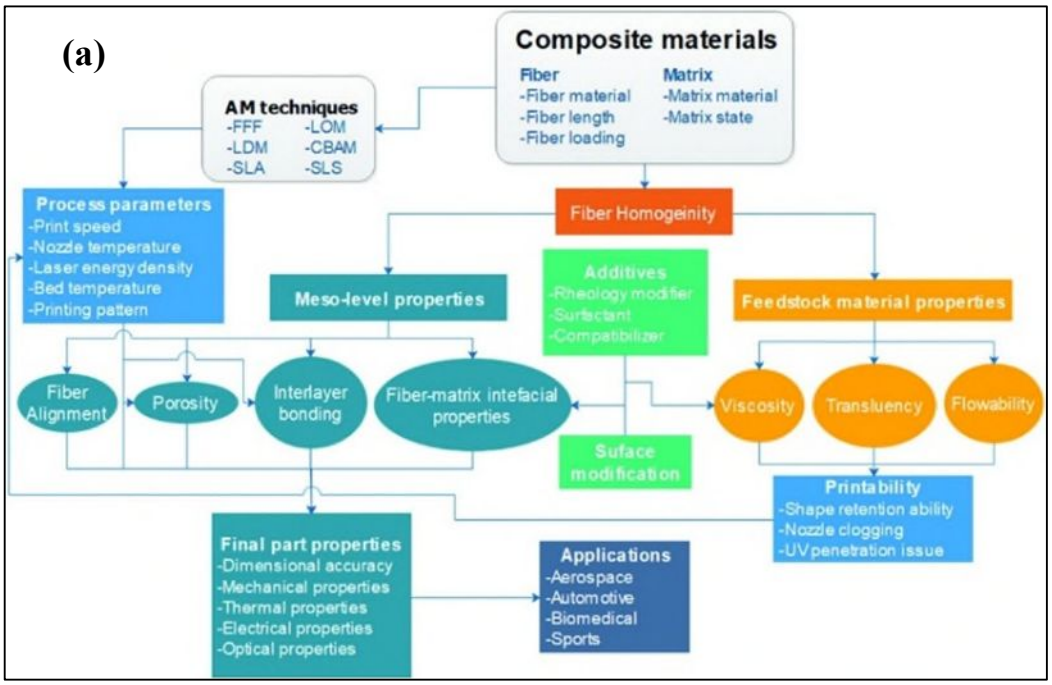

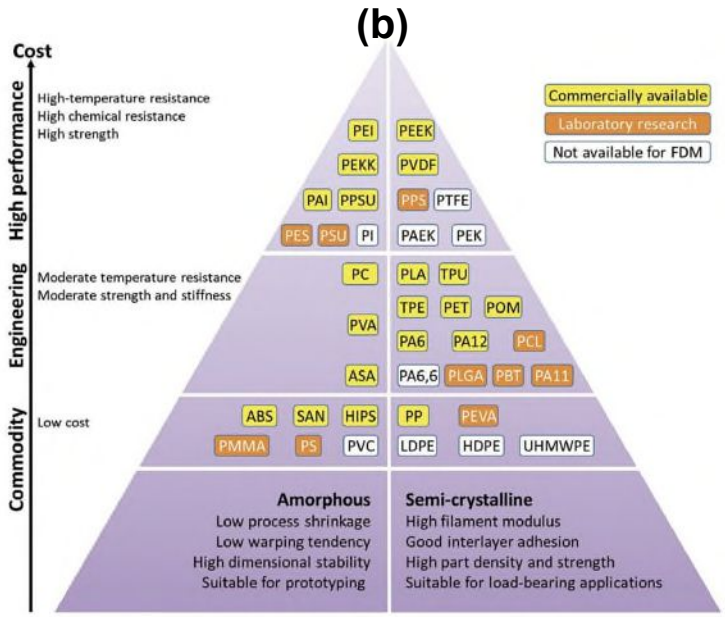

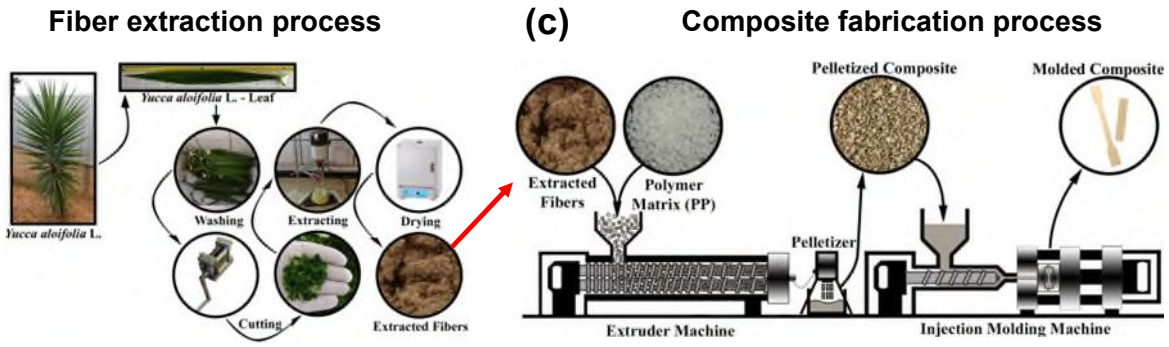


Fig. 6(ii) Process parameters of AM composite techniques (a) Adopted from MDPI [164], Copyright MDPI 2021; types of polymers available for FFF (b) Adopted from Oxford Open Materials Science [165]; Yucca aloifolia L/PP fabricated using twin-screw extruder followed by injection molding (c) Adapted with permission from Elsevier [166], Copyright Elsevier 2021.

3.2.5 Remedies to overcome the challenges of modern manufacturing techniques

The biggest challenge with modern manufacturing techniques is controlling the formation of defects during the manufacturing of NFRPCs. The remedies to control the formation of defects are: studying several process parameters and optimizing the best parameters, however, this approach is time-consuming. The other remedies are discussed below.

(i) In-situ inspection is the best possible way to control defects during the manufacturing of composites. Ingersoll Machine Tools (IMT) at the McNair Center developed the Advanced Composite Structures Inspection System (ACSIS) AFP, as shown in Fig. 7(a) [167]. ACSIS is a layer-by-layer in-situ monitoring system that consists of Kuka KR120 robotic arm with 4 laser profilometers, i.e., each layer could be scanned completely by ACSIS through the high resolution profilometer, immediately after laying down each layer by the AFP machine. After completing the scan for the first layer, the layup of a new layer can be carried out by moving the AFP mandrel back to its original position. This procedure can be continued for layup and scanning of each layer. The ability of ACSIS software is that it automatically operates the robotic arm and stores all captured images [168]. More importantly, AI-based algorithms are in-built into the software which

identifies layer-wise defects, as shown in Fig. 7(b). The defects captured are initially trained to the machine learning (ML) software with different color coding, as shown in Fig. 7(c, d). Further, the defects in the composites can be detected automatically using ML methods, as shown in Fig. 7(e). Further details about the ACSIS in-situ monitoring technique are discussed in recent articles [167, 168, 169].

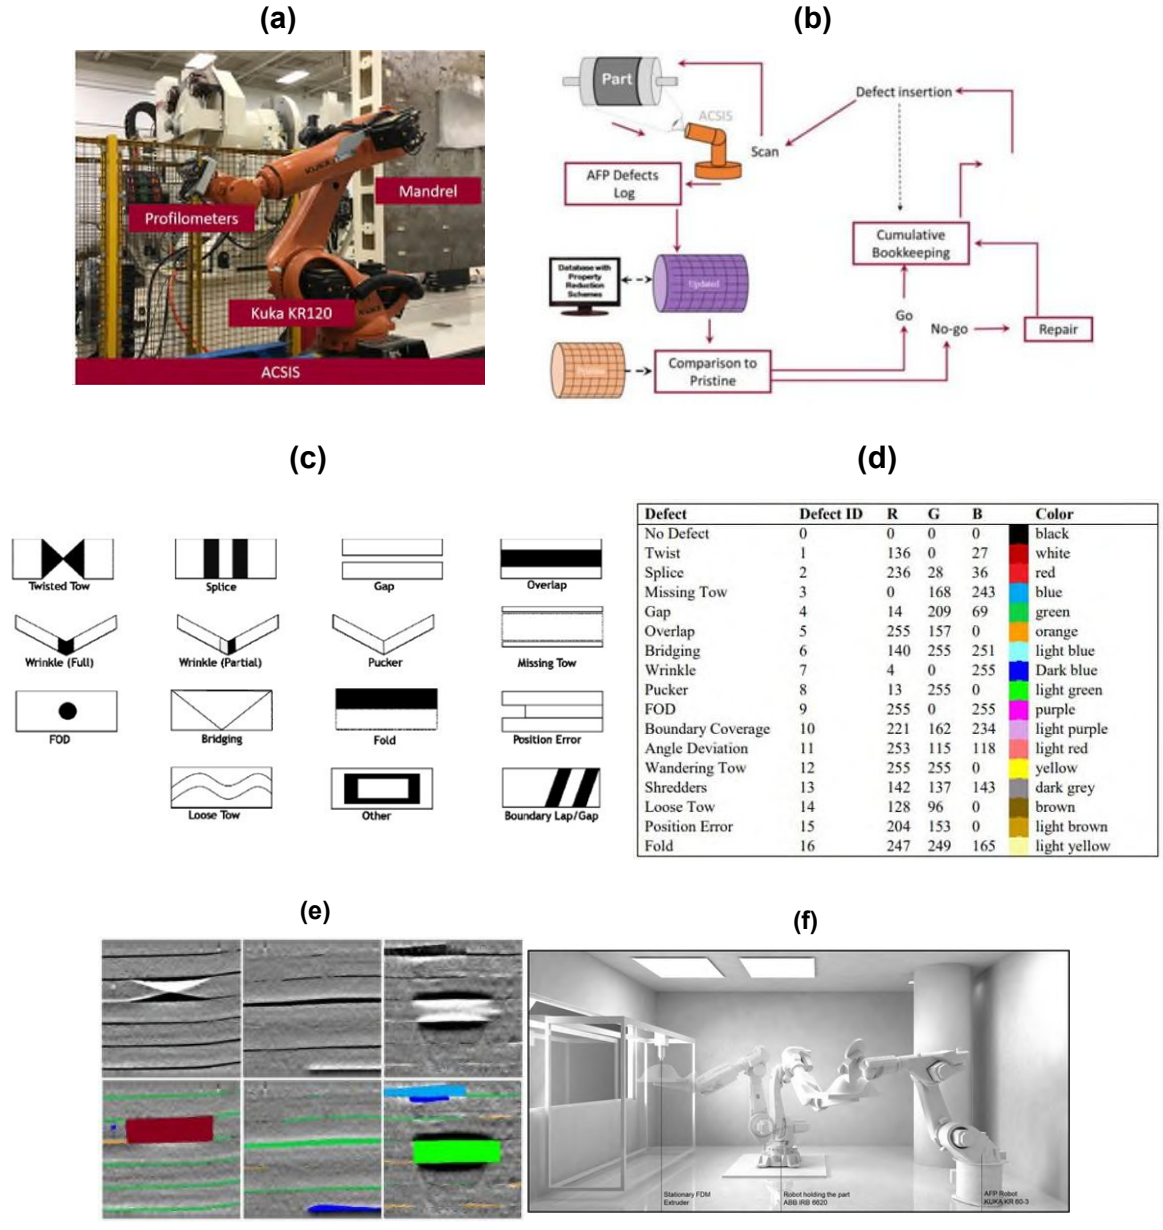


Fig. 7 In-situ defect monitoring in AFP using ACSIS (a) Adapted with permission from Elsevier [167, 169], Copyright Elsevier 2020 and Adapted from NASA Technical Reports (b) [170]; training defect data in ML

(c-d) Adapted from thesis [171]; automatic defect detecting using ML methods (e) Adapted from Elsevier [144]; fusing modern manufacturing techniques (AFP and AM) (f) Adapted from Taylor & Francis [172].

(ii) The AFP manufacturing time can be reduced by optimizing the process parameters through numerical simulation tools. Several software packages are available to perform AFP numerical simulations. Vistagy Inc [173] has developed Fibre SIM software, through this material wastage can be minimized and product quality can be enhanced by optimizing placement path planning, machine parameter setting and error analysis, etc. Also, Coriolis Composites [174] has developed CAD Fibre and CAT Fibre, which consist of programming, simulation and post-processing modules of AFP. AFP simulation with CAD Fibre software works based on CATIA version 5, it can be used for designing molds and then importing the mold files into the simulation interface [175]. In addition to these, FiberGrafiX was developed by Entech [176] to perform AFP simulation in studying the various process parameters.

(iii) Integration of AFP and FDM could reduce the time consumption for optimizing the process parameters. The other advantage of this technique is that the composites can be fabricated even using FDM alone or AFP alone or combinedly (integrated approach), as shown in Fig. 7(f). This approach was employed by Raspall et al. [172], and fabricated the composites at a lower time. Also, this integrated approach was employed by few researchers to fabricate large-scale biocomposite components [175, 177]. The in-situ defect monitoring system, ACSIS can be built in this integrated technique to study the layer-wise defects, such that the manufacturing defects can be reduced [178].

(iv) Replacing the AFP technique with the tailored fiber placement (TFP) technique:

Several defects such as local fiber buckling and wrinkling, gaps and overlaps, etc., are associated during the lay-up process with the AFP (Fig. 7(d)) technique [22]. However, to replace

this technique for overcoming these defects [179, 180], recently, numerous researchers have been employing the TFP technique to fabricate highly curvilinear NFRPCs parts [181, 182, 183]. TFP makes use of an embroidery machine that continuously lays the dry fiber filaments and stitches them to the textile substrate [180]. This technique works based on the desired fiber placement program generated by a CAD file, which is imported to the embroidery machine to tailor the fiber orientations. The stitch length and stitch width are the main parameters of the TFP technique [183]. The angle of fiber placement using this technique can be varied easily between 0º to 360º [182, 183]. After creating a desired structural pattern of fabric architecture through stitching and bending, based on the CAD file imported into the embroidery machine, the resin can be impregnated using the autoclave or any one of the OoA techniques [183, 184]. TFP technology has been used effectively, not only in thermoset polymer composite applications but also in thermoplastic polymer composite applications [185, 186].

TFP can be used in all manufacturing techniques of AFP could be used, with fewer defects [180, 187]. This technology is being widely used in the buckling optimization of composite cylinders with the filament winding technique [188]. Uhlig et al. [187] reported that the TFP technique is well suited for fabricating the variable axial (variable angle tow and stiffness) composites. These variable axial composites are well suited for improving the buckling and post-buckling response of composite plates [189]. Further details about these composites can be found in [180].

3.3 Machining of NFRPCs:

Machining is an important step before performing the mechanical tests on composites. Mechanical properties of composites depend on the machining characteristics of composites. There are two types of machining: (i) conventional machining, which includes turning, drilling,


milling, grinding, etc., and (ii) Unconventional machining, which includes water jet machining, laser machining, ultrasonic machining, electric discharge machining, etc., [190].

Machining induced defects and damages are higher in NFRPCs compared to SFRPCs**,** owing to high surface roughness and rapid occurrence of damage mechanisms (delamination, fiber-matrix debonding, fiber pull out, etc.) during the machining process [191]. Therefore, it is important to study the machining characteristics of NFRPCs, however, the challenges associated with these are higher [192]. The studies related to machining characteristics of NFRPCs are limited compared to SFRPCs [132, 193]. Raj et al. [190] reported in detail the challenges associated with the machining characteristics of NFRPCs. It is important to use NDE techniques for online monitoring of NFRPCs during machining for reducing defects [33, 194] and the digital twin models can be developed in minimizing the challenges associated with the machining of NFRPCs [195]. Different NDE techniques can be used, which are discussed in Section 4.1.

3.4 Mechanical property characterization of NFRPCs

Different types of mechanical tests can be performed on NFRPCs by varying the strain rates from 10^{-8} to 10^{8} s^{-1}, as shown in Fig. 8(a) [196]. The tensile properties of different fiber weaving architectures of composites, with different conventional OoA manufacturing techniques are shown in Fig. 8(b). From the figure, it is observed that unidirectional fiber reinforced polymer composites (FRPCs) exhibited the highest tensile properties followed by woven roving mat FRPCs. RTM, CM and RI are the commonly used manufacturing techniques in fabricating continuous FRPCs. Among these techniques, RTM exhibited better tensile properties compared to compression molding and RI. This is due to the possibility of a higher fiber volume fraction of RTM compared to the other techniques. Injection molding is mainly used for manufacturing short

random FRPCs, it exhibited the least properties. The mechanical properties of woven NFRPCs are better and more stable compared to random NFRPCs [197]. In particular, intraply composites are gaining interest in recent days, owing to their excellent impact resistance capability compared to interply composites [14, 198, 199]. From Fig. 8(c), it can be seen that the modern manufacturing techniques ATL + autoclave exhibited higher tensile strength than conventional manufacturing techniques. Moreover, FFF exhibited higher strength and fiber volume fraction than injection molding and hand lay-up + RI processes. Although the requirement of mold is not required in these techniques, higher strength and fiber volume fraction can be attained in these modern manufacturing techniques. Moreover, Fig. 8(d) shows the lower scrap rate of modern manufacturing techniques, compared to conventional manufacturing techniques. The lower the scrap rate, the higher would be the sustainability and lower would be the product cost [200].

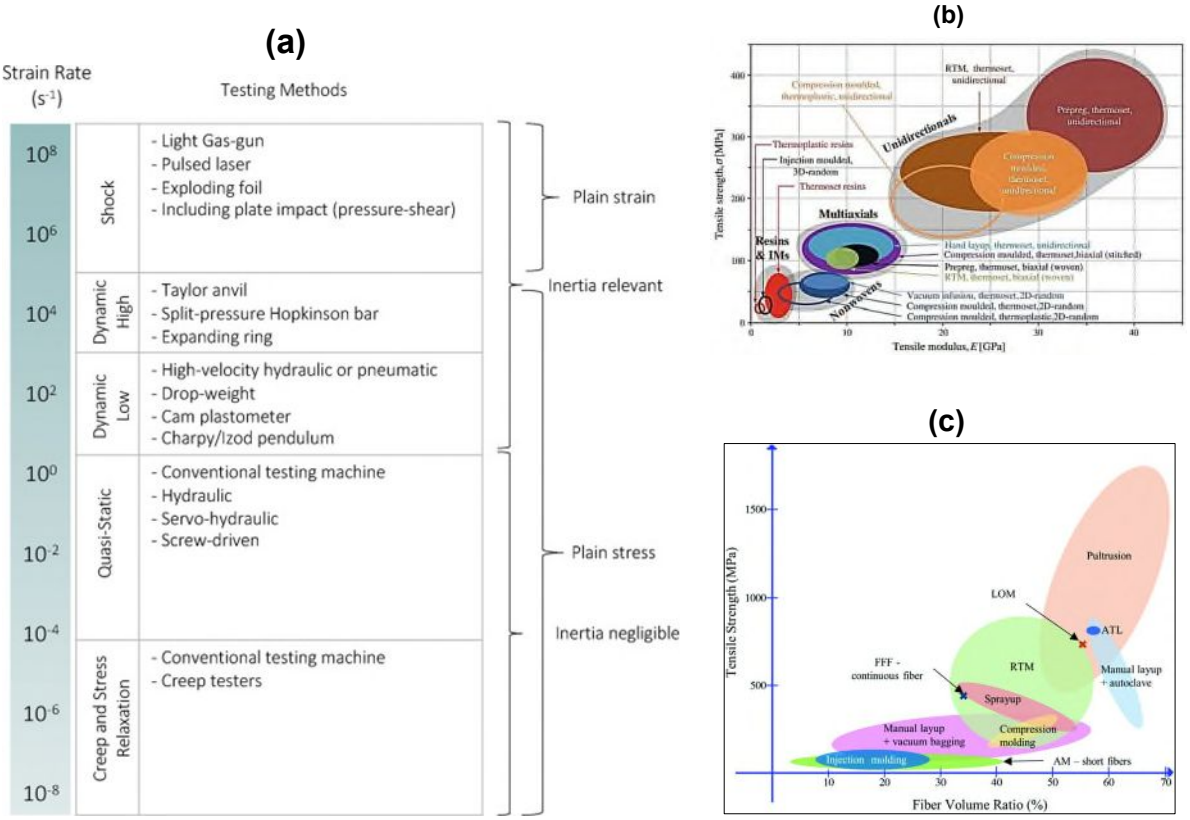

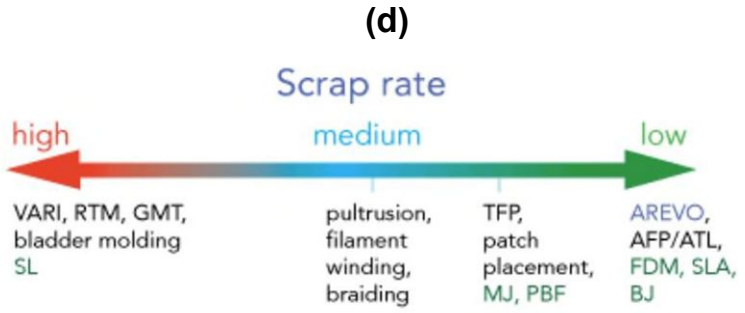



Fig. 8 Effect of strain rate on different mechanical tests of biocomposites (a) Adopted from Elsevier [196]; Comparison of tensile properties of polymers and different fiber weaving structures of composites using different manufacturing techniques (b) Adapted with permission from Elsevier [201], Copyright Elsevier 2014; comparison of tensile strength vs. fiber volume fraction between conventional and modern manufacturing techniques (c) Adopted from [149]; comparison of scrap rate between conventional and modern manufacturing techniques (d) Adopted from [200].


Mechanical (tensile, flexural, water absorption, vibration, low velocity impact (LVI), etc.,), thermal and fire resistance properties of NFRPCs fabricated using conventional [70, 72, 114, 202, 203, 204] and automated manufacturing [11, 109, 126, 130] techniques, are reported and discussed by several researchers. However, the studies related to medium or high velocity impact loading of NFRPCs are limited [52], except very few papers [205, 206, 207, 208, 209, 210]. High velocity impact (HVI) studies can be performed using the air gun [210, 211]. Moreover, the studies related to high strain rate studies of NFRPCs are limited, except very few papers [198, 212]. High strain rate studies can be performed using a drop mass tower [213], Split-Hopkinson Pressure Bar (SHPB) [214], etc. It is important to perform further studies related to HVI and high strain rate properties of NFRPCs to understand the material behavior under dynamic loading events. For example, bird strikes the aircraft, hailstones hit the wind turbine blades, etc., to protect the structure from catastrophic failure [215, 216].

The present work is not aimed at reporting the physical and mechanical properties of NFRPCs fabricated using different manufacturing techniques. Rather, the focus of this review paper is to discuss in detail for effective utilization of NDE techniques in understanding the process of defects generation that occurred at different stages of manufacturing. Subsequently, utilize NDE results to enhance the mechanical performance of NFRPCs. It is essential to investigate the microstructure of NFRPCs using NDE techniques for verifying the final component quality. Also, post characterization, investigating the microstructure of tested NFRPCs using NDE techniques is equally important to understand the failure mechanisms of composites such that the residual properties of composites cannot be degraded [217, 218]. Different types of NDE techniques will be discussed in Section 4.1.

4. Destructive and non-destructive evaluation techniques and generation of digital twins

In general, surface defects and dislocations or microfibrils (kink-bands, slips, etc.) in cell walls of natural fibers can be investigated using destructive techniques, such as microscopy (Normal light microscope, Polarized light microscope and Fluorescence microscope) and scanning electron microscopy. As compared to destructive techniques, NDE techniques can provide clear information and would not affect the residual properties of NFRPCs [35]. However, both destructive and NDE techniques are used as input parameters in modeling of NFRPCs using finite element (FE) analysis for studying the mechanical properties [36, 43, 219], as shown in Fig. 9(a). However, the present review article is mainly focusing on NDE techniques of NFRPCs. Figs. 9(b) shows the NDE inspection and its aided real and geometric modeling and Fig. 9(c) shows the digital twin (DT) concept in smart manufacturing and its applications in various fields.

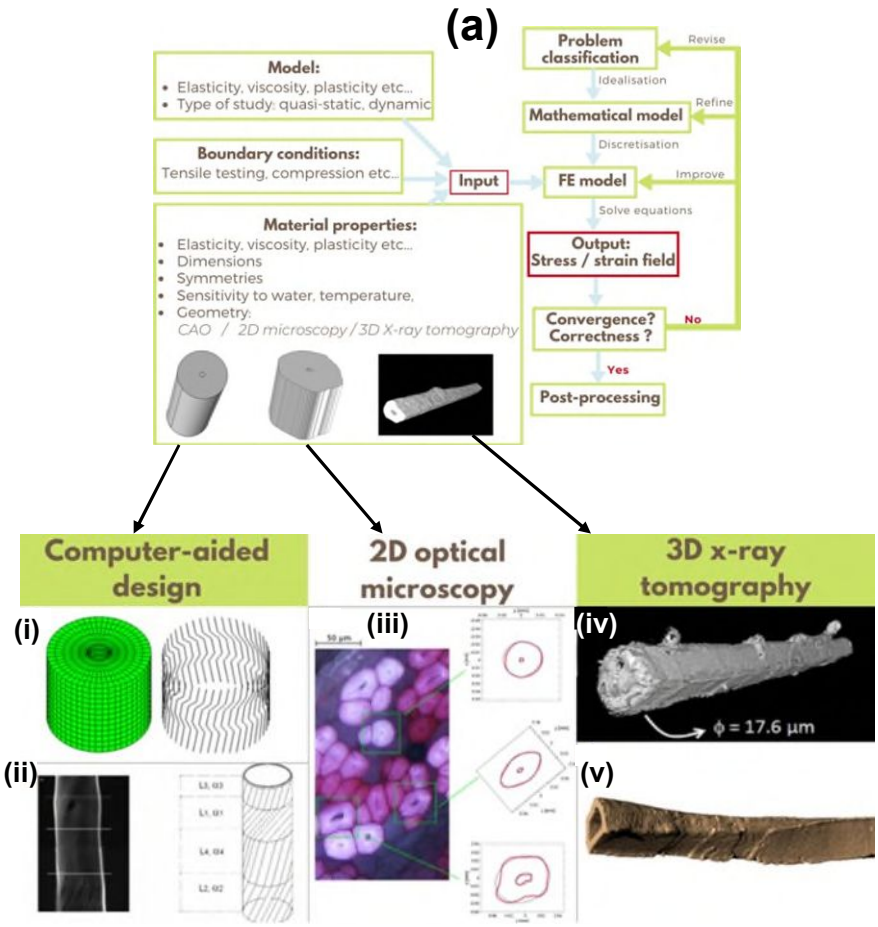
(a)
Problem classification
Revise
Idealisation
Mathematical model
Refine
Discretisation
Model:
Elasticity, viscosity, plasticity etc...
Type of study: quasi-static, dynamic
Boundary conditions:
Tensile testing, compression etc...
Input
FE model
Improve
Solve equations
Material properties:
Elasticity, viscosity, plasticity etc...
Dimensions
Symmetries
Sensitivity to water, temperature,
Geometry:
CAO / 2D microscopy / 3D X-ray tomography
Output:
Stress / strain field
Convergence?
Correctness ?
No
Yes
Post-processing
Computer-aided design
2D optical microscopy
3D x-ray tomography
(i)
(ii)
(iii)
(iv)
(v)
ϕ = 17.6 µm

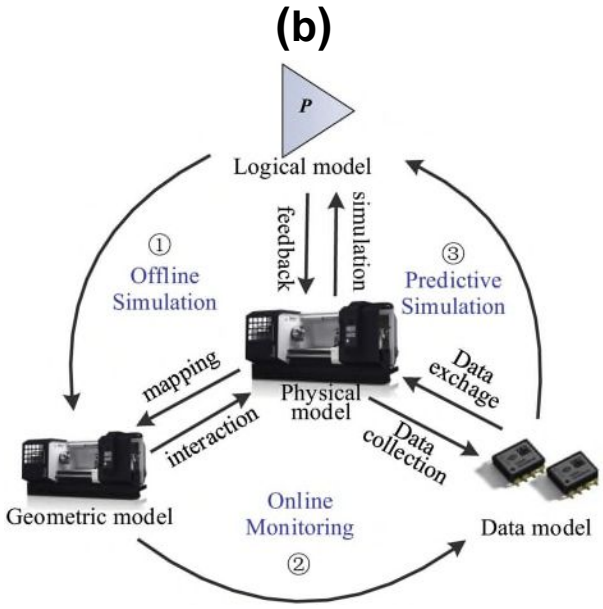
(b)
P
Logical model
feedback
simulation
①
Offline Simulation
③
Predictive Simulation
mapping
interaction
Physical model
Data exchage
Data collection
Geometric model
Online Monitoring
②
Data model

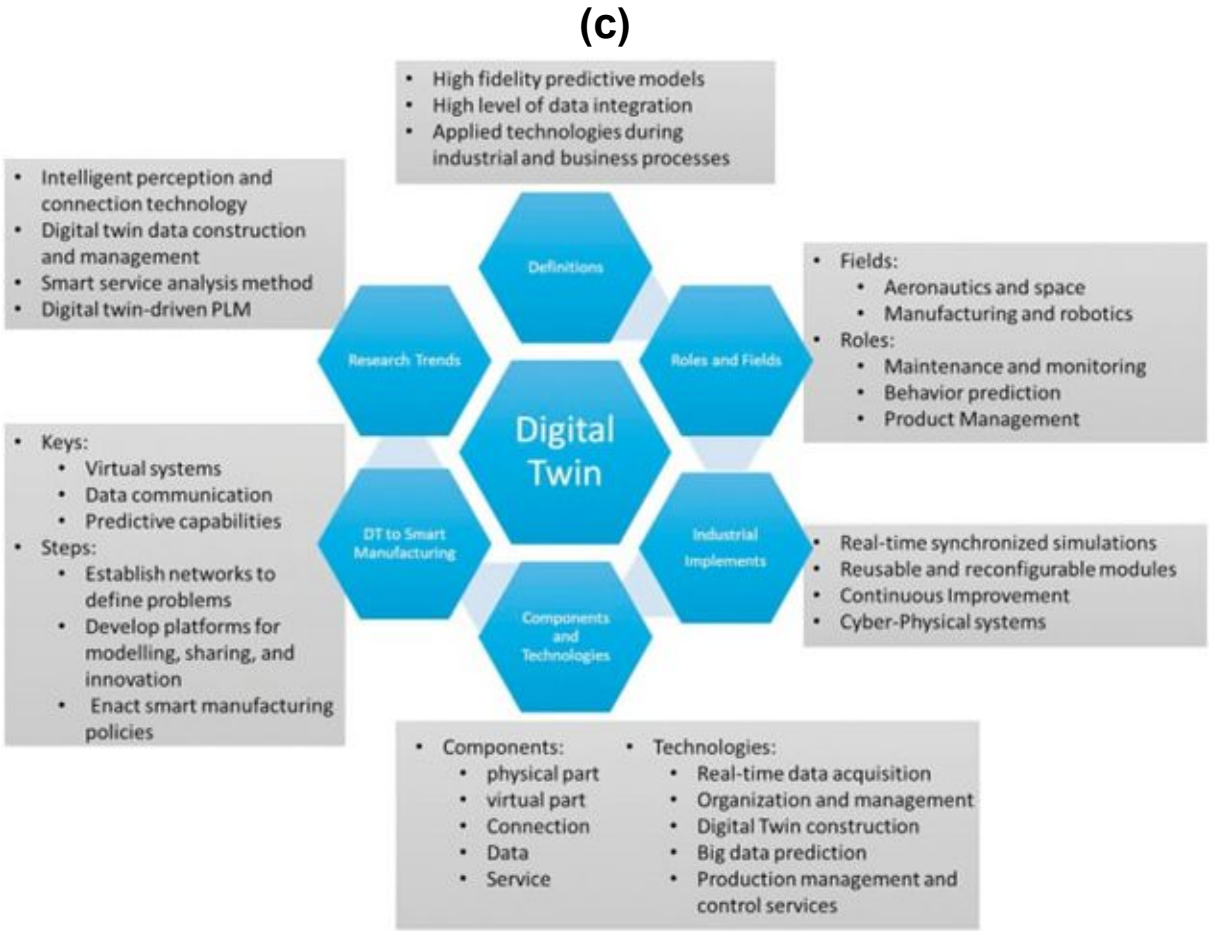



Fig. 9 Estimation of stress-strain fields in hemp/pp composites using FE modeling based on microstructural properties as input obtained using destructive and NDE techniques (a) Adapted with permission from Elsevier [43], Copyright Elsevier 2022; NDE aided real and geometric modeling (b) Adapted with permission from Elsevier [220], Copyright Elsevier 2020; digital twin concept and its application in various fields (c) Adapted with permission from Elsevier [221], Copyright Elsevier 2021.

4.1 Types of non-destructive evaluation techniques


Different sizes of defects can be induced in composites at different stages, such as manufacturing, in-service and maintenance, as shown in Fig. 10(a). These defects can be identified using NDE techniques [222]. From Fig. 10(b)(i), NDE techniques in inspecting composites manufactured using conventional and modern manufacturing techniques are divided into five groups. These techniques can be further divided into contact and non-contact techniques [223,

224]. Fig. 10(b)(i, ii and v) are corresponding to contact NDE techniques whereas Fig. 10(b)(iii and iv) are corresponding to non-contact NDE techniques. Fig. 10(c) shows the ability of different NDE techniques to capture the damage mechanism at different scales in composite specimens. It is clear from the figure that the tomography technique has the good ability to capture the finest damage mechanisms in composite specimens compared to other NDE techniques while the finest damage mechanisms could not be identified using visual inspection techniques.

(a)

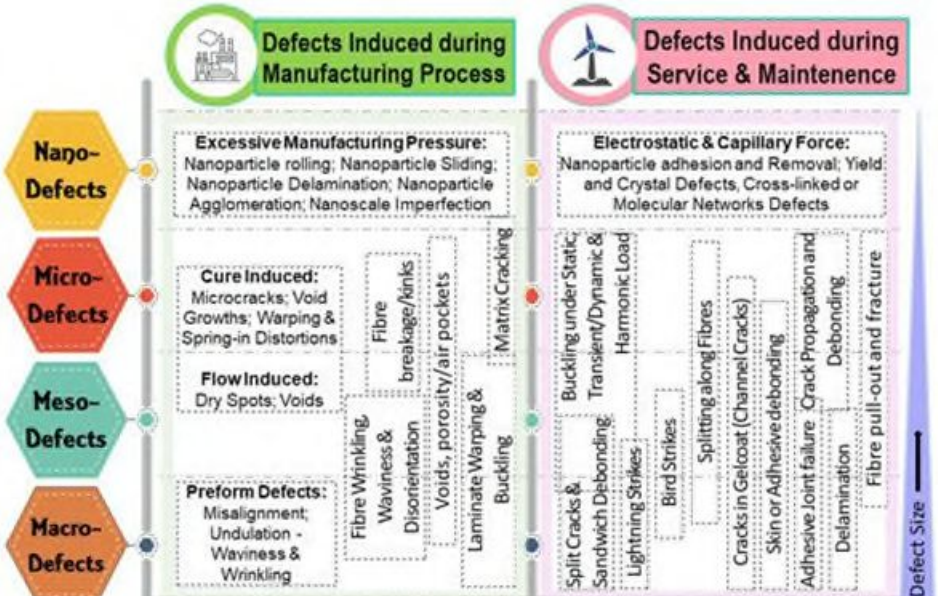

(b)

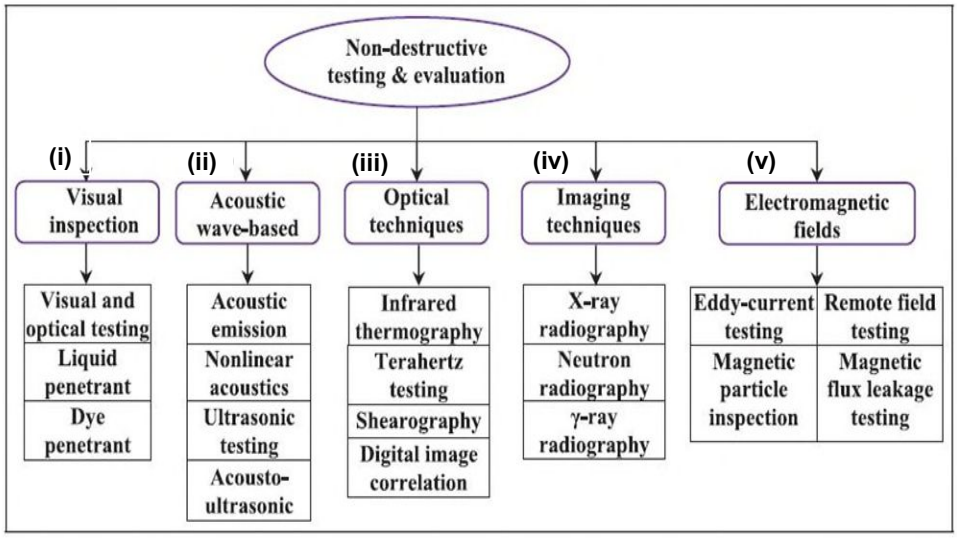

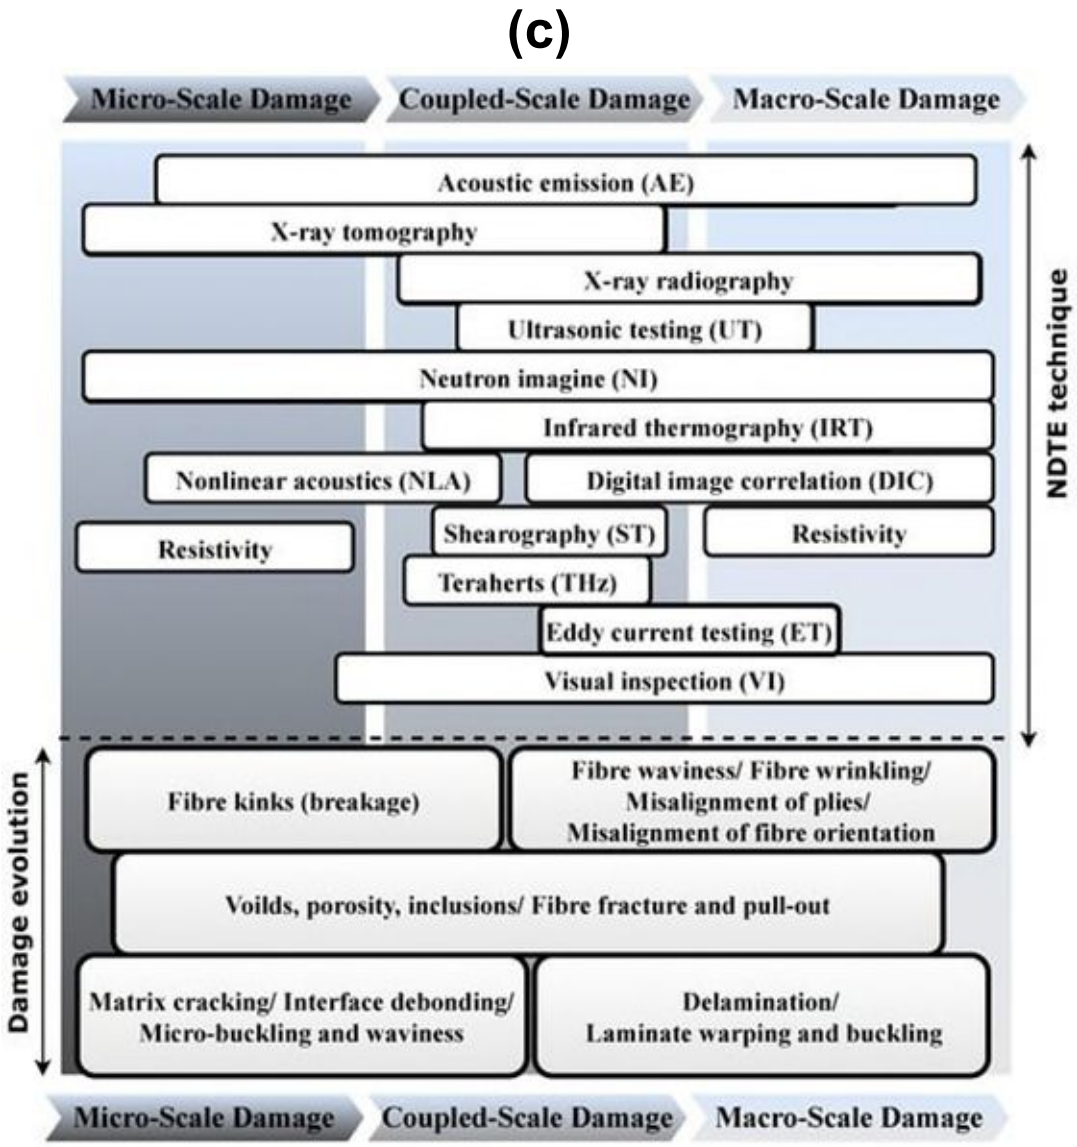


Fig. 10 Different scales of defects occurred during manufacturing and service and maintenance (a) Adopted from [225]; Schematic representation of different types of NDE techniques (b) Adopted from [226]; Identifying the different damage mechanisms in composite specimens using different NDE techniques (c) Adopted from [227].

(i) Visual inspection:

The failure mechanisms can be identified using the human eye. This is the cheapest noncontact technique compared to other NDE techniques. It can be classified as visual and optical testing, liquid penetrant and dye penetrant [228].

(ii) Acoustic wave-based techniques:

Acoustic Emission (AE):

AE is a contact NDE technique and is being widely used technique in detecting commonly occurred failure mechanisms such as fiber breakage, fiber pull out, delamination, etc., in FRPCs [229]. The defect information through this technique can be captured using an AE sensor that is attached to the specimen. AE technique is different compared to other NDE techniques. This technique receives AE energy in the form of a waveform from the failure mechanisms of the specimen, instead of sending energy to the specimen. The failure mechanisms of long-term loading (fatigue) and dynamic loading (impact) events can be captured using this technique [230]. Therefore, this technique is increasingly used in aircraft structural components. Moreover, the AE technique is the most widely used in studying the machining of NFRPCs, owing to its ability to capture various process conditions which include a change in cutting speed and fiber orientation, etc., [132, 231]. Wang et al. [232] have employed the AE technique for monitoring machining characteristics of flax/PP composites to understand process conditions during orthogonal cutting using a random forecast machine learning model. Applications of the AE technique in various fields of NFRPCs are reported by Sarasini and Santulli [233].

Ultrasonic Testing (UT):

UT is a contact NDE technique that consists of transmitter, receiver and, computer for storing and pre-and post-processing the data. In this technique, the signals can be propagated into the specimen from the transmitter and the defect information will be captured by the receiver [234]. It is one of the most commonly used NDE techniques in NFRPCs [235]. The defect of failure mechanisms such as porosity, fiber misalignment, crack size and orientation can be detected using this technique [229]. This technique is best suitable for investigating small size flat specimens

while using this instrument it is difficult to investigate curved or cylindrical specimens. The ultrasonic 'C' scan technique is being widely used in understanding the impact failure mechanisms of both thermoset and thermoplastic polymer composites [236, 237]. Different types of ultrasonic techniques (immersion, air-coupled, contact guided wave and air-coupled excitation and contact reception guided wave) and their advantages and limitations are discussed by Yilmaz et al. [238].

Acousto-ultrasonic (AU):

AU is a contact NDE technique that is based on a combination of acoustic and ultrasonic testing technology. This technique can detect internal imperfections and inhomogeneity in composites, these characteristics are especially higher in plant fibers [239]. This technique has proven to be an accurate one based on optimal economy, and sensitivity [240]. It detects the accumulated damage present in the specimen subjected to impact and fatigue loading.

(iii) Optical techniques:

Optical techniques are camera based non-contact NDE techniques. Several researchers are being used optical techniques in investigating NFRPCs [241]. Lopato et al. [242] investigated the different stages of failure mechanisms in thin basalt fiber reinforced composites by using two different NDE techniques combined terahertz and infrared thermography techniques. Sfarra et al. [239] reported that investigation of the plant fiber composites using different NDE techniques is required owing to inherent irregularities present in the fibers. The presence of damage, resin-rich regions and defects in the jute/hemp/epoxy hybrid composites were investigated and reported in detail. In another study, the indentation damage mechanisms of jute/hemp/epoxy hybrid composites were studied using optical and infrared NDE techniques [243].

Infrared thermography (IRT):

In this technique, the thermal radiation emitted by the surface of the specimen can be recorded using the infrared camera [234]. It is an accurate technique to determine the crack size and shape of the specimen. It measures the damages in a shorter time. Boccardi et al. [244] studied the microstructure of thermoplastic resin reinforced basalt fiber composites using UT and IRT techniques. It was reported that UT and IRT techniques are in good agreement in capturing failure mechanisms of basalt/polyamide composites. However, the IRT technique is found to be a better one to detect the failure mechanisms in basalt/polypropylene composites. However, gel-based UT could not capture the failure mechanisms in basalt/polyester composites owing to hydrophilic characteristics of composites, these would be soaked with the coupling agent. In another study, Zhang et al. [245] investigated the impact damage mechanisms of basalt/vinyl ester composites using UT and IRT techniques. From Fig. 11(a), it is clear that using the UT technique both delamination and resin-rich regions (shown in Red color) can be detected while IRT provides only delamination (Fig. 11(b)) in basalt/vinyl ester composites. Therefore, further studies are required related to NFRPCs to identify the best technique out of these two techniques. Brasington et al. [144] compared different NDE techniques (profilometry, thermography and eddy current) in inspecting the defects (gap, overlap, wrinkle, twist, etc.) in the AFP manufactured component and reported that the thermography technique is the best to capture all defects compared to other NDE techniques. IRT technique is also useful in studying the machining of NFRPCs. Wang et al. [246] have investigated the drilling performance of hemp/vinyl ester composites using conventional drilling (CD) and ultrasonically-assisted drilling (UAD) approaches through the infra red camera. It was reported that higher magnitude of cutting forces and energy are required and drilling induced damage was higher with CD approach compared to those with of UAD approach. Moreover, UAD approach exhibited better surface finish and quality of holes compared with those of UD approach.

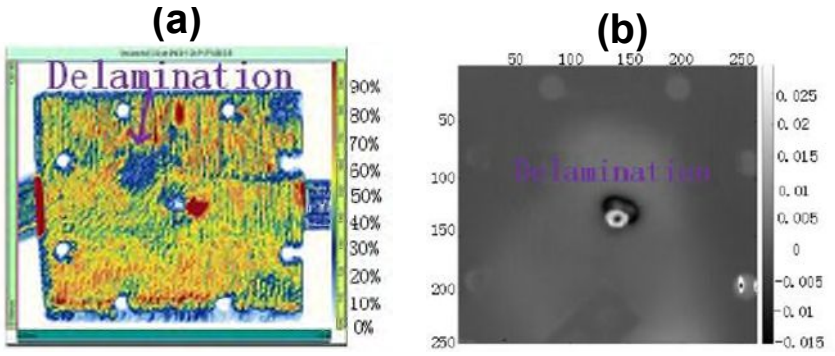


Fig. 11 Comparison of impact damage mechanisms in basalt/vinyl ester composites subjected to 15 J, using UT (a) and IRT (b) Adapted from MDPI [245].+

Shearography:


Shearography is a non-contact optical NDE technique. It consists of a laser light source, optical shearing device, charge-coupled camera (CCD), etc. The main advantage of this technique is that it is less susceptible to noise compared to many other techniques. It is mainly useful to detect delamination in composites. Further details about this technique are given in literature [229, 234].

Digital Image Correlation (DIC):

DIC is a widely used NDE technique to measure the in-situ strain and capture the failure mechanisms at different fiber orientations [117, 247]. It is a non-interferometric technique. The deformation of the specimen can be detected by comparing gray intensity variations of the reference and deformed images. DIC technique is useful to capture the deformation history in both quasi-static and high strain rate loadings [212]. Further details about this technique and working principle are given in our recent articles [213, 248]. Begum et al. [98] employed the DIC technique to measure the in-plane strain in-situ in flax/glass/epoxy and jute/glass/epoxy hybrid composites. Habibi and Laperriere [249] investigated the tensile properties of flax/epoxy composites using DIC and acoustic emission techniques. It was reported that the number of acoustic events noted was lower in open hole tensile experiments owing to formations of stress concentrations and crack

initiation near to open hole, which lead to premature failure in composites. The major drawback of DIC is that it suits to capture the displacement fields before the failure of the sample and it fails to identify the displacement fields when there are discontinuities that occur after the initiation of the failure. The discontinuities occur in the sample due to the cracks and fiber failures. For example, in Fig. 12(a), the DIC approach can be used when time (t) = 0.51 ms. The DIC approach cannot be used from time (t) = 0.77 ms. Moreover, the DIC approach may not be accurate for very high impact energy experiments. To overcome these drawbacks, Ramakrishnan et al. [250] proposed the crack-tracking approach to identify the crack length using Image J software, at any stage above or below t = 0.77 ms, by developing an algorithm. Through this algorithm, initially, a combination of median and Gaussian blur filters can be applied to the reference (undamaged) image, and then each image can be treated with the same filters, as shown in Fig. 12(b). Further, the deformed image can be subtracted with the reference image, such that the cracks can be isolated from the deformed image. However, at this stage, the cracks may not be visible clearly. Therefore, the subtracted image can be converted to mask and binarized to clearly measure the crack length. This crack-tracking approach can be used to any impact tests, irrespective of any impact energy for measuring the crack size.

(a)

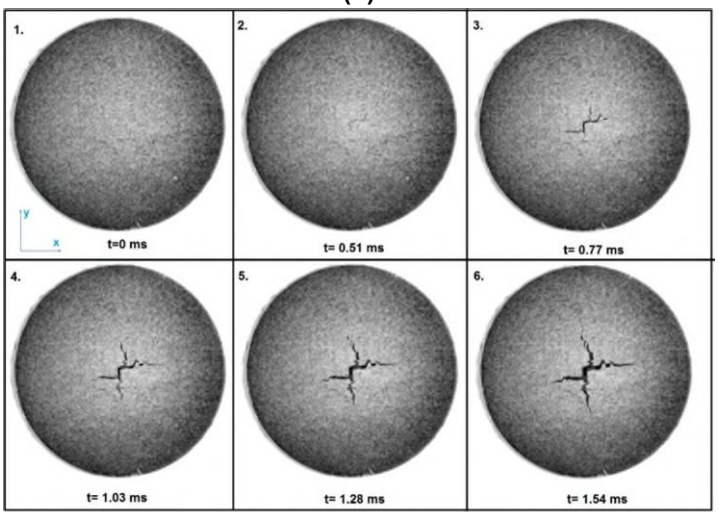

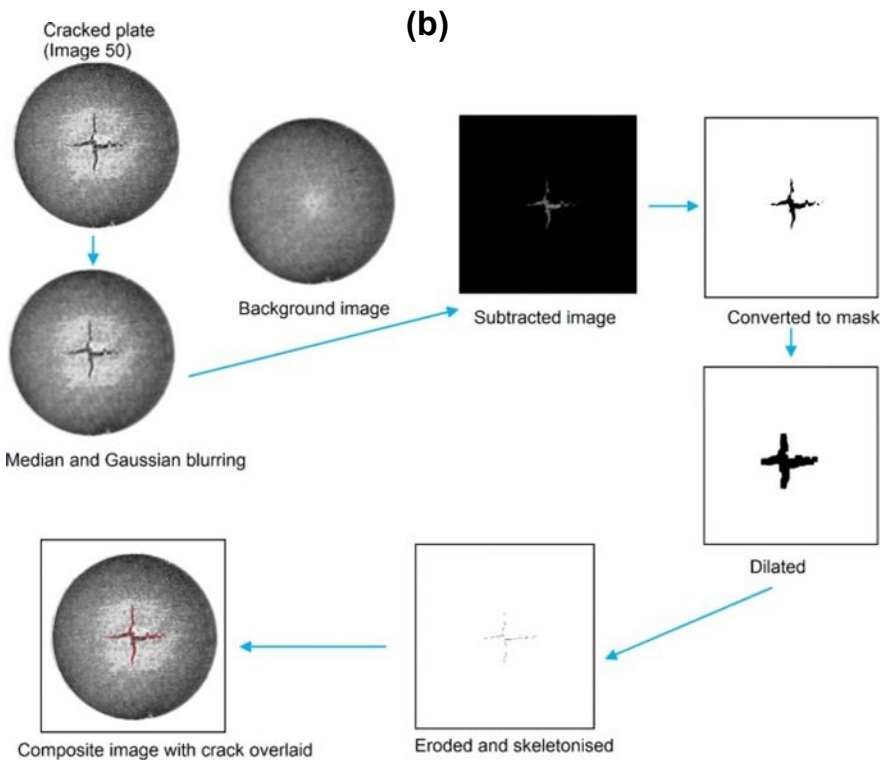


Fig. 12 In-situ observation of initiation and propagation of macro-cracks in flax/PP composites subjected to LVI at 6J using high speed camera (a) and procedure to measure the crack length in high speed camera images Adapted with permission from Elsevier [250], Copyright Elsevier 2021.

(iv) Electromagnetic fields

Electromagnetic techniques induce electric currents, magnetic fields, or a combination of both into a sample, in order to detect fractures, defects, etc., in composites and observe the electromagnetic response. Electromagnetic techniques are classified as eddy current testing, magnetic particle inspection, remote field testing, magnetic flux leakage testing. Further details about these techniques are elaborated in detail in literature [229, 234].


(v) Imaging techniques:

In recent times, X-ray computed tomography (XCT) is being widely used in medical, engineering and defence fields compared to other imaging techniques [24, 35]. This is owing to its high accuracy and it can provide information in both 2D and 3D [251]. However, the cost of XCT

is very high compared to other imaging techniques. Recently, the use of XCT is gaining more interest in studying natural fiber based wood [252, 253, 254] and non-wood [28, 255, 256] composites. Three dimensional voxel models can be created after reconstruction, using different software packages (Volume graphics (VG) Studio max, Fiji, Geodict, Avizo, etc.,) [35, 257, 258]. Mutiargo et al. [259] have reported that capturing microstructural information in complex geometrical components fabricated by AM is difficult with ultrasonic testing and eddy current, owing to presence of insurmountable difficulties. These challenges can be overcome by using XCT owing to its ability to capture the data during a 360º rotation of a sample [35, 121]. Also, the spatial resolution of XCT is higher than the ultrasonic testing and eddy current, as shown in Fig. 2. Typical spatial resolutions could be achieved with different XCT instruments based on the size of the sample size [260]. It is clear from Fig. 3(b) that spatial resolution could be achieved with conventional or macro XCT is low (>10 μm) and it increases gradually with micro XCT (>3 μm), nano XCT (>0.4 μm), synchrotron XCT (>0.2 μm), synchrotron XCT with Kirkpatrick–Baez mirrors (>0.04 μm), and focused ion beam tomography (FIBT) >0.01 μm.

Bensadoun et al. [261] reported that the use of XCT has several advantages in inspecting the fiber orientation, void content, delamination, etc. However, this can be possible only if the X-ray absorption coefficient of natural fiber and matrix are different, otherwise, difficult to identify the internal structure. Giuseppe et al. [262] measured the fiber length and diameter in NFRPCs using different approaches, namely 2D scanner, MorFi Compact® fiber analyzer (automated analyzer) and XCT, as shown in Fig. 13(c). It was reported that the techniques of 2D scanner and automated analyzer need specific treatments to separate the fiber from the polymer, while the separation of fiber from the polymer is not required in XCT. Moreover, XCT has several advantages and it can capture images with good resolution and measure the fiber length and

diameter precisely, over other two techniques. Bossio et al. [263] investigated the void volume fraction in hemp fiber reinforced with two different bio-resins (the first one is epoxy, which is derived from 25% of eggshells and the other one is Ecopoxy, which is derived from soybeans) braided composites using XCT, and reported that XCT is useful in optimizing the interaction between the cellulose yarns and bio-resins. Rask et al. [264] have performed in-situ tensile experiments on unidirectional flax/pp composites and monitored the microstructural changes during testing. Therefore, it is clear that XCT can be used effectively in observing microstructural changes in NFRPCs in-situ. These in-situ studies are limited related to NFRPCs, even though several studies are available with SFRPCs. The reason for limited studies available on NFRPCs is due to the lower density of natural fibers, which are closer to the density of polymers, therefore, performing XCT tests are difficult to achieve good resolution, compared to synthetic fibers [28]. The resolution of the NFRPCs can be enhanced by placing the sample closer to the X-ray tube during scanning. Further details to enhance the resolution of the sample are discussed in literature [35, 251]. Moreover, there are several other challenges are associated while inspecting NFRPCs, in that, particularly important to know the scanning parameters (voltage, current, intensity, etc.) [261, 265], which can be withstood by natural fibers without affecting the properties.

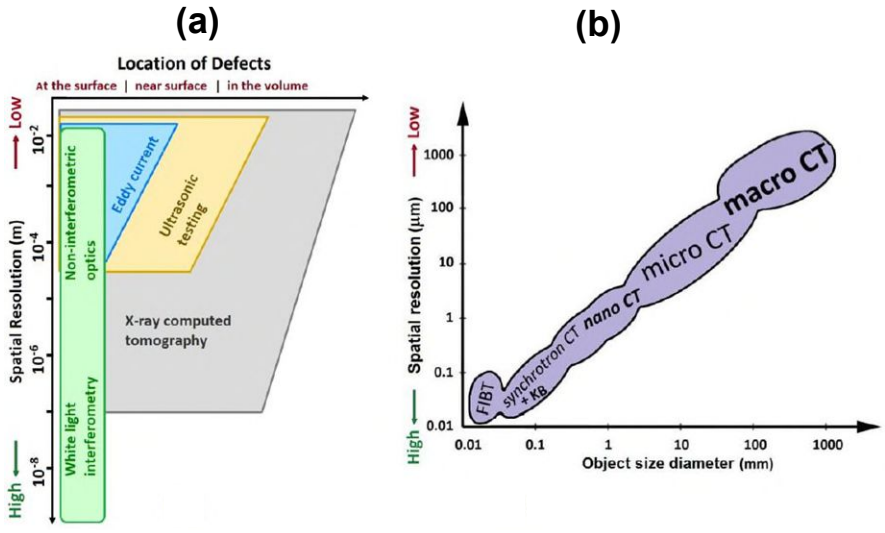

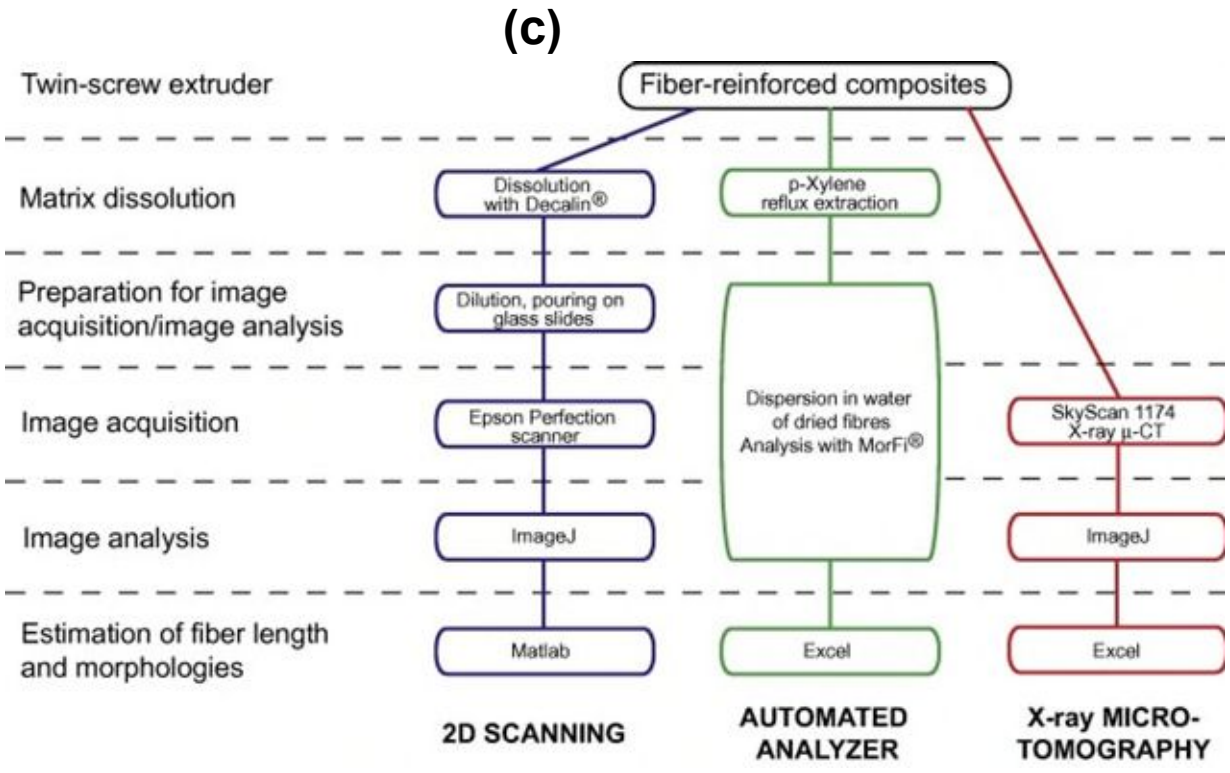


Fig. 13 Comparison of spatial resolution with XCT and other NDE techniques (a, b) Adapted with permission from Elsevier [266], Copyright Elsevier 2019; Comparison of different techniques for measuring fiber dimensions in polymer-lignocellulose fiber composites (c) Adapted with permission from Elsevier [262], Copyright Elsevier 2016.

4.2. XCT aided models in NFRPCs

(a) Void based models:

XCT based void models are useful to estimate the void volume fraction in NFRPCs. Yu et al. [267] investigated the void volume fraction in different fiber orientations of FDM printed basalt/polylactic acid (PLA) composites using XCT and found a lower void volume fraction of 7.92% in $[0/90]_6$ laminates and a higher void volume fraction of 8.23% in $[45/135]_3$ laminates, as shown in Fig. 14. Fig. 15 shows the XCT aided void analysis maps of injection molded basalt/polyamide composites. The void volume fraction of 1.2% is observed from the void analysis maps.

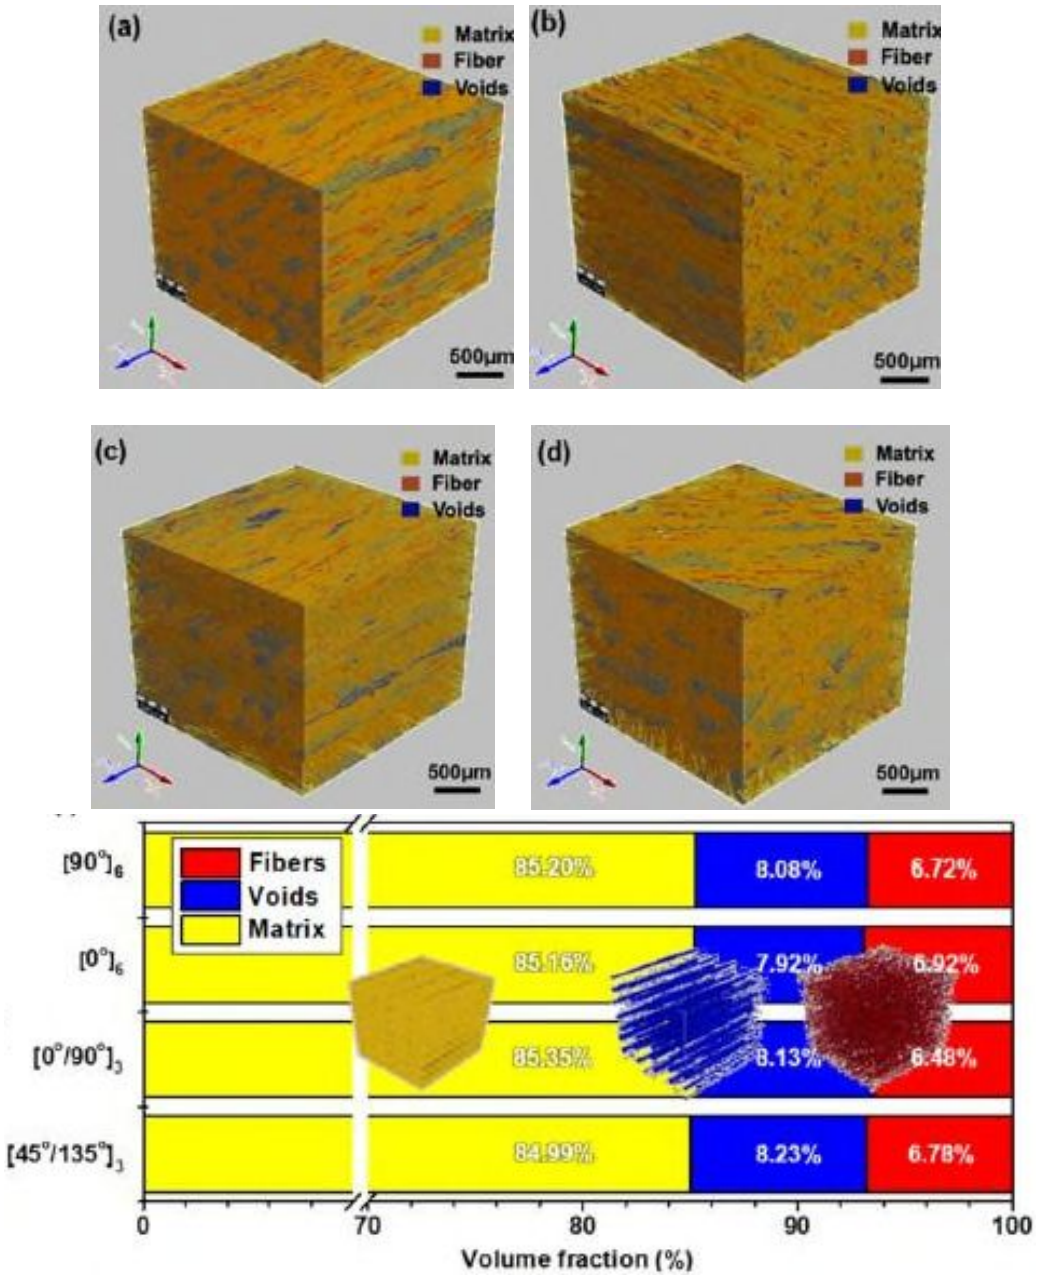


Fig. 14 XCT images of FDM printed basalt/PLA composites: (a) $[0/90]_6$; (b) $[0]_6$; (c) $[0/90]_3$; (d) $[45/135]_3$ Adapted with permission from Elsevier [267], Copyright Elsevier 2021.

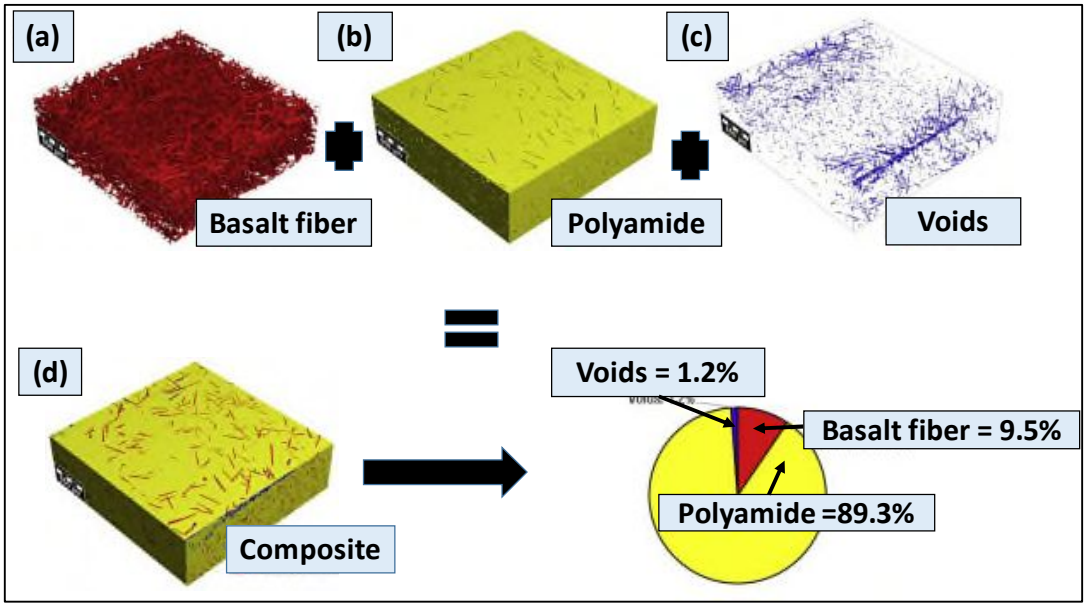


Fig. 15 Void analysis in injection molded short basalt fiber/Polyamide 6,6 using XCT. Adapted with permission from Elsevier [268], Copyright Elsevier 2020.

(b) XCT aided statistical models:

The statistical analytical models can be used to study the morphological characteristics of different constituents (size, shape and distribution of fibers and voids) in NFRPCs based on data provided through the XCT aided models [257]. XCT data can be presented statistically using VG Studio Max software [121], Avizo [269], Geodict [270], etc. Fracz et al. [28] investigated the distribution of hemp fibers in hemp biocomposites statistically, which are manufactured at different injection molding rates, 10, 35 and 75 cm^3/s, as shown in Fig. 16(a-c), respectively. It was reported that the clustering of fibers is lower at the highest injection molding rate. Normal distribution and two-parameter Weibull distribution models are the most widely used statistical models to study these morphological characteristics [121]. Giuseppe et al. [271] reported that the Log-normal distribution model fits well with the data compared to two parameter Weibull distribution.

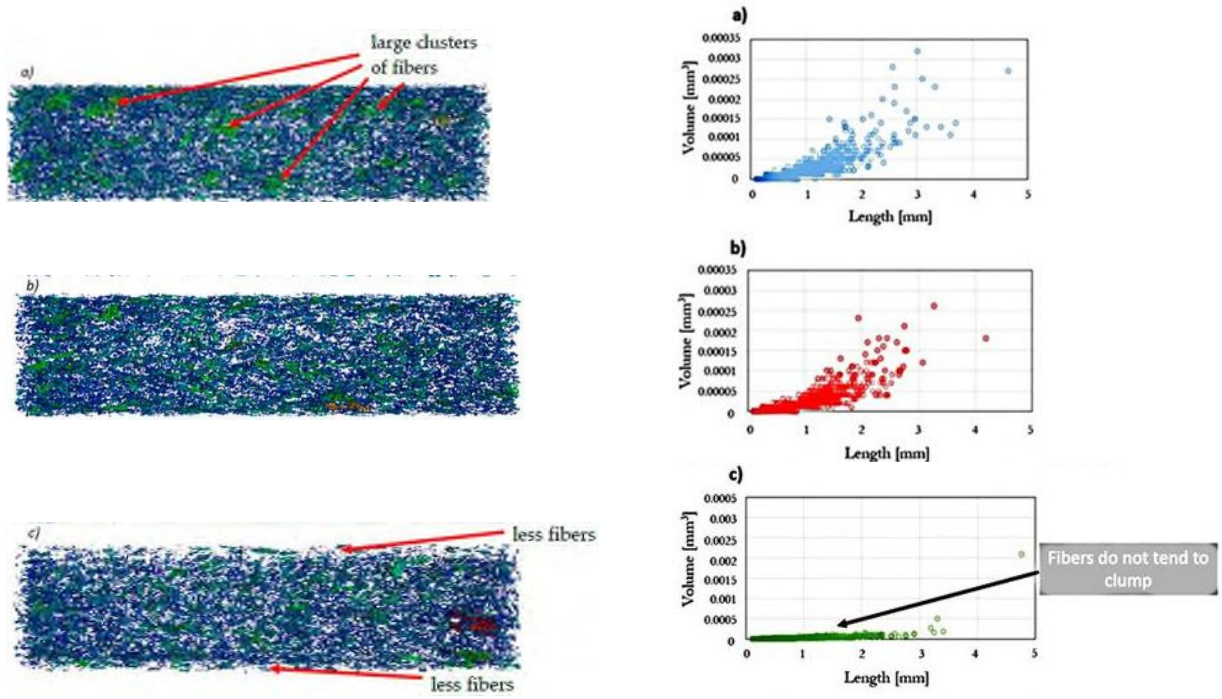


Fig. 16 Fiber distributions in 3D at different injection molding rates, 10, 35 and 75 cm^3/s (a-c) and corresponding statistical analysis of hemp fiber clusters as a function of length. Adapted from MDPI [28].

4.3 XCT aided real and virtual geometry-based simulations in generating digital twins

Generating XCT aided real geometry is straightforward from 2D XCT scanned images after reconstruction, using software packages, such as WiseTex, Avizo, VG Studio Max, Geodict, etc., [269, 271]. However, XCT scanned data can be used to create the virtual geometry, as shown in Fig. 17(a), using software packages, such as TexGen, WiseTex, etc., to predict mechanical properties [272]. Compaction based simulations can be performed using FEA software packages, such as Ansys, Abaqus, Voxtex, etc., while permeability based simulations can be performed using computational fluid dynamics (CFD) software packages, such as Geodict, Ansys, Paraview, Flowsquare, etc., [35, 269]. Fig. 17(b)-(c) show the comparison of compaction simulation results of real and virtual geometry modeling while Fig. 17(d) shows the comparison of permeability simulation results of real and virtual geometry modeling. From these figures, it can be observed

that both results are correlating well. Therefore, it is clear that XCT can be used effectively for generating geometrical models of NFRPCs for various digital twin applications.

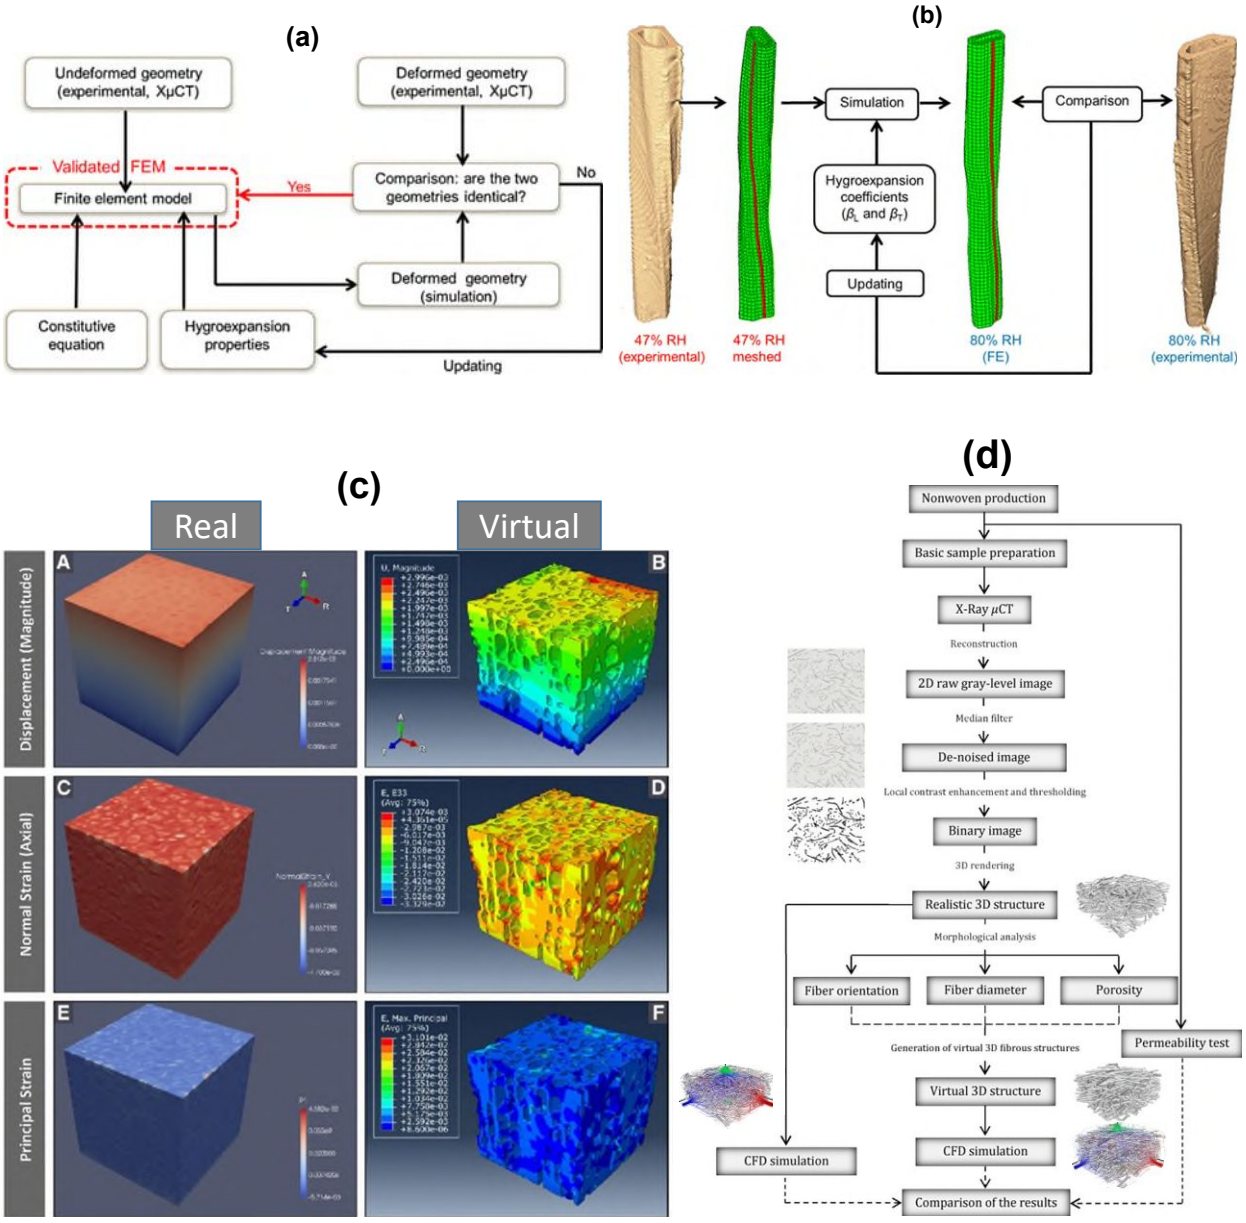


Fig. 17 Procedure for validating XCT aided virtual geometry modeling results with XCT aided real geometry modeling results (a) Adapted from Springer [45]; Comparison of XCT aided real and virtual geometry FEA simulations of wood composites (b) Adapted from Springer [45] and (c) Adapted from Springer [36]; Prediction of permeability in nonwoven fabrics using different approaches: experimental and XCT aided real and virtual geometry CFD simulations. Adapted with permission from Elsevier [273], Copyright Elsevier 2017.

The advantages, limitations and potential applications of each non-contact and contact NDE techniques are discussed in a recent article [224]. Table 2 shows the microstructure investigation details in NFRPCs subjected to different loading, which are measured using different NDE Techniques. Most of the studies presented in Table 2 were carried out recently.

Table 2 Microstructure investigation in NFRPCs using different NDE Techniques

NFRPCs	Manufacturing technique	Characterization	NDE Technique	Year	Reference
Basalt/polypropylene (PP) Hemp/ PP	CM	Tensile, flexural and fracture toughness	AE	2006	[274]
Flax/epoxy	CM	Tensile, bending and fatigue	AE, IRT, DIC, XCT	2022	[275]
Luffa/epoxy	RTM	LVI	AE, DIC	2022	[276]
Flax/epoxy	Autoclave	LVI	XCT	2021	[277]
Bamboo/ poly-benzoxazine	CM	High strain rate	High speed camera and DIC	2022	[212]
Hemp/PP Wood/PP	IM	Microstructure	XCT	2008	[278]
Palm/Phenolic	CM	Tensile and impact	IRT, UT	2021	[27]
Basalt/vinylester Jute/hemp/vinylester	RTM	LVI, quasi-static indentation	IRT, UT	2018	[245]
basalt/polyamide basalt/PP	CM	LVI	IRT, UT	2019	[244]
Flax/CORAL (bio-epoxy)	CM	Tensile	DIC, AE	2020	[249]
Basalt/PLA	FDM	Tensile and Void analysis	XCT	2019, 2021	[255, 267]
All-cellulose	CM	Tensile	DIC	2021	[241]
Jute/epoxy, Jute/glass/epoxy Flax/epoxy Flax/glass/epoxy	Manual molding	Tensile	DIC	2019	[279]
Jute/hemp/epoxy	CM	Static indentation	All optical techniques	2016	[239, 243]
Hemp/bio-resin	RI	Void analysis	XCT	2019	[263]
Hemp/PLA	FDM	Tensile	XCT	2019	[280]
Hemp bast fibers	-	Microstructure	XCT	2019	[47]
Kenaf/Jute		LVI and CAI	C-scan	2021	[281]
Basalt/epoxy	RI	LVI	C-scan	2021	[237]
Flax/PLA-PP	CM	Tensile, flexural and LVI	Laser UR, Profilometry, XCT	2019	[282]
Flax/carbon/epoxy	Autoclave	LVI	Laser vibrometry	2019	[283]
Basalt/epoxy	RTM	LVI	IRT, C-scan and terahertz imaging	2017	[284]
Basalt/Polyamide 6,6	IM	Void analysis	XCT	2020	[268]
Flax/epoxy and Flax vinyl ester	RI	Mechanical properties	XCT	2018	[285]
Silkworm cocoons	-	Tensile and microstructure	XCT	2021	[286]

Kenaf/epoxy/X-ray film	Hand lay-up	Tensile, flexural and HVI	Die penetrant	2018	[208]
Kenaf/Aramid/Polyvinyl butyral	CM	HVI	Visual	2016	[206]
Non woven Kenaf/PLA/clay	Resin casting	HVI	High speed camera	2020	[205, 207]
Glass/jute/flax/epoxy	RI	LVI and CAI	Visaul inspection	2020	[287]
Basalt/Kevlar/epoxy	RTM	Flexural and LVI	AE	2013	[288]
Basalt/carbon/epoxy	Autoclave	Flexural and Laser shock wave	XCT and AE	2015	[289]
Basalt/hemp/polyester	CM	Flexural and LVI	AE	2015	[290]
Basalt/flax/epoxy	RI	Tensile and Fatigue	IRT	2020	[291]
Carbon/flax/epoxy	Autoclave	Tensile, Flexural and LVI	DIC and XCT	2016	[292]
Basalt/glass/epoxy based vinylester	RTM	LVI	IRT	2013	[293]
Basalt/vinylester	RTM	LVI	IRT	2016	[294]
Jute/glass/polyester	RTM	Impact and post impact	AE and IRT	2009	[295]
Flax/ epoxidized pine oil	Hand lay-up	Compression	DIC	2020	[296]
Abaca/glass/polyester	RI	Tensile and flexural	XCT	2021	[297]
Basalt/epoxy, basalt/vinylester	RI	LVI	C-scan	2021	[237]
Short Palm fiber/Phenolic	CM	Tensile and LVI	IRT and C- scan	2021	[27]
Jute/PLA	CM	LVI	C-scan	2017	[298]
Jute/vinylester	RI	LVI	C-scan	2006	[299]
Hemp/polyester	CM	LVI	C-scan	2012	[300]
Flax/epoxy	RTM	Four point bending and fatigue	Fibre Bragg Grating and DIC	2020	[301]
Flax/PP	FW	Tensile	XCT	2012	[264]
Hemp/ Poly(3-hydroxybutyric-co-3-hydroxyvaleric acid) (PHBV)	IM	Microstructure assessment	XCT	2021	[28]
Flax/PLA	CM	Microstructure assessment	XCT	2021	[256]
Bamboo scrimber	CM	Compression	DIC	2021	[302]
LINEO FlaxPreg T-UD 110	Autoclave	Tensile	DIC	2018	[48]
Flax/PP and Flax/epoxy	CM	LVI	High speed camera and DIC	2021	[250]
Hemp fiber	-	Microstructure assessment and tensile	XCT and DIC	2017	[265]
Bamboo node	-	Tensile	AE	2020	[303]
Flax/PP	CM	Machining	AE	2020	[232]
Hemp/vinyelster	CM	Machining	IRT	2019	[246]
Banana/epoxy	Hand lay-up	Machining	C-scan	2014	[194]

From Fig. 18 it is clear that the number of publications related to NDE techniques has been increased every year. The number of papers published in 1996 is approximately 100 and in 2019 is approximately above 700. Also, it is interesting to note that the number of papers published from 2015 to now, related to X-ray imaging is higher followed by digital image correlation compared to other NDE techniques, which can be seen in Table 1.

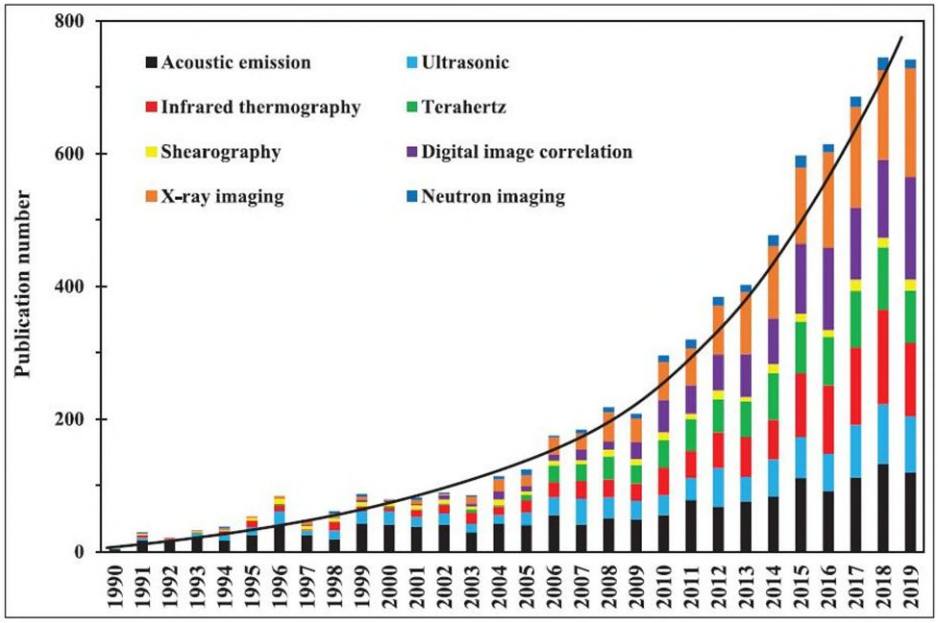


Fig. 18 Number of publications related to NDE techniques of composite materials or structures in the past 30 years. Adapted from Sage, open access [226].

5. Artificial Intelligence approach in polymer composites

Performing several experiments require many costly instruments and require more time and manpower. Therefore, it is necessary to minimize the number of experiments and obtain the data using advanced technology. Although several numerical software packages are commercially available in the market to predict the properties of composites, however, these require severe computational resources. In recent years, the use of AI approach is being increasingly used in designing, manufacturing and inspecting and post-processing data [304]. The idea of AI is inspired

by the biological nervous system and it is useful to solve complex mathematical problems based on the available data. The AI-aided approach requires limited experimental data, which minimizes the time and labor cost. AI is subdivided into Machine Learning (ML) and Deep Learning (DL), as shown in Fig. 19(a-b). AI technology is being widely used for smart manufacturing, as shown in Fig. 19(c). As compared to ML, the role of human participants is less in DL [305]. Moreover, ML is used in predicting the properties of composites [306] while DL architecture contains many hidden layers with non-linear combinations of multi-layers. In general, ML requires step-by-step training in each module, while many parameters can be trained combinedly in DL.

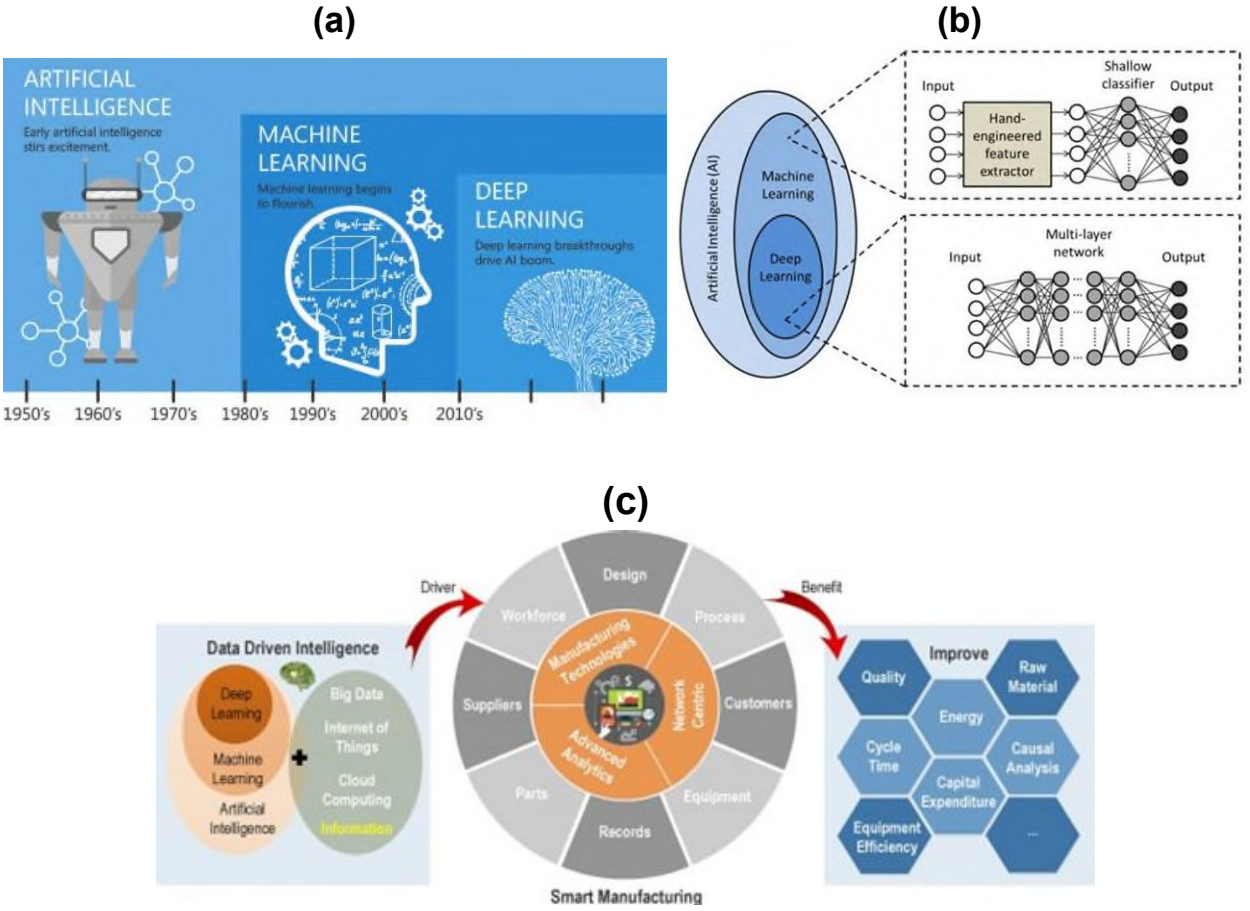


Fig. 19 Progression of AI, ML and deep learning (a) Adapted from thesis [307]; the relationship between AI, ML and deep learning (b) Adapted from MDPI [308] and data driven intelligence approach for smart manufacturing (c) Adapted with permission from Elsevier [309], Copyright Elsevier 2018.

5.1 Machine learning

The branches of ML are shown in Fig. 20(a). Further, ML algorithms can be divided into supervised, unsupervised and reinforcement learning, as shown in Fig. 20(b) [310]. In the training stage, the correct value has to be given for each input signal, this is called as supervised training, as shown in Fig. 21(a). The calculated output value is then compared with the correct value to check the error (%). In general, the output determined through the ML is the class of the sample presented in the input layer, as shown in Fig. 21(b). If the output value is not relying directly on the given input parameter, this kind of approach is called as unsupervised learning. The third one is reinforcement learning, it is useful to solve real-time problems based on iterations [311].

ML is useful in designing, manufacturing and predicting multifunctional properties of composites, as shown in Fig. 21(c-d). A faster convergence with better control could achieve by optimizing the process parameters through the ML approach, which replaces the traditional numeric optimization paradigm. Liu et al. reported that the ANN approach can be the best optimization technique for all stages of composites recycling [312]. Li [313] has outlined a fuzzy neural network approach in replacing conventional PID control in the filament winding technique and obtained better results in adjusting the parameters. Sacco et al. [167] reported that ML is useful in controlling and optimizing many process parameters in the AFP technique. Heider et al. [314] used five hidden layers neural network approach in optimizing process parameters in the automated thermoplastic tow-placement process and optimized better process parameters. The results obtained through this approach was matching with the numerical simulations.

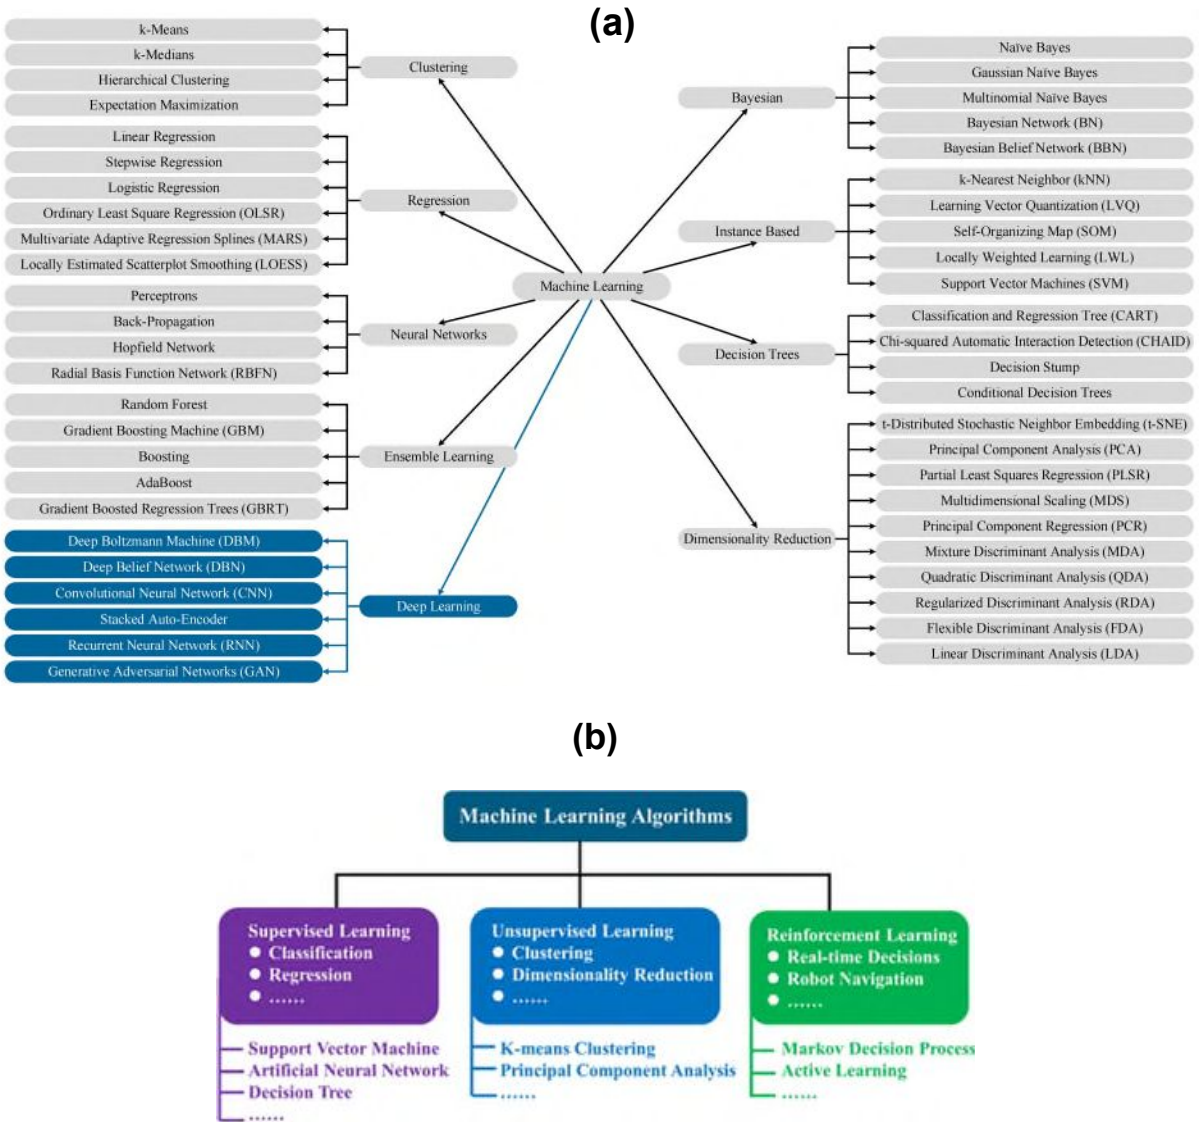
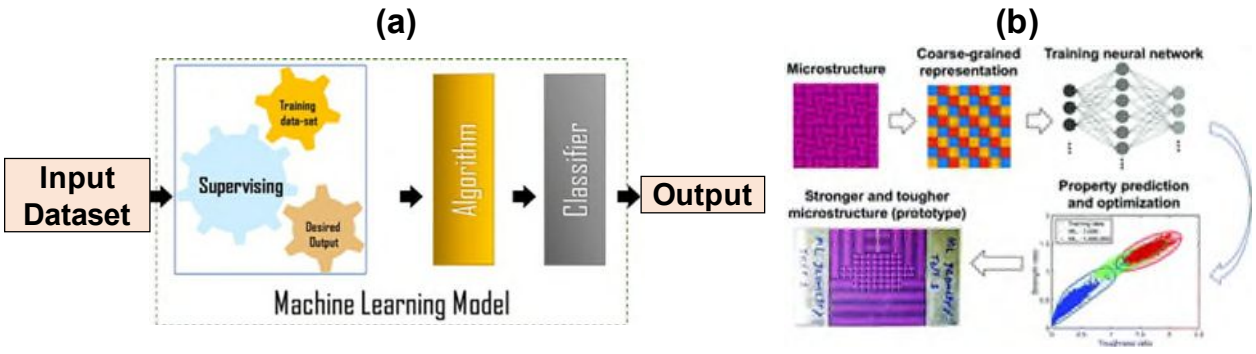


Fig. 20 Branches of Machine learning (a) Adapted from MDPI [315]; types of ML algorithms (b) Adapted from Wiley, open access [311].



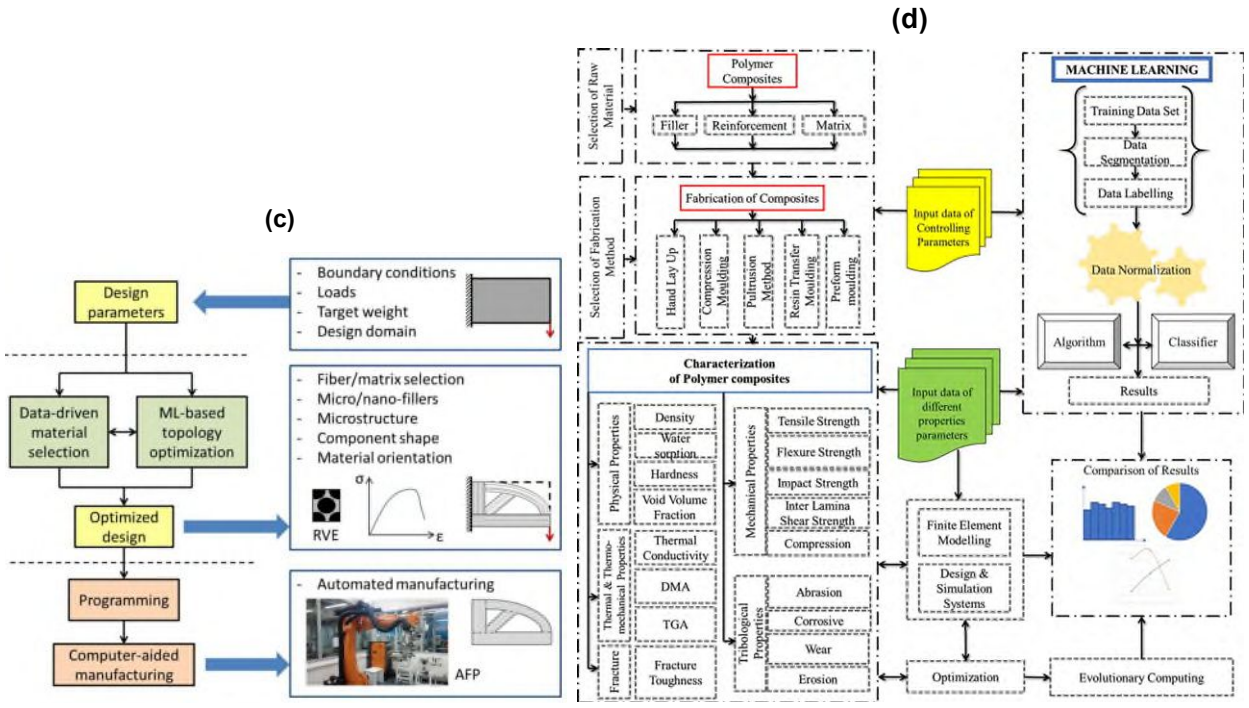


Fig. 21 Supervised training in ML (a, b) and application of ML in designing, manufacturing and predicting multi-functional properties of polymer composites (c, d). Adapted from MDPI, RSC and Elsevier with permission.[308, 316, 317].

Recently, Fernandes et al. [318] have employed the ML approach in processed Infrared Thermography images to identify the fiber orientation of randomly oriented strands. These kinds of ANN approaches can be used in determining the defects and damages in composites which are recorded using other NDE techniques. IRT NDE combined with a machine learning tool is useful to detect the defects automatically in NFRPCs [39].

5.2. Deep learning

Deep learning models can be divided into convolutional neural networks (CNN), deep belief networks (DBN), autoencoder (AE), recurrent neural networks (RNN), etc., [309, 319]. The application of these models for inspecting faults in machines, prediction of analytical problems in various domains, etc.

5.2.1 Convolutional Neural Networks

The working principle of CNN is based on a deep learning algorithm. Nowadays, CNN approaches have been widely used in processing images and videos [115]. CNN requires the input data in the form of the image, such that the set of variables based on pixel values can be reduced greatly for faster processing by adjustable weight. The various pieces of information in the image can be trained and enhanced with multiple filters, therefore, it can distinguish one from the other. CNN contains three types of layers, namely Convolution, Pooling and Fully connected layers. The key features in the input image are extracted through the convolution layer. The width and size of the output can be reduced using the Pooling layer and then the reduced data can be transferred into a column vector as an input to the fully connected layer. A fully connected layer works similarly to ANN, it consists of three layers, which are input, hidden and output layers (Fig. 22(a)). In that, each neuron in the layer can be connected to all neurons in the previous layer for predicting the output [307], as shown in Fig. 22(b). Fig. 22(c) shows the schematic representation of CNN employed by Ramkumar et al. [40] to predict the mechanical properties of NFRPCs. The total computational (CPU) time (including loading the network and the images, etc.) for predicting the permeability would be less than 10 seconds for 800 images, as shown in Fig, 22(d) [41]. The CPU time of CNN is very low compared to FEA or CFD flow simulation tools, which required several thousand seconds to predict the permeability. These findings confirm the advantages of employing CNN.

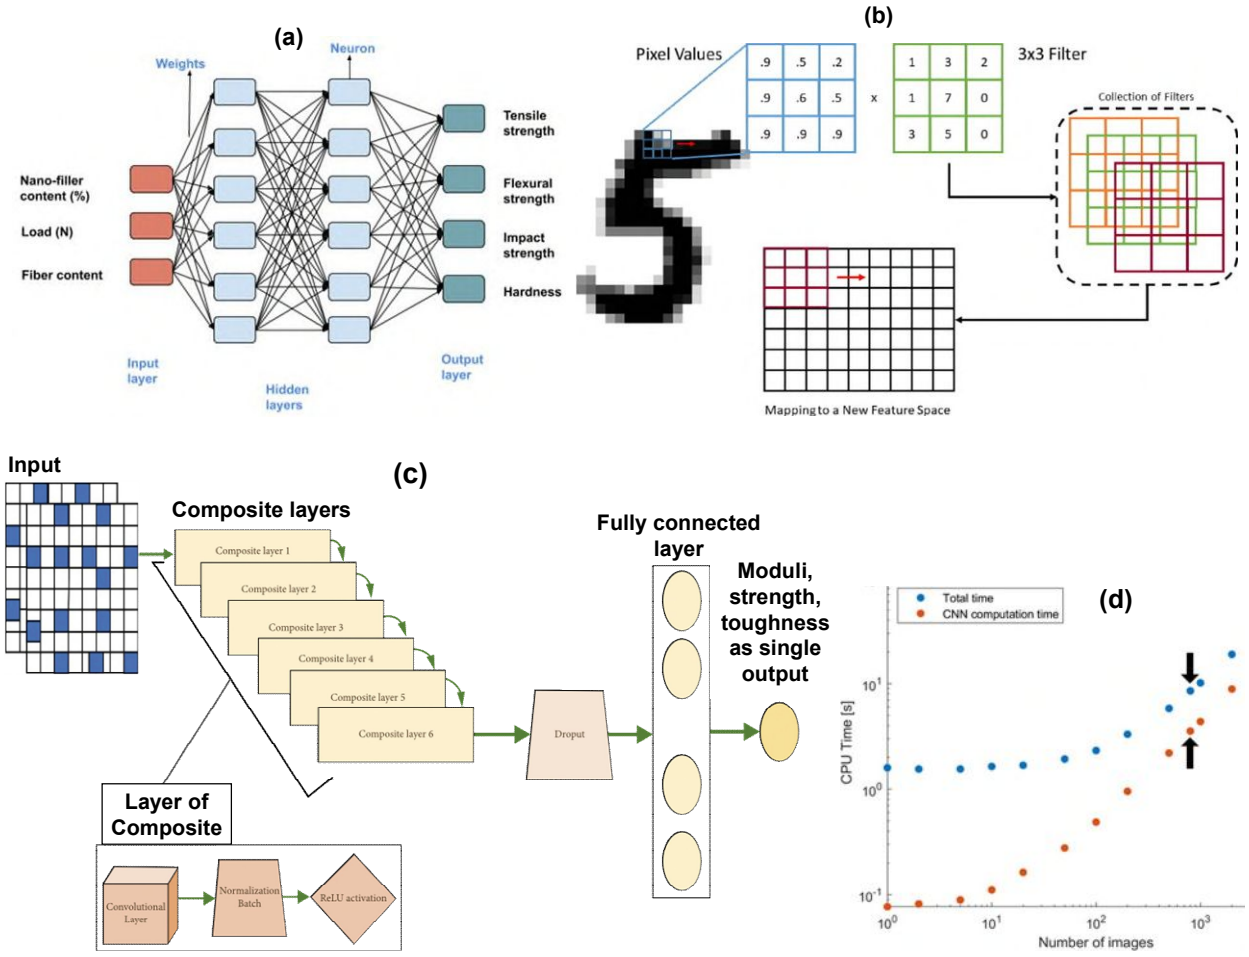


Fig. 22 ANN approach to predict mechanical properties of NFRPCs (a) Adapted from MDPI [320]; Procedure for mapping of CNN (b) Adapted with permission from Elsevier [167], Copyright Elsevier 2020; Schematic representation of CNN to predict mechanical properties of NFRPCs (c) Adapted from Hindawi [40] and its computational (CPU) time to predict permeability of fibrous structures. Adapted from Else5vier, open access [41].

In general, the microstructural information of most of the NDE recorded or scanned images are not clearly visible in the preprocessing stage. Therefore, it is essential to use reconstruction software packages to identify the information in recorded images before post-processing the data [35]. In recent times, trained deep learning tools are used for segmenting the NDE images to create digital material twins of fibers and composites [321, 322]. Also, it is useful in enhancing the image quality of NDE techniques by reducing the noise in the images, for clearly identifying the defects and damages in composites [38, 319, 323], as shown in Fig. 23. Mutiargo et al. [259] have used

U-Net, it is a deep learning architecture, to enhance the image quality of XCT scanned images and accurately detect the porosity in AM built samples. Jiang et al. [319] have predicted compression after impact properties of composites using CNN.

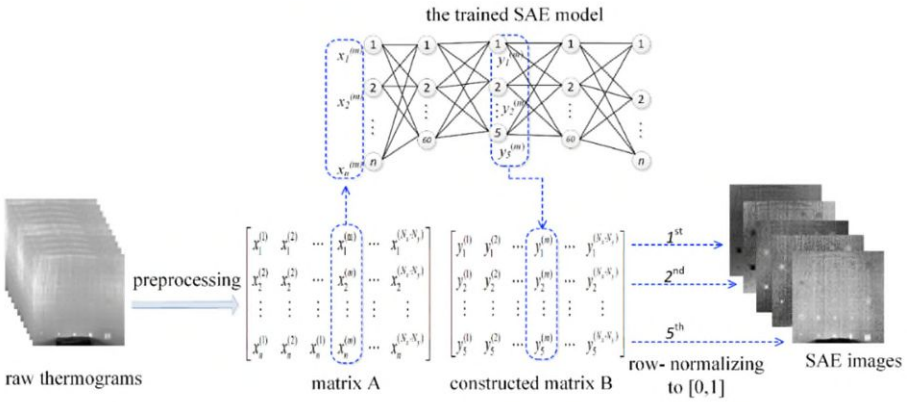


Fig. 23 Enhancement of image quality using stacked autoencoder (SAE) deep learning approach. Adapted from MDPI [324].

6. Future perspectives

- Limited studies have been found in manufacturing NFRPCs using AFP, ATL and TFP techniques. Further studies are required with these advanced fiber placement techniques, as the shape and dimensions of many natural fibers are not uniform, which lead to many defects.
- The studies related to 4D printing of NFRPCs are limited, except very few papers [129, 130, 153, 325]. However, these studies are important to understand the shape memory effect with respect to time.
- Modeling of NFRPCs using in-situ NDE techniques are limited compared to SFRPCs [270, 275]. In particular, these studies are very limited on plant FRPCs compared to wood composites [53], as shown in Fig. 24. These studies are important to conduct, which minimize the number of experiments and reduce the cost and process time, and

enhance the product quality by minimizing the defects [337]. Future demand for NDE techniques in different countries is shown in Fig. 25.

- Recently, researchers are being increasingly performing mechanical tests on SFRPCs by combining XCT and the digital volume correlation technique [326, 327]. These combined advanced techniques are useful to measure the deformations in 3D and minimize the defects in composites. However, these studies are very limited on NFRPCs [252], which will be useful to compare the microstructure in 3D and develop numerical models.
- The expensive XCT technique can be replaced with a hybrid approach (combining two NDE techniques (E.g. IRT and UT)), to obtain the same qualitative results for a very cheaper price [222].
- In recent times, European Union focus on Industry 4.0 which includes artificial intelligence, additive manufacturing, robotics, big data, etc., [46, 109, 328]. However, it is essential to apply the Industry 4.0 concept in adopting new technologies in designing, manufacturing and analyzing NFRPCS to develop high-quality environmentally friendly components in a shorter time. In particular, the adoption of digital twins with the help of NDE techniques in NFRPCS manufactured using modern techniques (AFP, ATL, TFP, AM, etc.,) adds extra benefit in maintaining residual properties of components. The service life of the component depends on residual properties of the component [276].
- In the past, the AI approach was used by several authors to predict the mechanical properties of NFRPCs [329]. However, to the best knowledge of the authors, there are no studies available to explore the best use of NDE combined with the artificial

intelligence approach (ML and DL). This combined approach will be useful in designing and manufacturing high-quality and environmentally friendly NFRPCs.

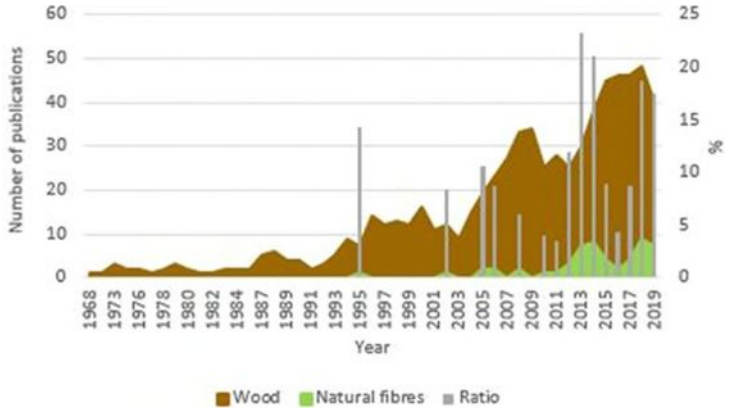


Fig. 24 Modeling of wood and plant fibers. Adapted with permission from Elsevier [43]. Copyright Elsevier 2022.

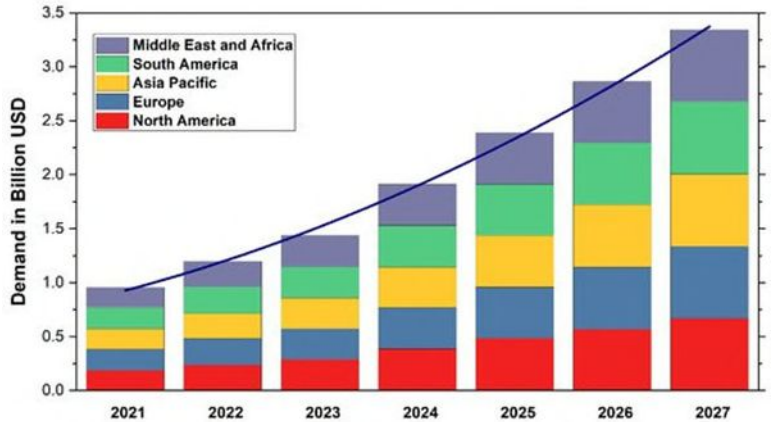


Fig. 25 Future demand for the use of NDE techniques in different countries. Adapted from MDPI [225].

7. Conclusions

In this review article, the important steps in the processing of NFRPCs using conventional and automated manufacturing techniques (ATL, AFP, TFP and AM) were presented. The advantages of automated manufacturing techniques over conventional manufacturing techniques

were highlighted. Moreover, the challenges associated with the automated manufacturing techniques and the remedies to overcome those challenges were identified that could enhance the mechanical performance of NFRPCs. Further, we discussed the use of NDE techniques in understanding the evolution of defects generation at different stages of manufacturing, inspecting the defects and determining the cause of multi-scale damage and failure in manufactured NFRPCs. The applications and limitations of both contact and non-contact NDE techniques in obtaining the microstructural information were presented. It was shown that in the last 5 recent years, the higher number of published articles were related to XCT followed by digital image correlation.

The application of AI technology for designing, smart manufacturing, inspecting and post-processing the data was presented. We discussed the importance of artificial intelligence (AI) technology and different methods of ML and DL in enhancing the quality of NDE images before post-processing the data, and minimizing the analysis time through automatic defect detection techniques. Moreover, different ML techniques were discussed to reduce the size of the NDE data, which would be several gigabytes. The application of NDE techniques and Artificial intelligence technology for segmenting the NDE images to create digital material twins of NFRPCs were also highlighted.

It was concluded that the 4D printing of NFPRCs has not been thoroughly investigated, therefore, it is essential to conduct research in this area and utilized the full potential of NFPRCs in biomedical and robotic applications. The studies related to the comparison of XCT results of NFRPCs with the digital volume correlation technique are also limited, these studies provide the validation of XCT results and detailed deformation information of specimens in 3D, even though these studies are available for SFRPCs. Therefore, further studies are essential to potentially utilize

the NFRPCs in manufacturing several eco-friendly components for various engineering applications.

Acknowledgements

This publication is based on work supported by the Abu Dhabi Award for Research Excellence (AARE-2019) under project number 8434000349/AARE19-232.

Author Contributions:

J.P: Conceptualization, Methodology, Data curation, Visualization, Formal analysis, Investigation, Writing—original draft. **K.N.**: Conceptualization, Methodology, Data curation, Software, Validation, Formal analysis, Visualization, Investigation, Writing—original draft. **G.R.**: Writing—review & editing, Investigation. **V.A.**: Writing—review & editing, formal analysis. **M.A.K.**: Writing—review & editing, formal analysis. **K.A.K.**: Conceptualization, Methodology, Writing—review & editing, Visualization, Resources, Investigation, Supervision, Project administration, Funding acquisition.

Conflict of interest:

The authors declare that there is no conflict of interest for this work.

References

1. Mahmud S, Hasan KMF, Jahid MA, Mohiuddin K, Zhang R, Zhu J (2021) Comprehensive review on plant fiber-reinforced polymeric biocomposites. Journal of Materials Science 56: 7231-64. Doi:10.1007/s10853-021-05774-9

2. Gholampour A, Ozbakkaloglu T (2019) A review of natural fiber composites: properties, modification and processing techniques, characterization, applications. Journal of Materials Science 55: 829-92. Doi:10.1007/s10853-019-03990-y

3. Wu Y, Wang Y, Yang F, Wang J, Wang X (2020) Study on the Properties of Transparent Bamboo Prepared by Epoxy Resin Impregnation. Polymers 12: 1-12. Doi:10.3390/polym12040863

4. Bhagat D, Bhalla S, West RP (2021) Fabrication and structural evaluation of fibre reinforced bamboo composite beams as green structural elements. Composites Part C: Open Access 5: 100150. Doi:10.1016/j.jcomc.2021.100150

5. Vigneshwaran S, Uthayakumar M, Arumugaprabu V (2019) Development and sustainability of industrial waste-based red mud hybrid composites. J Clean Prod 230: 862-8. Doi:10.1016/j.jclepro.2019.05.131

6. Joshi SV, Drzal LT, Mohanty AK, Arora S (2004) Are natural fiber composites environmentally superior to glass fiber reinforced composites? Compos Part A Appl Sci 35: 371-6.

7. Chandgude S, Salunkhe S (2021) In state of art: Mechanical behavior of natural fiber-based hybrid polymeric composites for application of automobile components. Polym Compos 42: 2678-703. Doi:10.1002/pc.26045

8. Chauhan V, Kärki T, Varis J (2021) Design of Tooling System and Identifying Crucial Processing Parameters for NFPC in Automotive Applications. J Compos Sci 5: 169. Doi:10.3390/jcs5070169

9. Amiri A, Burkart V, Yu A, Webster D, Ulven C (2018) Chapter 13, The potential of natural composite materials in structural design. Sustainable Composites for Aerospace Applications, Woodhead Publishing Series in Composites Science and Engineering: 269-91.

10. Grand View Research Natural fiber composites (NFC) market size, share & trends analysis report by raw material, by matrix, by technology (injection molding, compression molding, pultrusion), by application, and segment forecasts 2018-2014 Report ID: 978-1-68038-890-9.

11. Balla VK, Kate KH, Satyavolu J, Singh P, Tadimeti JGD (2019) Additive manufacturing of natural fiber reinforced polymer composites: Processing and prospects. Composites Part B: Engineering 174: 106956. Doi:10.1016/j.compositesb.2019.106956

12. Gomez-Campos A, Vialle C, Rouilly A, Sablayrolles C, Hamelin L (2021) Flax fiber for technical textile: A life cycle inventory. Journal of Cleaner Production 281: 125177. Doi:10.1016/j.jclepro.2020.125177

13. Azman MA, Asyraf MRM, Khalina A, Petru M, Ruzaidi CM, Sapuan SM, Wan Nik WB, Ishak MR, Ilyas RA, Suriani MJ (2021) Natural Fiber Reinforced Composite Material for Product Design: A Short Review. Polymers 13. Doi:10.3390/polym13121917

14. Dhar Malingam S, Ng LF, Chan KH, Subramaniam K, Selamat MZ, Zakaria KA (2018) The static and dynamic mechanical properties of kenaf/glass fibre reinforced hybrid composites. Materials Research Express 5. Doi:10.1088/2053-1591/aad58e

15. Vigneshwaran S, Sundarakannan R, John KM, Joel Johnson RD, Prasath KA, Ajith S, Arumugaprabu V, Uthayakumar M (2020) Recent advancement in the natural fiber polymer composites: A comprehensive review. Journal of Cleaner Production 277: 124109. Doi:10.1016/j.jclepro.2020.124109

16. Rafiee M, Abidnejad R, Ranta A, Ojha K, Karakoç A, Paltakari J (2021) Exploring the possibilities of FDM filaments comprising natural fiber-reinforced biocomposites for additive manufacturing. AIMS Materials Science 8: 524-37. Doi:10.3934/matersci.2021032

17. Pickering KL, Efendy MGA, Le TM (2016) A review of recent developments in natural fibre composites and their mechanical performance. Compos Part A Appl Sci 83: 98-112. Doi:10.1016/j.compositesa.2015.08.038

18. Moonart U, Utara S (2019) Effect of surface treatments and filler loading on the properties of hemp fiber/natural rubber composites. Cellulose 26: 7271-95. Doi:10.1007/s10570-019-02611-w

19. Zhang X, Fan X, Han C, Li Y, Price E, Wnek G, Liao Y-TT, Yu X (2021) Novel strategies to grow natural fibers with improved thermal stability and fire resistance. J Clean Prod 320: 128729. Doi:10.1016/j.jclepro.2021.128729

20. Prabhakar MN, Naga Kumar C, Woo LD, Jung-IL S (2021) Hybrid approach to improve the flame-retardant and thermal properties of sustainable biocomposites used in outdoor engineering applications. Composites Part A: Applied Science and Manufacturing: 106674. Doi:10.1016/j.compositesa.2021.106674

21. Manral A, Kumar Bajpai P, Ahmad F, Joshi R (2021) Processing of sustainable thermoplastic based biocomposites: A comprehensive review on performance enhancement. Journal of Cleaner Production 316: 128068. Doi:10.1016/j.jclepro.2021.128068

22. Thor M, Sause MGR, Hinterhölzl RM (2020) Mechanisms of Origin and Classification of Out-of-Plane Fiber Waviness in Composite Materials—A Review. J Compos Sci 4: 1-39. Doi:10.3390/jcs4030130

23. Thomas S, Balakrishnan P (2021) Green Composites. Springer Nature: 1-614. Doi:10.1007/978-981-15-9643-8

24. Vasudevan A, Senthil Kumaran S, Naresh K, Velmurugan R (2019) Layer-wise damage prediction in carbon/Kevlar/S-glass/E-glass fibre reinforced epoxy hybrid composites under low-velocity impact loading using advanced 3D computed tomography. International Journal of Crashworthiness: 1-15. Doi:10.1080/13588265.2018.1511234

25. Ziolkowski G, Pach J, Pyka D, Kurzynowski T, Jamroziak K (2020) X-ray Computed Tomography for the Development of Ballistic Composite. Materials 13: 1-19. Doi:10.3390/ma13235566

26. Tiwari KA, Raisutis R, Tumsys O, Ostreika A, Jankauskas K, Jakutavicius J (2019) Defect Estimation in Non-Destructive Testing of Composites by Ultrasonic Guided Waves and Image Processing. Electronics 8: 315. Doi:10.3390/electronics8030315

27. Loganathan TM, Sultan MTH, Muhammad Amir SM, Jamil J, Yusof MR, Md Shah AU (2021) Infrared Thermographic and Ultrasonic Inspection of Randomly-Oriented Short-Natural Fiber-Reinforced Polymeric Composites. Front Mater 7: 1-10. Doi:10.3389/fmats.2020.604459

28. Fracz W, Janowski G, Pruchniak M, Walek L (2021) The Use of Computed Tomography in the Study of Microstructure of Molded Pieces Made of Poly(3-hydroxybutyric-co-3-hydroxyvaleric acid) (PHBV) Biocomposites with Natural Fiber. Polymers 13: 1-13. Doi:10.3390/polym13172942

29. Suriani MJ, Rapi HZ, Ilyas RA, Petru M, Sapuan SM (2021) Delamination and Manufacturing Defects in Natural Fiber-Reinforced Hybrid Composite: A Review. Polymers (Basel) 13. Doi:10.3390/polym13081323

30. Melelli A, Durand S, Arnould O, Richely E, Guessasma S, Jamme F, Beaugrand J, Bourmaud A (2021) Extensive investigation of the ultrastructure of kink-bands in flax fibres. Ind Crops Prod 164: 113368. Doi:10.1016/j.indcrop.2021.113368

31. Ravikumar P, Rajeshkumar G, Manimegalai P, Sumesh KR, Sanjay MR, Siengchin S (2022) Delamination and surface roughness analysis of jute/polyester composites using response surface methodology: Consequence of sodium bicarbonate treatment. Journal of Industrial Textiles. Doi:10.1177/15280837221077040

32. Patel K, Gohil PP, Chaudhary V, Patel K (2015) Investigation on drilling of banana fibre reinforced composites. International Conference on Civil, Materials and Environmental Sciences (CMES 2015): 201-5.

33. Nassar MMA, Arunachalam R, Alzebdeh KI (2016) Machinability of natural fiber reinforced composites: a review. Int J Adv Manuf Syst 88: 2985-3004. Doi:10.1007/s00170-016-9010-9

34. Barouni AK, Rekatsinas CS (2021) Study on the Propagation of Stress Waves in Natural Fiber Composite Strips. Journal of Composites Science 5: 34. Doi:10.3390/jcs5010034

35. Naresh K, Khan KA, Umer R, Cantwell WJ (2020) The use of X-ray computed tomography for design and process modeling of aerospace composites: A review. Materials & Design 190: 108553. Doi:10.1016/j.matdes.2020.108553

36. Palombini FL, Lautert EL, Mariath JEdA, de Oliveira BF (2019) Combining numerical models and discretizing methods in the analysis of bamboo parenchyma using finite element analysis based on X-ray microtomography. Wood Science and Technology 54: 161-86. Doi:10.1007/s00226-019-01146-4

37. Jespersen KM, Glud JA, Zangenberg J, Hosoi A, Kawada H, Mikkelsen LP (2018) Ex-situ X-ray computed tomography, tension clamp and in-situ transilluminated white light imaging data of non-crimp fabric based fibre composite under fatigue loading. Data Brief 21: 228-33. Doi:10.1016/j.dib.2018.09.109

38. Wei Z, Fernandes H, Herrmann HG, Tarpani JR, Osman A (2021) A Deep Learning Method for the Impact Damage Segmentation of Curve-Shaped CFRP Specimens Inspected by Infrared Thermography. Sensors 21. Doi:10.3390/s21020395

39. Duan Y, Liu S, Hu C, Hu J, Zhang H, Yan Y, Tao N, Zhang C, Maldague X, Fang Q, Ibarra-Castanedo C, Chen D, Li X, Meng J (2019) Automated defect classification in infrared thermography based on a neural network. NDT & E International 107: 102147. Doi:10.1016/j.ndteint.2019.102147

40. Ramkumar G, Sahoo S, Anitha G, Ramesh S, Nirmala P, Tamilselvi M, Subbiah R, Rajkumar S, M R (2021) An Unconventional Approach for Analyzing the Mechanical Properties of Natural Fiber

Composite Using Convolutional Neural Network. Adv Mater Sci Eng 2021: 1-15. Doi:10.1155/2021/5450935

41. Caglar B, Broggi G, Ali MA, Orgéas L, Michaud V (2022) Deep learning accelerated prediction of the permeability of fibrous microstructures. Compos Part A Appl Sci: 106973. Doi:10.1016/j.compositesa.2022.106973

42. Alhijazi M, Zeeshan Q, Qin Z, Safaei B, Asmael M (2020) Finite element analysis of natural fibers composites: A review. Nanotechnology Reviews 9: 853-75. Doi:10.1515/ntrev-2020-0069

43. Richely E, Bourmaud A, Placet V, Guessasma S, Beaugrand J (2022) A critical review of the ultrastructure, mechanics and modelling of flax fibres and their defects. Progress in Materials Science 124. Doi:10.1016/j.pmatsci.2021.100851

44. Kern WT, Kim W, Argento A, Lee EC, Mielewski DF (2016) Finite element analysis and microscopy of natural fiber composites containing microcellular voids. Materials & Design 106: 285-94. Doi:10.1016/j.matdes.2016.05.094

45. Joffre T, Isaksson P, Dumont PJJ, Roscoat SRd, Sticko S, Orgéas L, Gamstedt EK (2016) A Method to Measure Moisture Induced Swelling Properties of a Single Wood Cell. Experimental Mechanics 56: 723-33. Doi:10.1007/s11340-015-0119-9

46. Ciano MP, Pozzi R, Rossi T, Strozzi F (2020) Digital twin-enabled smart industrial systems: a bibliometric review. Int J Comput Integr Manuf 34: 690-708. Doi:10.1080/0951192x.2020.1852600

47. Guessasma S, Beaugrand J (2019) Damage Kinetics at the Sub-micrometric Scale in Bast Fibers Using Finite Element Simulation and High-Resolution X-Ray Micro-Tomography. Front Plant Sci 10: 194. Doi:10.3389/fpls.2019.00194

48. Strohrmann K, Hajek M (2018) Bilinear approach to tensile properties of flax composites in finite element analyses. Journal of Materials Science 54: 1409-21. Doi:10.1007/s10853-018-2912-1

49. Dicker MPM, Duckworth PF, Baker AB, Francois G, Hazzard MK, Weaver PM (2014) Green composites: A review of material attributes and complementary applications. Composites Part A: Applied Science and Manufacturing 56: 280-9. Doi:10.1016/j.compositesa.2013.10.014

50. Mitra B (2014) Environment Friendly Composite Materials: Biocomposites and Green Composites. Defence Science Journal 64: 244-61. Doi:10.14429/dsj.64.7323

51. Yan L, Kasal B, Huang L (2016) A review of recent research on the use of cellulosic fibres, their fibre fabric reinforced cementitious, geo-polymer and polymer composites in civil engineering. Composites Part B: Engineering 92: 94-132. Doi:10.1016/j.compositesb.2016.02.002

52. Nurazzi NM, Asyraf MRM, Khalina A, Abdullah N, Aisyah HA, Rafiqah SA, Sabaruddin FA, Kamarudin SH, Norrrahim MNF, Ilyas RA, Sapuan SM (2021) A Review on Natural Fiber Reinforced

Polymer Composite for Bullet Proof and Ballistic Applications. Polymers (Basel) 13. Doi:10.3390/polym13040646

53. Gurunathan T, Mohanty S, Nayak SK (2015) A review of the recent developments in biocomposites based on natural fibres and their application perspectives. Composites Part A: Applied Science and Manufacturing 77: 1-25. Doi:10.1016/j.compositesa.2015.06.007

54. Khalid MY, Al Rashid A, Arif ZU, Ahmed W, Arshad H, Zaidi AA (2021) Natural fiber reinforced composites: Sustainable materials for emerging applications. Results in Engineering 11: 100263. Doi:10.1016/j.rineng.2021.100263

55. Bhagia S, Dunlap JR, Khuraishi MZA, Lowden RR, Muchero W, Vaidya UK, Pu Y, Ragauskas AJ (2021) Fabrication of Lignocellulosic Biomass Paper Containing Nanofibrillated Biomass. BioResources 16: 209-22.

56. Bhagia S, Bornani K, Agrawal R, Satlewal A, Ďurkovič J, Lagaňa R, Bhagia M, Yoo CG, Zhao X, Kunc V, Pu Y, Ozcan S, Ragauskas AJ (2021) Critical review of FDM 3D printing of PLA biocomposites filled with biomass resources, characterization, biodegradability, upcycling and opportunities for biorefineries. Applied Materials Today 24. Doi:10.1016/j.apmt.2021.101078

57. Rana AS, Vamshi MK, Naresh K, Velmurugan R, Sarathi R (2019) Mechanical, thermal, electrical and crystallographic behaviour of EPDM rubber/clay nanocomposites for out-door insulation applications. Advances in Materials and Processing Technologies 6: 54-74. Doi:10.1080/2374068x.2019.1703339

58. Rana AS, Vamshi MK, Naresh K, Velmurugan R, Sarathi R (2020) Effect of nanoclay on mechanical, thermal and morphological properties of silicone rubber and EPDM/silicone rubber hybrid composites. Advances in Materials and Processing Technologies 7: 109-16. Doi:10.1080/2374068x.2020.1754720

59. Pecas P, Carvalho H, Salman H, Leite M (2018) Natural Fibre Composites and Their Applications: A Review. Journal of Composites Science 2: 66. Doi:10.3390/jcs2040066

60. Huang S, Fu Q, Yan L, Kasal B (2021) Characterization of interfacial properties between fibre and polymer matrix in composite materials – A critical review. Journal of Materials Research and Technology 13: 1441-84. Doi:10.1016/j.jmrt.2021.05.076

61. Ha NS, Lu G (2020) A review of recent research on bio-inspired structures and materials for energy absorption applications. Composites Part B: Engineering 181. Doi:10.1016/j.compositesb.2019.107496

62. Pandey JK, Nagarajan V, Mohanty AK, Misra M. Commercial potential and competitiveness of natural fiber composites. Biocomposites2015. p. 1-15.

63. Meereboer KW, Misra M, Mohanty AK (2020) Review of recent advances in the biodegradability of polyhydroxyalkanoate (PHA) bioplastics and their composites. Green Chemistry 22: 5519-58. Doi:10.1039/d0gc01647k

64. Gironi F, Piemonte V (2011) Bioplastics and Petroleum-based Plastics: Strengths and Weaknesses. Energy Sources, Part A: Recovery, Utilization, and Environmental Effects 33: 1949-59. Doi:10.1080/15567030903436830

65. Gumede TP, Luyt AS, Muller AJ (2018) Review on PCL, PBS, and PCL/PBS blends containing carbon nanotubes. Express Polymer Letters 12: 505-29. Doi:10.3144/expresspolymlett.2018.43

66. Karthick SA, Ragavi T, Naresh K, Sreekanth PR (2022) A study on collagen-PVA and chitosan-PVA nanofibrous matrix for wound dressing application. Materials Today: Proceedings 56: 1347-50.

67. Averous L, Boquillon N (2004) Biocomposites based on plasticized starch: thermal and mechanical behaviours. Carbohydrate Polymers 56: 111-22. Doi:10.1016/j.carbpol.2003.11.015

68. Rajeshkumar G, Arvindh Seshadri S, Devnani GL, Sanjay MR, Siengchin S, Prakash Maran J, Al-Dhabi NA, Karuppiah P, Mariadhas VA, Sivarajasekar N, Ronaldo Anuf A (2021) Environment friendly, renewable and sustainable poly lactic acid (PLA) based natural fiber reinforced composites – A comprehensive review. Journal of Cleaner Production 310: 127483. Doi:10.1016/j.jclepro.2021.127483

69. Faruk O, Bledzki AK, Fink H-P, Sain M (2014) Progress Report on Natural Fiber Reinforced Composites. Macromolecular Materials and Engineering 299: 9-26. Doi:10.1002/mame.201300008

70. Muneer Ahmed M, Dhakal HN, Zhang ZY, Barouni A, Zahari R (2021) Enhancement of impact toughness and damage behaviour of natural fibre reinforced composites and their hybrids through novel improvement techniques: A critical review. Compos Struct 259: 113496. Doi:10.1016/j.compstruct.2020.113496

71. Ahmad F, Choi HS, Park MK (2015) A Review: Natural Fiber Composites Selection in View of Mechanical, Light Weight, and Economic Properties. Macromol Mater Eng 300: 10-24. Doi:10.1002/mame.201400089

72. Keerthi Gowda BS, Naresh K, Ilangovan S, Sanjay MR, Siengchin S (2021) Effect of Fiber Volume Fraction on Mechanical and Fire Resistance Properties of Basalt/Polyester and Pineapple/Polyester Composites. Journal of Natural Fibers.

73. Fiore V, Scalici T, Di Bella G, Valenza A (2015) A review on basalt fibre and its composites. Composites Part B: Engineering 74: 74-94. Doi:10.1016/j.compositesb.2014.12.034

74. Ilangovan S, Kumaran SS, Vasudevan A, Naresh K (2019) Effect of silica nanoparticles on mechanical and thermal properties of neat epoxy and filament wounded E-glass/epoxy and basalt/epoxy composite tubes. Materials Research Express 6. Doi:10.1088/2053-1591/ab2601

75. Li Z, Ma J, Ma H, Xu X (2018) Properties and Applications of Basalt Fiber and Its Composites. IOP Conf Series: Earth and Environmental Science 186: 012052

76. Ilangovan S, Senthil Kumaran S, Naresh K (2020) Effect of nanoparticles loading on free vibration response of epoxy and filament winding basalt/epoxy and E-glass/epoxy composite tubes: Experimental, analytical and numerical investigations. Materials Research Express. Doi:10.1088/2053-1591/ab6e36
77. Bouvier M, Guiheneuf V, Jean-marie A (2019) Modeling and simulation of a composite high-pressure vessel made of sustainable and renewable alternative fibers. International Journal of Hydrogen Energy 44: 11970-8. Doi:10.1016/j.ijhydene.2019.03.088
78. Arun Prasath KA, V, Amuthakkannan P, Naresh K, Muthugopal MS, Jeganathan M, Pragadeesh R (2020) Quasi static and flexural mechanical property evaluation of basalt/flax reinforced composites. Materials Physics and Mechanics 46: 132-8. Doi:10.18149/MPM.4612020_13
79. Gomez-Campos A, Vialle C, Rouilly A, Hamelin L, Rogeon A, Hardy D, Sablayrolles C (2021) Natural Fibre Polymer Composites - A game changer for the aviation sector? Journal of Cleaner Production 286: 124986. Doi:10.1016/j.jclepro.2020.124986
80. Ead AS, Appel R, Alex N, Ayranci C, Carey JP (2021) Life cycle analysis for green composites: A review of literature including considerations for local and global agricultural use. Journal of Engineered Fibers and Fabrics 16. Doi:10.1177/15589250211026940
81. Naresh K, Khan KA, Umer R (2021) Experimental Characterization and Modeling Multifunctional Properties of Epoxy/Graphene Oxide Nanocomposites. Polymers (Basel) 13. Doi:10.3390/polym13162831
82. Murugan P, Naresh K, Shankar K, Velmurugan R, Balaganesan G (2018) High velocity impact damage investigation of carbon/epoxy/clay nanocomposites using 3D Computed Tomography. Materials Today: Proceedings 5: 16946-55. Doi:10.1016/j.matpr.2018.04.098
83. Sundarakannan R, Arumugaprabu V, Manikandan V, Arun Prasath K, Vigneshwaran S, Naresh K (2022) Effect of polyethylene terephthalate char on impact and erosion properties of polyester matrix composites. Advances in Materials and Processing Technologies: 1-14. Doi:10.1080/2374068x.2022.2036589
84. Bazli L, Eskandarinezhad S, Kakur N, Ramachandran V, Bacigalupe A, Mansilla M, Escobar M (2021) Electrical properties of polymer blend composites based on Silicone rubber/EPDM/clay for high voltage insulators. Journal of Composites and Compounds 2: 18-24. Doi:10.52547/jcc.3.1.3
85. Gupta MK, Ramesh M, Thomas S (2021) Effect of hybridization on properties of natural and synthetic fiber-reinforced polymer composites (2001–2020): A review. Polym Compos 42: 4981-5010. Doi:10.1002/pc.26244
86. Dittenber DB, GangaRao HVS (2012) Critical review of recent publications on use of natural composites in infrastructure. Composites Part A: Applied Science and Manufacturing 43: 1419-29. Doi:10.1016/j.compositesa.2011.11.019

87. Kumar S, Prasad L, Patel VK, Kumar V, Kumar A, Yadav A, Winczek J (2021) Physical and Mechanical Properties of Natural Leaf Fiber-Reinforced Epoxy Polyester Composites. Polymers (Basel) 13. Doi:10.3390/polym13091369

88. Khalid MY, Imran R, Arif ZU, Akram N, Arshad H, Al Rashid A, García Márquez FP (2021) Developments in Chemical Treatments, Manufacturing Techniques and Potential Applications of Natural-Fibers-Based Biodegradable Composites. Coatings 11. Doi:10.3390/coatings11030293

89. da Luz FS, Garcia Filho FDC, Del-Rio MTG, Nascimento LFC, Pinheiro WA, Monteiro SN (2020) Graphene-Incorporated Natural Fiber Polymer Composites: A First Overview. Polymers (Basel) 12. Doi:10.3390/polym12071601

90. Rosenstock Voltz L, Di Guiseppe I, Geng S, Oksman K (2020) The Effect of Recycling on Wood-Fiber Thermoplastic Composites. Polymers 12: 1750. Doi:10.3390/polym12081750

91. Beg MDH, Pickering KL (2008) Reprocessing of wood fibre reinforced polypropylene composites. Part I: Effects on physical and mechanical properties. Compos Part A Appl Sci 39: 1091. Doi:10.1016/j.compositesa.2008.04.013

92. Srebrenkoska V, Gaceva GB, Avella M, Errico ME, Gentile G (2008) Recycling of polypropylene-based eco-composites. Polymer International 57: 1252-7. Doi:10.1002/pi.2470

93. Zhao X, Copenhaver K, Wang L, Korey M, Gardner DJ, Li K, Lamm ME, Kishore V, Bhagia S, Tajvidi M, Tekinalp H, Oyedeji O, Wasti S, Webb E, Ragauskas AJ, Zhu H, Peter WH, Ozcan S (2022) Recycling of natural fiber composites: Challenges and opportunities. Resources, Conservation and Recycling 177. Doi:10.1016/j.resconrec.2021.105962

94. Uitterhaegen E, Parinet J, Labonne L, Mérian T, Ballas S, Véronèse T, Merah O, Talou T, Stevens CV, Chabert F, Evon P (2018) Performance, durability and recycling of thermoplastic biocomposites reinforced with coriander straw. Compos Part A Appl Sci 113: 254-63. Doi:10.1016/j.compositesa.2018.07.038

95. Fonseca-Valero C, Ochoa-Mendoza A, Arranz-Andrés J, González-Sánchez C (2015) Mechanical recycling and composition effects on the properties and structure of hardwood cellulose-reinforced high density polyethylene eco-composites. Compos Part A Appl Sci 69: 94-104. Doi:10.1016/j.compositesa.2014.11.009

96. M RS, Siengchin S, Parameswaranpillai J, Jawaid M, Pruncu CI, Khan A (2019) A comprehensive review of techniques for natural fibers as reinforcement in composites: Preparation, processing and characterization. Carbohydr Polym 207: 108-21. Doi:10.1016/j.carbpol.2018.11.083

97. Nurazzi NM, Harussani MM, Aisyah HA, Ilyas RA, Norrrahim MNF, Khalina A, Abdullah N (2021) Treatments of natural fiber as reinforcement in polymer composites—a short review. Functional Composites and Structures 3: 024002. Doi:10.1088/2631-6331/abff36

98. Begum S, Fawzia S, Hashmi MSJ (2020) Polymer matrix composite with natural and synthetic fibres. Advances in Materials and Processing Technologies 6: 547-64. Doi:10.1080/2374068x.2020.1728645

99. Karthi N, Kumaresan K, Rajeshkumar G, Gokulkumar S, Sathish S (2021) Tribological and Thermo-Mechanical Performance of Chemically Modified Musa Acuminata / Corchorus Capsularis Reinforced Hybrid Composites. Journal of Natural Fibers: 1-14. Doi:10.1080/15440478.2020.1870614

100. Mwaikambo LY, Ansell MP (2002) Chemical modification of hemp, sisal, jute, and kapok fibers by alkalization. Journal of Applied Polymer Science 84: 2222-34. Doi:10.1002/app.10460

101. Thyavihalli Girijappa YG, Mavinkere Rangappa S, Parameswaranpillai J, Siengchin S (2019) Natural Fibers as Sustainable and Renewable Resource for Development of Eco-Friendly Composites: A Comprehensive Review. Frontiers in Materials 6. Doi:10.3389/fmats.2019.00226

102. Rahman M, Das S, Hasan M (2018) Mechanical properties of chemically treated banana and pineapple leaf fiber reinforced hybrid polypropylene composites. Adv Mater Process Technol 4: 527-37. Doi:10.1080/2374068x.2018.1468972

103. Ighalo JO, Adeyanju CA, Ogunniyi S, Adeniyi AG, Abdulkareem SA (2020) An empirical review of the recent advances in treatment of natural fibers for reinforced plastic composites. Composite Interfaces 28: 925-60. Doi:10.1080/09276440.2020.1826274

104. Mohanty AK, Vivekanandhan S, Pin J-M, Misra M (2018) Composites from renewable and sustainable resources: Challenges and innovations. Science 362: 536-42.

105. Rastogi V, Samyn P (2015) Bio-Based Coatings for Paper Applications. Coatings 5: 887. Doi:10.3390/coatings5040887

106. Santhosh Kumar S, Hiremath SS (2020) Natural Fiber Reinforced Composites in the Context of Biodegradability: A Review. 160-78. Doi:10.1016/b978-0-12-803581-8.11418-3

107. Srinivas K, Lakshumu Naidu A, Raju Bahubalendruni MVA (2017) A Review on Chemical and Mechanical Properties of Natural Fiber Reinforced Polymer Composites. Int J Performability Eng 13: 189-200. Doi:10.23940/ijpe.17.02.p8.189200

108. Lukaszewicz DHJA, Ward C, Potter KD (2012) The engineering aspects of automated prepreg layup: History, present and future. Composites Part B: Engineering 43: 997-1009. Doi:10.1016/j.compositesb.2011.12.003

109. Parmar H, Khan T, Tucci F, Umer R (2021) Advanced robotics and additive manufacturing of composites: towards a new era in Industry 4.0. Mater Manuf Process: 1-35. Doi:10.1080/10426914.2020.1866195

110. Selva Priya M, Naresh K, Jayaganthan R, Velmurugan R (2019) A comparative study between in-house 3D printed and injection molded ABS and PLA polymers for low-frequency applications. Materials Research Express 6: 085345. Doi:10.1088/2053-1591/ab2776

111. Sekar V, Fouladi MH, Namasivayam SN, Sivanesan S (2019) Additive Manufacturing: A Novel Method for Developing an Acoustic Panel Made of Natural Fiber-Reinforced Composites with Enhanced Mechanical and Acoustical Properties. Journal of Engineering 2019: 1-19. Doi:10.1155/2019/4546863

112. Naresh K, Salem A, Khan KA, Cantwell WJ, Umer R (2021) Thermo-Mechanical Compaction-Creep and Void Analysis of Prepregs Using XCT-Aided Geometrical Models. Appl Compos Mater 28: 659–84. Doi:10.1007/s10443-021-09877-z

113. Fairuz AM, Sapuan SM, Zainudin ES, Jaafar CNA (2015) Pultrusion Process of Natural Fibre-Reinforced Polymer Composites. Chapter 11, Manufacturing of Natural Fibre Reinforced Polymer Composites: 217-31. Doi:10.1007/978-3-319-07944-8_11

114. Vinod A, Tengsuthiwat J, Gowda Y, Vijay R, Sanjay MR, Siengchin S, Dhakal HN (2022) Jute/Hemp bio-epoxy hybrid bio-composites: Influence of stacking sequence on adhesion of fiber-matrix. International Journal of Adhesion and Adhesives 113. Doi:10.1016/j.ijadhadh.2021.103050

115. Aleksendric D, Carlone P (2015) Soft Computing in the Design and Manufacturing of Composite Materials. Woodhead Publishing, United Kingdom: 15-38.

116. Shrigandhi GD, Kothavale BS (2021) Biodegradable composites for filament winding process. Materials Today: Proceedings 42: 2762-8. Doi:10.1016/j.matpr.2020.12.718

117. Naresh K, Shankar K, Rao BS, Velmurugan R (2016) Effect of high strain rate on glass/carbon/hybrid fiber reinforced epoxy laminated composites. Composites Part B: Engineering 100: 125-35. Doi:10.1016/j.compositesb.2016.06.007

118. Naresh K, Shankar K, Velmurugan R, Gupta NK (2018) Statistical analysis of the tensile strength of GFRP, CFRP and hybrid composites. Thin-Walled Structures 126: 150-61. Doi:10.1016/j.tws.2016.12.021

119. Naresh K, Khan KA, Umer R, Vasudevan A (2020) Temperature-Frequency-Dependent Viscoelastic Properties of Neat Epoxy and Fiber Reinforced Polymer Composites: Experimental Characterization and Theoretical Predictions. Polymers 12: 1700. Doi:10.3390/polym12081700

120. Khan T, Irfan MS, Cantwell WJ, Umer R (2022) Crack healing in infusible thermoplastic composite laminates. Composites Part A: Applied Science and Manufacturing 156. Doi:10.1016/j.compositesa.2022.106896

121. Naresh K, Salem A, Khan KA, Cantwell WJ, Umer R (2021) Isothermal compaction-creep-recovery behavior and statistical void analysis of prepregs under various process parameters. Composites Part A: Applied Science and Manufacturing: 106663. Doi:10.1016/j.compositesa.2021.106663

122. Ud Din I, Naresh K, Umer R, Khan KA, Drzal LT, Haq M, Cantwell WJ (2020) Processing and out-of-plane properties of composites with embedded graphene paper for EMI shielding applications. Composites Part A: Applied Science and Manufacturing 134: 105901. Doi:10.1016/j.compositesa.2020.105901

123. Minchenkov K, Vedernikov A, Safonov A, Akhatov I (2021) Thermoplastic Pultrusion: A Review. Polymers 13. Doi:10.3390/polym13020180

124. Gadam SUK, Roux JA, McCarty TA, Vaughan JG (2000) The impact of pultrusion processing parameters on resin pressure rise inside a tapered cylindrical die for glass-fibre/epoxy composites. Composites Science and Technology 60: 945-58.

125. Zhang H, Huang T, Jiang Q, He L, Bismarck A, Hu Q (2021) Recent progress of 3D printed continuous fiber reinforced polymer composites based on fused deposition modeling: a review. Journal of Materials Science 56: 12999-3022. Doi:10.1007/s10853-021-06111-w

126. Frketic J, Dickens T, Ramakrishnan S (2017) Automated manufacturing and processing of fiber-reinforced polymer (FRP) composites: An additive review of contemporary and modern techniques for advanced materials manufacturing. Additive Manufacturing 14: 69-86. Doi:10.1016/j.addma.2017.01.003

127. Chansoda K, Suvanjumrat C, Chookaew W (2021) Comparative study on the wood-based PLA fabricated by compression
molding and additive manufacturing. IOP Conf Series: Materials Science and Engineering 1137: 012032.

128. Immonen K, Willberg-Keyrilainen P, Ropponen J, Nurmela A, Metsa-Kortelainen S, Kaukoniemi OV, Kangas H (2021) Thermoplastic Cellulose-Based Compound for Additive Manufacturing. Molecules 26. Doi:10.3390/molecules26061701

129. Le Duigou A, Fruleux T, Matsuzaki R, Chabaud G, Ueda M, Castro M (2021) 4D printing of continuous flax-fibre based shape-changing hygromorph biocomposites: Towards sustainable metamaterials. Materials & Design 211. Doi:10.1016/j.matdes.2021.110158

130. Le Duigou A, Correa D, Ueda M, Matsuzaki R, Castro M (2020) A review of 3D and 4D printing of natural fibre biocomposites. Materials & Design 194: 108911. Doi:10.1016/j.matdes.2020.108911

131. Ji A, Zhang S, Bhagia S, Yoo CG, Ragauskas AJ (2020) 3D printing of biomass-derived composites: application and characterization approaches. RSC Advances 10: 21698-723. Doi:10.1039/d0ra03620j

132. Lotfi A, Li H, Dao DV, Prusty G (2019) Natural fiber–reinforced composites: A review on material, manufacturing, and machinability. J Thermoplast Compos Mater 34: 238-84. Doi:10.1177/0892705719844546

133. Baley C, Kervoëlen A, Lan M, Cartié D, Le Duigou A, Bourmaud A, Davies P (2016) Flax/PP manufacture by automated fibre placement (AFP). Materials & Design 94: 207-13. Doi:10.1016/j.matdes.2016.01.011

134. Sanandiya ND, Vijay Y, Dimopoulou M, Dritsas S, Fernandez JG (2018) Large-scale additive manufacturing with bioinspired cellulosic materials. Sci Rep 8: 8642. Doi:10.1038/s41598-018-26985-2

135. Quanjin M, Rejab MRM, Kaige J, Idris MS, Harith MN (2018) Filament winding technique, experiment and simulation analysis on tubular structure. IOP Conf Ser: Mater Sci Eng 342: 012029. Doi:10.1088/1757-899x/342/1/012029

136. Kim BC, Potter K, Weaver PM (2012) Continuous tow shearing for manufacturing variable angle tow composites. Composites Part A: Applied Science and Manufacturing 43: 1347-56. Doi:10.1016/j.compositesa.2012.02.024

137. Zhang L, Wang X, Pei J, Zhou Y (2020) Review of automated fibre placement and its prospects for advanced composites. Journal of Materials Science 55: 7121-55. Doi:10.1007/s10853-019-04090-7

138. Zhang W, Liu F, Jiang T, Yi M, Chen W (2021) Overview of current design and analysis of potential theories for automated fibre placement mechanisms. Chinese J Aeronaut 35: 1-13. Doi:10.1016/j.cja.2021.04.018

139. Wang H, Chen J, Fan Z, Xiao J, Wang X (2021) Experimental Investigation on the Influence of Fiber Path Curvature on the Mechanical Properties of Composites. Materials (Basel) 14. Doi:10.3390/ma14102602

140. Han ZY, Fu HY, Fu Y, Z (2004) Analysis and application of filament winding with concave curved surface. Propul Technol 25: 286-8.

141. Wang GY, Cao J, Zhang H (2012) A 2-axis computer-controlled winding forming method for composite bend pipe. J Harbin Technol U 44: 130-4.

142. Harik R (2020) Next automated fiber placement: advancing composites manufacturing towards a new paradigm. SAMPE J: 6-14.

143. Ge X (2012) Parameterized self-motion manifold of 7-DOF automatic fiber placement robotic manipulator. J Mech Eng 48: 27-31.

144. Brasington A, Sacco C, Halbritter J, Wehbe R, Harik R (2021) Automated fiber placement: A review of history, current technologies, and future paths forward. Composites Part C: Open Access 6: 100182. Doi:10.1016/j.jcomc.2021.100182

145. Taneva E, Kusnoto B, Evans CA. 3D Scanning, Imaging, and Printing in Orthodontics. Issues in Contemporary Orthodontics2015.

146. Schmidleithner C, Kalaskar DM. Stereolithography. 3D Printing2018.

147. Tan LJ, Zhu W, Zhou K (2020) Recent Progress on Polymer Materials for Additive Manufacturing. Advanced Functional Materials 30: 2003062. Doi:10.1002/adfm.202003062

148. Wu Y, Li C, Chen T, Qiu R, Liu W (2021) Photo-curing 3D printing of micro-scale bamboo fibers reinforced palm oil-based thermosets composites. Compos Part A Appl: 106676. Doi:10.1016/j.compositesa.2021.106676

149. Goh GD, Yap YL, Agarwala S, Yeong WY (2019) Recent Progress in Additive Manufacturing of Fiber Reinforced Polymer Composite. Advanced Materials Technologies 4: 1800271. Doi:10.1002/admt.201800271

150. Fidan I, Imeri A, Gupta A, Hasanov S, Nasirov A, Elliott A, Alifui-Segbaya F, Nanami N (2019) The trends and challenges of fiber reinforced additive manufacturing. Int J Adv Manuf Syst 102: 1801-18. Doi:10.1007/s00170-018-03269-7

151. Low Z-X, Chua YT, Ray BM, Mattia D, Metcalfe IS, Patterson DA (2017) Perspective on 3D printing of separation membranes and comparison to related unconventional fabrication techniques. Journal of Membrane Science 523: 596-613. Doi:10.1016/j.memsci.2016.10.006

152. Yang Y, Song X, Li X, Chen Z, Zhou C, Zhou Q, Chen Y (2018) Recent Progress in Biomimetic Additive Manufacturing Technology: From Materials to Functional Structures. Adv Mater: e1706539. Doi:10.1002/adma.201706539

153. Azlin MNM, Ilyas RA, Zuhri MYM, Sapuan SM, Harussani MM, Sharma S, Nordin AH, Nurazzi NM, Afiqah AN (2022) 3D Printing and Shaping Polymers, Composites, and Nanocomposites: A Review. Polymers 14: 180. Doi:10.3390/polym14010180

154. Verma P, Ubaid J, Schiffer A, Jain A, Martínez-Pañeda E, Kumar S (2021) Essential work of fracture assessment of acrylonitrile butadiene styrene (ABS) processed via fused filament fabrication additive manufacturing. Int J Adv Manuf Syst 113: 771-84. Doi:10.1007/s00170-020-06580-4

155. Budelmann D, Schmidt C, Meiners D (2020) Prepreg tack: A review of mechanisms, measurement, and manufacturing implication. Polymer Composites 41: 3440-58. Doi:10.1002/pc.25642

156. Szcesny M, Heieck F, Carosella S, Middendorf P, Sehrschön H, Schneiderbauer M (2017) The advanced ply placement process – an innovative direct 3D placement technology for plies and tapes. Advanced Manufacturing: Polymer & Composites Science 3: 2-9. Doi:10.1080/20550340.2017.1291398

157. Sefene EM (2022) State-of-the-art of selective laser melting process: A comprehensive review. Journal of Manufacturing Systems 63: 250-74. Doi:10.1016/j.jmsy.2022.04.002

158. Cruz Sanchez FA, Boudaoud H, Camargo M, Pearce JM (2020) Plastic recycling in additive manufacturing: A systematic literature review and opportunities for the circular economy. Journal of Cleaner Production 264: 121602. Doi:10.1016/j.jclepro.2020.121602

159. Moumen AE, Tarfaoui M, Lafdi K (2019) Additive manufacturing of polymer composites: Processing and modeling approaches. composites Part B: Engineering 171: 166-82.
160. Nadimpalli VK, Na JK, Bruner DT, King BA, Yang L, Stucker BE (2016) In-Situ Non-Destructive Evaluation of Ultrasonic Additive Manufactured Components. Solid Freeform Fabrication 2016: Proceedings of the 26th Annual International Solid Freeform Fabrication Symposium – An Additive Manufacturing Conference Reviewed Paper: 1557-67.
161. Brenken B, Barocio E, Favaloro A, Kunc V, Pipes RB (2018) Fused filament fabrication of fiber-reinforced polymers: A review. Additive Manufacturing 21: 1-16. Doi:10.1016/j.addma.2018.01.002
162. Rajendran Royan NR, Leong JS, Chan WN, Tan JR, Shamsuddin ZSB (2021) Current State and Challenges of Natural Fibre-Reinforced Polymer Composites as Feeder in FDM-Based 3D Printing. Polymers 13. Doi:10.3390/polym13142289
163. Mitchell A, Lafont U, Hołyńska M, Semprimoschnig C (2018) Additive manufacturing — A review of 4D printing and future applications. Additive Manufacturing 24: 606-26. Doi:10.1016/j.addma.2018.10.038
164. Lee CH, Padzil F, Lee SH, Ainun ZMA, Abdullah LC (2021) Potential for Natural Fiber Reinforcement in PLA Polymer Filaments for Fused Deposition Modeling (FDM) Additive Manufacturing: A Review. Polymers (Basel) 13. Doi:10.3390/polym13091407
165. Maguire A, Pottackal N, Saadi MASR, Rahman MM, Ajayan PM (2021) Additive manufacturing of polymer-based structures by extrusion technologies. Oxford Open Materials Science 1. Doi:10.1093/oxfmat/itaa004
166. Nascimento HM, Granzotto DCT, Radovanovic E, Fávaro SL (2021) Obtention and characterization of polypropylene composites reinforced with new natural fibers from Yucca aloifolia L. Composites Part B: Engineering 227. Doi:10.1016/j.compositesb.2021.109414
167. Sacco C, Baz Radwan A, Anderson A, Harik R, Gregory E (2020) Machine learning in composites manufacturing: A case study of Automated Fiber Placement inspection. Composite Structures 250: 112514. Doi:10.1016/j.compstruct.2020.112514
168. Wehbe R, Sacco C, Baz Radwan A, Albazzan M, Harik R (2020) Influence of process parameters in AFP fiber steering on cylinders: Constant curvature paths. Composites Part C: Open Access 2: 100036. Doi:10.1016/j.jcomc.2020.100036
169. Sacco C, Brasington A, Saidy C, Kirkpatrick M, Halbritter J, Wehbe R, Harik R (2021) On the effect of manual rework in AFP quality control for a doubly-curved part. Composites Part B: Engineering 227. Doi:10.1016/j.compositesb.2021.109432
170. BahamondeJácome LG, Albazzan MA, Chevalier PL, Gürdal Z, Tatting BF, Harik R (2018) Rapid tools for an AFP manufacturing defects assessment framework, SAMPE 2018, Long Beach, California.

171. Sacco C (2017) Machine Learning Methods for Rapid Inspection of Automated Fiber Placement Manufactured Composite Structures. Chapter 3, Thesis and dissertation: Master of Science in Aerospace Engineering, University of South Carolina: 29-54.
172. Raspall F, Velu R, Vaheed NM (2019) Fabrication of complex 3D composites by fusing automated fiber placement (AFP) and additive manufacturing (AM) technologies. Advanced Manufacturing: Polymer & Composites Science 5: 6-16. Doi:10.1080/20550340.2018.1557397
173. Vistagy I (2012) Vistagy Fiber SIM 2012 Brochure. Spring, New York.
174. Hasenjaeger B (2013) Programming and simulating automated fiber placement CNC machines. SAMPE J 49: 7-13.
175. Cheng T, Wood D, Antorveza K, Kiesewetter L, Ozdemir E, Menges A (2021) Programming material compliance and actuation: hybrid additive fabrication of biocomposite structures for large-scale self-shaping. Bioinspir Biomim 16: 055004.
176. Ltd C (2012) VERICUT Composite Brochure. Springer, New York.
177. Lee NA, Weber RE, Kennedy JH, Van Zak JJ, Smith M, Duro-Royo J, Oxman N (2020) Sequential Multimaterial Additive Manufacturing of Functionally Graded Biopolymer Composites. 3D Printing and Additive Manufacturing 7: 205-15.
178. Nicholas P, Rossi G, Williams E, Bennett M, Schork T (2020) Integrating real-time multi-resolution scanning and machine learning for Conformal Robotic 3D Printing in Architecture. International Journal of Architectural Computing 18: 371-84. Doi:10.1177/1478077120948203
179. Spickenheuer A, Scheffler C, Bittrich L, Haase R, Weise D, Garray D (2018) Tailored Fiber Placement in Thermoplastic Composites. Technologies for Lightweight Structures 1: 114. Doi:10.21935/tls.v1i2.95
180. Lozano GG, Tiwari A, Turner C, Astwood S (2015) A review on design for manufacture of variable stiffness composite laminates. Proc Inst Mech Eng B J Eng Manuf 230: 981-92. Doi:10.1177/0954405415600012
181. Rihaczek G, Klammer M, Basnak O, Petrs J, Grisin B, Dahy H, Carosella S, Middendorf P (2020) Curved Foldable Tailored Fiber Reinforcements for Moldless Customized Bio-Composite Structures. Proof of Concept: Biomimetic NFRP Stools. Polymers 12. Doi:10.3390/polym12092000
182. Sippach T, Dahy H, Uhlig K, Grisin B, Carosella S, Middendorf P (2020) Structural Optimization through Biomimetic-Inspired Material-Specific Application of Plant-Based Natural Fiber-Reinforced Polymer Composites (NFRP) for Future Sustainable Lightweight Architecture. Polymers 12. Doi:10.3390/polym12123048
183. Costalonga Martins V, Cutajar S, van der Hoven C, Baszyński P, Dahy H (2020) FlexFlax Stool: Validation of Moldless Fabrication of Complex Spatial Forms of Natural Fiber-Reinforced Polymer

(NFRP) Structures through an Integrative Approach of Tailored Fiber Placement and Coreless Filament Winding Techniques. Applied Sciences 10. Doi:10.3390/app10093278

184. Cutajar S, Martins VC, Hoven Cvd, Baszyński P, Dahy H (2020) Towards Modular Natural FiberReinforced Polymer Architecture. Proceedings of the 40th Annual Conference of the Association of Computer Aided Design in Architecture 1: 564-73.

185. Wright T, Bechtold T, Bernhard A, Manian AP, Scheiderbauer M (2019) Tailored fibre placement of carbon fibre rovings for reinforced polypropylene composite part 1: PP infusion of carbon reinforcement. Composites Part B: Engineering 162: 703-11. Doi:10.1016/j.compositesb.2019.01.016

186. El-Dessouky HM, Saleh MN, Gautam M, Han G, Scaife RJ, Potluri P (2019) Tailored fibre placement of commingled carbon-thermoplastic fibres for notch-insensitive composites. Composite Structures 214: 348-58. Doi:10.1016/j.compstruct.2019.02.043

187. Uhlig K, Bittrich L, Spickenheuer A, Almeida JHS (2019) Waviness and fiber volume content analysis in continuous carbon fiber reinforced plastics made by tailored fiber placement. Compos Struct 222: 110910. Doi:10.1016/j.compstruct.2019.110910

188. Almeida JHS, Bittrich L, Jansen E, Tita V, Spickenheuer A (2019) Buckling optimization of composite cylinders for axial compression: A design methodology considering a variable-axial fiber layout. Compos Struct 222. Doi:10.1016/j.compstruct.2019.110928

189. Wu Z, Raju G, Weaver PM (2015) Framework for the Buckling Optimization of Variable-Angle Tow Composite Plates. AIAA Journal 53: 3788-804. Doi:10.2514/1.J054029

190. Raj SSR, Dhas JER, Jesuthanam CP (2020) Challenges on machining characteristics of natural fiber-reinforced composites – A review. J Reinf Plast Compos 40: 41-69. Doi:10.1177/0731684420940773

191. Masoud F, Sapuan SM, Mohd Ariffin MKA, Nukman Y, Bayraktar E (2020) Cutting Processes of Natural Fiber-Reinforced Polymer Composites. Polymers 12. Doi:10.3390/polym12061332

192. Patel K, Patel K, Gohil P, Chaudhary V (2018) Investigations of Milling Parameters on Hemp Fiber Reinforced Composite Using ANOVA and Regression. Appl Mech Mater 877: 177-82. Doi:10.4028/www.scientific.net/AMM.877.177

193. Balasubramanian K, Sultan MTH, Cardona F, Rajeswari N (2016) Machining analysis of natural fibre reinforced composites using fuzzy logic. IOP Conf Ser: Mater Sci Eng 152: 1-7.

194. Venkateshwaran N, ElayaPerumal A (2013) Hole quality evaluation of natural fiber composite using image analysis technique. Journal of Reinforced Plastics and Composites 32: 1188-97. Doi:10.1177/0731684413486847

195. Liu S, Bao J, Lu Y, Li J, Lu S, Sun X (2021) Digital twin modeling method based on biomimicry for machining aerospace components. Journal of Manufacturing Systems 58: 180-95. Doi:10.1016/j.jmsy.2020.04.014

196. Lazarus BS, Velasco-Hogan A, Gómez-del Río T, Meyers MA, Jasiuk I (2020) A review of impact resistant biological and bioinspired materials and structures. J Mater Res Technol 9: 15705-38. Doi:10.1016/j.jmrt.2020.10.062

197. Aisyah HA, Paridah MT, Sapuan SM, Ilyas RA, Khalina A, Nurazzi NM, Lee SH, Lee CH (2021) A Comprehensive Review on Advanced Sustainable Woven Natural Fibre Polymer Composites. Polymers 13. Doi:10.3390/polym13030471

198. Bandaru AK, Chouhan H, Bhatnagar N (2020) High strain rate compression testing of intra-ply and inter-ply hybrid thermoplastic composites reinforced with Kevlar/basalt fibers. Polymer Testing 84: 106407. Doi:10.1016/j.polymertesting.2020.106407

199. M B, Kumaran SS, Samson PE (2021) Effect of silica nanoparticles on mechanical and thermal properties of intra-inter ply hybrid laminated composites. Materials Research Express 8. Doi:10.1088/2053-1591/abf530

200. https://wwwdesignworldonlinecom/what-is-polymer-directed-energy-deposition-ded-for-3d-printing-and-how-can-it-benefit-you/.

201. Shah DU (2014) Natural fibre composites: Comprehensive Ashby-type materials selection charts. Materials & Design (1980-2015) 62: 21-31. Doi:10.1016/j.matdes.2014.05.002

202. Sarikaya E, Çallioğlu H, Demirel H (2019) Production of epoxy composites reinforced by different natural fibers and their mechanical properties. Composites Part B: Engineering 167: 461-6. Doi:10.1016/j.compositesb.2019.03.020

203. Senthilrajan S, Venkateshwaran N, Naresh K (2022) Parametric Study of different Fiber Parameters and their Influence on Acoustics and Vibration Behavior of Jute Fiber/Polyester resin Composites. Journal of Natural Fibers: 1-13. Doi:10.1080/15440478.2022.2085225

204. Sanjeevi S, Shanmugam V, Kumar S, Ganesan V, Sas G, Johnson DJ, Shanmugam M, Ayyanar A, Naresh K, Neisiany RE, Das O (2021) Effects of water absorption on the mechanical properties of hybrid natural fibre/phenol formaldehyde composites. Sci Rep 11: 13385. Doi:10.1038/s41598-021-92457-9

205. Moyo M, Kanny K, Velmurugan R (2020) Performance of Kenaf Non-woven Mat/PLA Biocomposites under Medium Velocity Impact. Fibers and Polymers 21: 2642-51. Doi:10.1007/s12221-020-1130-z

206. Salman SD, Leman Z, Sultan MTH, Ishak MR, Cardona F (2016) Ballistic Impact Resistance of Plain Woven Kenaf/Aramid Reinforced Polyvinyl Butyral Laminated Hybrid Composite. BioResources 11: 7282-95.

207. Moyo M, Kanny K, Velmurugan R (2020) The efficacy of nanoclay loading in the medium velocity impact resistance of kenaf/PLA biocomposites. Applied Nanoscience 11: 441-53. Doi:10.1007/s13204-020-01602-9

208. Azmi AMR, Sultan MTH, Jawaid M, Talib ARA, Nor AFM (2018) Tensile and Flexural Properties of a Newly Developed Bulletproof Vest Using a Kenaf/X-ray Film Hybrid Composite. BioResources 13: 4416-27.

209. Yahaya R, Sapuan SM, Jawaid M, Leman Z, Zainudin ES (2014) Quasi-static penetration and ballistic properties of kenaf–aramid hybrid composites. Materials & Design 63: 775-82. Doi:10.1016/j.matdes.2014.07.010

210. Bandaru AK, Ahmad S, Bhatnagar N (2017) Ballistic performance of hybrid thermoplastic composite armors reinforced with Kevlar and basalt fabrics. Composites Part A: Applied Science and Manufacturing 97: 151-65. Doi:10.1016/j.compositesa.2016.12.007

211. Velmurugan R, Naresh K, Shankar K (2017) Influence of fibre orientation and thickness on the response of CFRP composites subjected to high velocity impact loading. Advances in Materials and Processing Technologies 4: 120-31. Doi:10.1080/2374068x.2017.1410688

212. Zhang K, Wang F, Yang B, Li L, Gao L, Sun Y, Guo F (2022) Mechanical Response and Failure Mechanisms of Natural Bamboo Fiber Reinforced Poly-Benzoxazine Composite Subjected to Split-Hopkinson Tensile Bar Loading. Polymers 14. Doi:10.3390/polym14071450

213. Naresh K, Shankar K, Velmurugan R, Gupta NK (2020) High strain rate studies for different laminate configurations of bi-directional glass/epoxy and carbon/epoxy composites using DIC. Structures 27: 2451-65. Doi:10.1016/j.istruc.2020.05.022

214. Liu Y, Shen J, Li Y, Ge X, Li Y (2021) Enhanced high-strain-rate impact resistance of helicoidal composites by fused deposition modelling. Mech Adv Mater Struct: 1-13. Doi:10.1080/15376494.2021.2006837

215. Naresh K, Rajalakshmi K, Vasudevan A, Senthil Kumaran S, Velmurugan R, Shankar K (2018) Effect of nanoclay and different impactor shapes on glass/epoxy composites subjected to quasi-static punch shear loading. Advances in Materials and Processing Technologies 4: 345-57. Doi:10.1080/2374068x.2018.1428879

216. Naresh K, Cantwell WJ, Khan KA, Umer R (2021) Single and multi-layer core designs for Pseudo-Ductile failure in honeycomb sandwich structures. Composite Structures 256: 113059. Doi:10.1016/j.compstruct.2020.113059

217. Sarasini F, Tirillo J, D'Altilia S, Valente T, Santulli C, Touchard F (2016) Damage tolerance of carbon/flax hybrid composites subjected to LVI. Compos B Eng 91: 144.

218. Santulli C (2019) Mechanical and Impact Damage Analysis on Carbon/Natural Fibers Hybrid Composites: A Review. Materials 12: 517. Doi:10.3390/ma12030517

219. Otani LB, Alves H, Melo JDD, Amico SC (2014) Elastic Moduli characterization of

composites using the Impulse Excitation Technique. Technical-scientific Informative ITC-06 / ATCP, ATCP Physical Engineering: 1-36. Doi:10.13140/RG.2.1.1551.2481

220. Jiang H, Qin S, Fu J, Zhang J, Ding G (2021) How to model and implement connections between physical and virtual models for digital twin application. Journal of Manufacturing Systems 58: 36-51. Doi:10.1016/j.jmsy.2020.05.012

221. Xia K, Sacco C, Kirkpatrick M, Saidy C, Nguyen L, Kircaliali A, Harik R (2021) A digital twin to train deep reinforcement learning agent for smart manufacturing plants: Environment, interfaces and intelligence. Journal of Manufacturing Systems 58: 210-30. Doi:10.1016/j.jmsy.2020.06.012

222. Katunin A, Dragan K, Nowak T, Chalimoniuk M (2021) Quality Control Approach for the Detection of Internal Lower Density Areas in Composite Disks in Industrial Conditions Based on a Combination of NDT Techniques. Sensors 21: 1-25. Doi:10.3390/s21217174

223. Alhammad M, Fragonara LZ, Avdelidis NP Diagnosis of Composite Materials in Aircraft Applications–Brief Survey of Recent Literature. Preprints. Doi:10.20944/preprints202011.0216.v1

224. Nsengiyumva W, Zhong S, Lin J, Zhang Q, Zhong J, Huang Y (2021) Advances, limitations and prospects of nondestructive testing and evaluation of thick composites and sandwich structures: A state-of-the-art review. Composite Structures 256: 112951. Doi:10.1016/j.compstruct.2020.112951

225. Gupta R, Mitchell D, Blanche J, Harper S, Tang W, Pancholi K, Baines L, Bucknall DG, Flynn D (2021) A Review of Sensing Technologies for Non-Destructive Evaluation of Structural Composite Materials. Journal of Composites Science 5. Doi:10.3390/jcs5120319

226. Wang B, Zhong S, Lee T-L, Fancey KS, Mi J (2020) Non-destructive testing and evaluation of composite materials/structures: A state-of-the-art review. Advances in Mechanical Engineering 12: 168781402091376. Doi:10.1177/1687814020913761

227. Hassani S, Mousavi M, Gandomi AH (2021) Structural Health Monitoring in Composite Structures: A Comprehensive Review. Sensors (Basel) 22. Doi:10.3390/s22010153

228. Gupta K, McClanahan A, Erickson K, Zoughi R (2008) Show me the road to hydrogen non-destructive evaluation (NDE), Technical Report. A University Transportation Center Program at Missouri University of Science and Technology: 1-47.

229. Towsyfyan H, Biguri A, Boardman R, Blumensath T (2019) Successes and challenges in non-destructive testing of aircraft composite structures. Chinese J Aeronaut 33: 771-91. Doi:10.1016/j.cja.2019.09.017

230. Boopathy G, Surendar G, Nema A (2017) A review on non-destructive testing of composite materials in aircraft applications. Int J Mech Eng 8: 1334-42.

231. Wang Z, Dixit P, Chegdani F, Takabi B, Tai BL, El Mansori M, Bukkapatnam S (2020) Bidirectional Gated Recurrent Deep Learning Neural Networks for Smart Acoustic Emission Sensing of

Natural Fiber–Reinforced Polymer Composite Machining Process. Smart and Sustainable Manufacturing Systems 4: 20190042. Doi:10.1520/ssms20190042

232. Wang Z, Chegdani F, Yalamarti N, Takabi B, Tai B, El Mansori M, Bukkapatnam S (2020) Acoustic Emission Characterization of Natural Fiber Reinforced Plastic Composite Machining Using a Random Forest Machine Learning Model. Journal of Manufacturing Science and Engineering 142. Doi:10.1115/1.4045945

233. Sarasini F, Santulli C (2014) Non-destructive testing (NDT) of natural fibre composites: acoustic emission technique. Natural Fibre Composites: 273-302. Doi:10.1533/9780857099228.3.273

234. Gholizadeh S (2016) A review of non-destructive testing methods of composite materials. Procedia Structural Integrity 1: 50-7. Doi:10.1016/j.prostr.2016.02.008

235. Loganathan TM, Sultan MTH, Gobalakrishnan MK (2018) Chapter 11, Ultrasonic inspection of natural fiber-reinforced composites. Sustainable Composites for Aerospace Applications, Woodhead Publishing Series in Composites Science and Engineering: 227-51.

236. Lu T, Chen X, Wang H, Zhang L, Zhou Y (2020) Comparison of low-velocity impact damage in thermoplastic and thermoset composites by non-destructive three-dimensional X-ray microscope. Polymer Testing 91: 106730. Doi:10.1016/j.polymertesting.2020.106730

237. Papa I, Lopresto V, Langella A (2021) Ultrasonic inspection of composites materials: Application to detect impact damage. Int J Lightweight Mater Manuf 4: 37-42. Doi:10.1016/j.ijlmm.2020.04.002

238. Yilmaz B, Asokkumar A, Jasiūnienė E, Kažys RJ (2020) Air-Coupled, Contact, and Immersion Ultrasonic Non-Destructive Testing: Comparison for Bonding Quality Evaluation. Applied Sciences 10: 6757. Doi:10.3390/app10196757

239. Sfarra S, Ibarra-Castanedo C, Santulli C, Paoletti D, Maldague X (2016) Monitoring of jute/hemp fiber hybrid laminates by nondestructive testing techniques. Science and Engineering of Composite Materials 23: 283-300. Doi:10.1515/secm-2013-0138

240. Grager J-C, Kotschate D, Gamper J, Gaal M, Pinkert K, Mooshofer H, Goldammer M, Grosse CU (2018) Advances in air-coupled ultrasonic testing combining an optical microphone with novel transmitter concepts. 12th European conference on Non-Destructive Testing, At: Gothenburg, Sweden: 1-10.

241. Chen F, Bouvard J-L, Sawada D, Pradille C, Hummel M, Sixta H, Budtova T (2021) Exploring digital image correlation technique for the analysis of the tensile properties of all-cellulose composites. Cellulose 28: 4165-78. Doi:10.1007/s10570-021-03807-9

242. Lopato P, Psuj G, Szymanik B (2016) Nondestructive Inspection of Thin Basalt Fiber Reinforced Composites Using Combined Terahertz Imaging and Infrared Thermography. Advances in Materials Science and Engineering 2016: 1-13. Doi:10.1155/2016/1249625

243. Sfarra S, Ibarra-Castanedo C, Santulli C, Sarasini F, Ambrosini D, Paoletti D, Maldague X (2013) Eco-Friendly Laminates: From the Indentation to Non-Destructive Evaluation by Optical and Infrared Monitoring Techniques. Strain 49: 175-89. Doi:10.1111/str.12026

244. Boccardi, Boffa, Carlomagno, Core, Meola, Monaco, Russo, Simeoli (2019) Lock-In Thermography and Ultrasonic Testing of Impacted Basalt Fibers Reinforced Thermoplastic Matrix Composites. Applied Sciences 9: 3025. Doi:10.3390/app9153025

245. Zhang H, Sfarra S, Sarasini F, Santulli C, Fernandes H, Avdelidis N, Ibarra-Castanedo C, Maldague X (2018) Thermographic Non-Destructive Evaluation for Natural Fiber-Reinforced Composite Laminates. Applied Sciences 8: 240. Doi:10.3390/app8020240

246. Wang D, Onawumi PY, Ismail SO, Dhakal HN, Popov I, Silberschmidt VV, Roy A (2019) Machinability of natural-fibre-reinforced polymer composites: Conventional vs ultrasonically-assisted machining. Composites Part A: Applied Science and Manufacturing 119: 188-95. Doi:10.1016/j.compositesa.2019.01.028

247. Xu H, Li L, Li G (2022) n situ characterization of the flexural behavior and failure mechanism of 2D needle-punched carbon/carbon composites by digital image correlation. J Mater Sci. Doi:10.1007/s10853-022-07272-y

248. Naresh K, Shankar K, Velmurugan R (2018) Digital image processing and thermo-mechanical response of neat epoxy and different laminate orientations of fiber reinforced polymer composites for vibration isolation applications. Int J Polym Anal 23: 684-709. Doi:10.1080/1023666x.2018.1494431

249. Habibi M, Laperrière L (2020) Digital image correlation and acoustic emission for damage analysis during tensile loading of open-hole flax laminates. Eng Fract Mech 228: 106921. Doi:10.1016/j.engfracmech.2020.106921

250. Ramakrishnan KR, Corn S, Le Moigne N, Ienny P, Slangen P (2021) Experimental assessment of low velocity impact damage in flax fabrics reinforced biocomposites by coupled high-speed imaging and DIC analysis. Composites Part A: Applied Science and Manufacturing 140. Doi:10.1016/j.compositesa.2020.106137

251. Garcea SC, Wang Y, Withers PJ (2018) X-ray computed tomography of polymer composites. Composites Science and Technology 156: 305-19. Doi:10.1016/j.compscitech.2017.10.023

252. Li S, Yang S, Shang L, Liu X, Ma J, Ma Q, Tian G (2021) 3D Visualization of Bamboo Node's Vascular Bundle. Forests 12. Doi:10.3390/f12121799

253. Palombini FL, Kindlein W, de Oliveira BF, de Araujo Mariath JE (2016) Bionics and design: 3D microstructural characterization and numerical analysis of bamboo based on X-ray microtomography. Materials Characterization 120: 357-68. Doi:10.1016/j.matchar.2016.09.022

254. Koddenberg T, Militz H (2018) Morphological imaging and quantification of axial xylem tissue in Fraxinus excelsior L. through X-ray micro-computed tomography. Micron 111: 28-35. Doi:10.1016/j.micron.2018.05.004

255. Yu S, Hwang YH, Hwang JY, Hong SH (2019) Analytical study on the 3D-printed structure and mechanical properties of basalt fiber-reinforced PLA composites using X-ray microscopy. Composites Science and Technology 175: 18-27. Doi:10.1016/j.compscitech.2019.03.005

256. de Kergariou C, Le Duigou A, Popineau V, Gager V, Kervoelen A, Perriman A, Saidani-Scott H, Allegri G, Panzera TH, Scarpa F (2021) Measure of porosity in flax fibres reinforced polylactic acid biocomposites. Composites Part A: Applied Science and Manufacturing 141: 106183. Doi:10.1016/j.compositesa.2020.106183

257. Naresh K, Khan KA, Cantwell WJ, Umer R (2022) Rate and temperature dependent compaction-creep-recovery and void analysis of compression molded prepregs. Compos B Eng 235: 109757. Doi:10.1016/j.compositesb.2022.109757

258. du Plessis A, Yadroitsev I, Yadroitsava I, Le Roux SG (2018) X-Ray Microcomputed Tomography in Additive Manufacturing: A Review of the Current Technology and Applications. 3D Printing and Additive Manufacturing 5: 227-47. Doi:10.1089/3dp.2018.0060

259. Mutiargo B, Pavlovic M, Malcolm AA, Goh B, Krishnan M, Shota T, Shaista H, Jhinaoui A, Putro MIS (2019) Evaluation of X-Ray Computed Tomography (CT) Images of Additively Manufactured Components using Deep Learning. 3rd Singapore International Non-destructive Testing Conference and Exhibition (SINCE2019), Singapore: 94-102.

260. Naresh K, Khan KA, Cantwell WJ, Umer R (2021) Viscoelastic and cyclic compaction response of prepregs tested under isothermal temperatures and various compaction speeds. Polymer Composites 42: 6928-40. Doi:10.1002/pc.26351

261. Bensadoun F, Barburski M, Straumit I, Le Quan Tran N, Fuentes C, Zenina J, Shishkina O, Pyka G, Verpoest I, Van Vuure AW, Wevers M, Lomov SV (2014) Challenges of X-Ray Tomography Technique on Natural Fibre-Based Composites. 11th European Conference on Non-Destructive Testing (ECNDT 2014), October 6-10, 2014, Prague, Czech Republic: 1-12.

262. Di Giuseppe E, Castellani R, Dobosz S, Malvestio J, Berzin F, Beaugrand J, Delisée C, Vergnes B, Budtova T (2016) Reliability evaluation of automated analysis, 2D scanner, and micro-tomography methods for measuring fiber dimensions in polymer-lignocellulosic fiber composites. Compos Part A Appl Sci 90: 320. Doi:10.1016/j.compositesa.2016.07.020

263. Bruni-Bossio BM, Melenka GW, Ayranci C, Carey JP (2019) Micro-computed tomography analysis of natural fiber and bio-matrix tubular-braided composites. J Compos Mater 53: 4003-13 Doi:10.1177/0021998319853023

264. Rask M, Madsen B, Sørensen BF, Fife JL, Martyniuk K, Lauridsen EM (2012) In situ observations of microscale damage evolution in unidirectional natural fibre composites. Compos Part A Appl Sci 43: 1639-49. Doi:10.1016/j.compositesa.2012.02.007

265. Fuentes CA, Willekens P, Petit J, Thouminot C, Müssig J, Trindade LM, Van Vuure AW (2017) Effect of the middle lamella biochemical composition on the non-linear behaviour of technical fibres of hemp under tensile loading using strain mapping. Compos Part A Appl Sci 101: 529-42. Doi:10.1016/j.compositesa.2017.07.017

266. Villarraga-Gómez H, Herazo EL, Smith ST (2019) X-ray computed tomography: from medical imaging to dimensional metrology. Precision Engineering 60: 544-69. Doi:10.1016/j.precisioneng.2019.06.007

267. Yu S, Bale H, Park S, Hwang JY, Hong SH (2021) Anisotropic microstructure dependent mechanical behavior of 3D-printed basalt fiber-reinforced thermoplastic composites. Compos B Eng 224: 109184. Doi:10.1016/j.compositesb.2021.109184

268. Yu S, Hwang JY, Hong SH (2020) 3D microstructural characterization and mechanical properties determination of short basalt fiber-reinforced polyamide 6,6 composites. Compos B Eng 187: 107839. Doi:10.1016/j.compositesb.2020.107839

269. Auenhammer RM, Jeppesen N, Mikkelsen LP, Dahl VA, Blinzler BJ, Asp LE (2022) Robust numerical analysis of fibrous composites from X-ray computed tomography image data enabling low resolutions. Composites Science and Technology 224. Doi:10.1016/j.compscitech.2022.109458

270. Alahmed N, Naresh K, Khan KA, Cantwell WJ, Umer R (2022) In-situ X-ray computed tomography characterization of compaction-creep-recovery response and statistical void analysis of carbon/epoxy prepregs. Composites Communications 31: 101117. Doi:10.1016/j.coco.2022.101117

271. Wielhorski Y, Mendoza A, Rubino M, Roux S (2022) Numerical modeling of 3D woven composite reinforcements: A review. Compos Part A Appl Sci 154: 106729. Doi:10.1016/j.compositesa.2021.106729

272. Hasan KMF, Horváth PG, Alpár T (2021) Potential fabric-reinforced composites: a comprehensive review. Journal of Materials Science 56: 14381-415. Doi:10.1007/s10853-021-06177-6

273. Soltani P, Zarrebini M, Laghaei R, Hassanpour A (2017) Prediction of permeability of realistic and virtual layered nonwovens using combined application of X-ray μ CT and computer simulation. Chemical Engineering Research and Design 124: 299-312. Doi:10.1016/j.cherd.2017.06.035

274. Czigány T (2006) Special manufacturing and characteristics of basalt fiber reinforced hybrid polypropylene composites: Mechanical properties and acoustic emission study. Composites Science and Technology 66: 3210-20. Doi:10.1016/j.compscitech.2005.07.007

275. Seychal G, Ramasso E, Le Moal P, Bourbon G, Gabrion X, Placet V (2022) Towards in-situ acoustic emission-based health monitoring in bio-based composites structures: Does embedment of sensors

affect the mechanical behaviour of flax/epoxy laminates? Compos B Eng 236: 109787. Doi:10.1016/j.compositesb.2022.109787

276. Grabi M, Chellil A, Habibi M, Grabi H, Laperriere L (2022) Characterization of low-velocity impact and post-impact damage of luffa mat composite using acoustic emission and digital image correlation. Journal of Composite Materials. Doi:10.1177/00219983221083733

277. Chew E, Liu JL, Tay TE, Tran LQN, Tan VBC (2021) Improving the mechanical properties of natural fibre reinforced laminates composites through Biomimicry. Compos Struct 258: 113208. Doi:10.1016/j.compstruct.2020.113208

278. Alemdar A, Zhang H, Sain M, Cescutti G, Müssig J (2008) Determination of Fiber Size Distributions of Injection Moulded Polypropylene/Natural Fibers Using X-ray Microtomography. Advanced Engineering Materials 10: 126-30. Doi:10.1002/adem.200700232

279. Xu D, Cerbu C, Wang H, Rosca IC (2019) Analysis of the hybrid composite materials reinforced with natural fibers considering digital image correlation (DIC) measurements. Mechanics of Materials 135: 46-56. Doi:10.1016/j.mechmat.2019.05.001

280. Guessasma S, Belhabib S, Nouri H (2019) Understanding the microstructural role of bio-sourced 3D printed structures on the tensile performance. Polymer Testing 77: 105924.

281. Tabrej K, Sultan MTH, Jawaid M, ShahS. Sani AUM (2021) Low Velocity Impact, Ultrasonic C-Scan and Compression After Impact of Kenaf/Jute Hybrid Composites. Impact Studies of Composite Materials, Composites Science and Technology book series (CST): 73-85.

282. Fischer B, Sarasini F, Tirillò J, Touchard F, Chocinski-Arnault L, Mellier D, Panzer N, Sommerhuber R, Russo P, Papa I, Lopresto V, Ecault R (2019) Impact damage assessment in biocomposites by micro-CT and innovative air-coupled detection of laser-generated ultrasound. Composite Structures 210: 922-31. Doi:10.1016/j.compstruct.2018.12.013

283. Derusova D, Vavilov V, Sfarra S, Sarasini F, Krasnoveikin V, Chulkov A, Pawar S (2019) Ultrasonic spectroscopic analysis of impact damage in composites by using laser vibrometry. Composite Structures 211: 221-8. Doi:10.1016/j.compstruct.2018.12.050

284. Zhang H, Sfarra S, Genest M, Sarasini F, Perilli S, Fernandes H, Fleuret J, Maldague X (2017) Numerical and experimental analyses for natural and non-natural impacted composites via thermographic inspection, ultrasonic C-scan and terahertz imaging SPIE Commercial + Scientific Sensing and Imaging, Anaheim, California, United States 10214.

285. Seghini MC, Touchard F, Sarasini F, Chocinski-Arnault L, Mellier D, Tirillò J (2018) Interfacial adhesion assessment in flax/epoxy and in flax/vinylester composites by single yarn fragmentation test: Correlation with micro-CT analysis. Compos Part A Appl 113: 66-75. Doi:10.1016/j.compositesa.2018.07.015

286. Song W, Zhang C, Wang Z (2021) Investigation of the microstructural characteristics and the tensile strength of silkworm cocoons using X-ray micro computed tomography. Materials & Design 199: 109436. Doi:10.1016/j.matdes.2020.109436

287. Selver E, Dalfi H, Yousaf Z (2020) Investigation of the impact and post-impact behaviour of glass and glass/natural fibre hybrid composites made with various stacking sequences: Experimental and theoretical analysis. Journal of Industrial Textiles: 152808371990067. Doi:10.1177/1528083719900670

288. Sarasini F, Tirillò J, Valente M, Ferrante L, Cioffi S, Iannace S, Sorrentino L (2013) Hybrid composites based on aramid and basalt woven fabrics: Impact damage modes and residual flexural properties. Materials & Design 49: 290-302. Doi:10.1016/j.matdes.2013.01.010

289. Ferrante L, Tirillò J, Sarasini F, Touchard F, Ecault R, Vidal Urriza MA, Chocinski-Arnault L, Mellier D (2015) Behaviour of woven hybrid basalt-carbon/epoxy composites subjected to laser shock wave testing: Preliminary results. Composites Part B: Engineering 78: 162-73. Doi:10.1016/j.compositesb.2015.03.084

290. Dhakal HN, Sarasini F, Santulli C, Tirillò J, Zhang Z, Arumugam V (2015) Effect of basalt fibre hybridisation on post-impact mechanical behaviour of hemp fibre reinforced composites. Composites Part A: Applied Science and Manufacturing 75: 54-67. Doi:10.1016/j.compositesa.2015.04.020

291. Seghini MC, Touchard F, Sarasini F, Chocinski–Arnault L, Ricciardi MR, Antonucci V, Tirillò J (2020) Fatigue behaviour of flax-basalt/epoxy hybrid composites in comparison with non-hybrid composites. International Journal of Fatigue 139. Doi:10.1016/j.ijfatigue.2020.105800

292. Sarasini F, Tirillò J, D'Altilia S, Valente T, Santulli C, Touchard F (2016) Damage tolerance of carbon/flax hybrid composites subjected to LVI. Compos B Eng 91: 144-53. Doi:10.1016/j.compositesb.2016.01.050

293. Sfarra S, Ibarra-Castanedo C, Santulli C, Paoletti A, Paoletti D, Sarasini F, Bendada A, Maldague X (2013) Falling weight impacted glass and basalt fibre woven composites inspected using non-destructive techniques. Composites Part B: Engineering 45: 601-8. Doi:10.1016/j.compositesb.2012.09.078

294. Sfarra S, Ibarra-Castanedo C, Sarasini F, Santulli C, Maldague XPV (2016) Basalt fibre laminates non-destructively inspected after low-velocity impacts. FME Transaction 44: 380-5. Doi:10.5937/fmet1604380S

295. De Rosa IM, Santulli C, Sarasini F, Valente M (2009) Post-impact damage characterization of hybrid configurations of jute/glass polyester laminates using acoustic emission and IR thermography. Composites Science and Technology 69: 1142-50. Doi:10.1016/j.compscitech.2009.02.011

296. Tomlinson D, Fam A (2020) Axial response of flax fibre reinforced polymer-skinned tubes with lightweight foam cores and bioresin blend. Thin-Walled Structures 155. Doi:10.1016/j.tws.2020.106923

297. Paglicawan MA, Emolaga CS, Sudayon JMB, Tria KB (2021) Mechanical Properties of Abaca-Glass Fiber Composites Fabricated by Vacuum-Assisted Resin Transfer Method. Polymers 13: 2719. Doi:10.3390/polym13162719

298. Papa I, Lopresto V, Simeoli G, Langella A, Russo P (2017) Ultrasonic damage investigation on woven jute/poly (lactic acid) composites subjected to low velocity impact. Composites Part B: Engineering 115: 282-8. Doi:10.1016/j.compositesb.2016.09.076

299. Scarponi C, Valente M (2006) An application of a new ultrasonic technique to jute composite laminates subjected to low-velocity impact. Int J Mater Prod Technol 26: 6-18.

300. Dhakal HN, Zhang ZY, Bennett N, Reis PNB (2012) Low-velocity impact response of non-woven hemp fibre reinforced unsaturated polyester composites: Influence of impactor geometry and impact velocity. Composite Structures 94: 2756-63. Doi:10.1016/j.compstruct.2012.04.004

301. Szebényi G, Blößl Y, Hegedüs G, Tábi T, Czigany T, Schledjewski R (2020) Fatigue monitoring of flax fibre reinforced epoxy composites using integrated fibre-optical FBG sensors. Composites Science and Technology 199: 108317. Doi:10.1016/j.compscitech.2020.108317

302. Wang X, Zhong Y, Luo X, Ren H (2021) Compressive Failure Mechanism of Structural Bamboo Scrimber. Polymers 13: 4223. Doi:10.3390/polym13234223

303. Chen G, Luo H (2020) Effects of node with discontinuous hierarchical fibers on the tensile fracture behaviors of natural bamboo. Sustainable Materials and Technologies 26: e00228. Doi:10.1016/j.susmat.2020.e00228

304. Sharma A, Mukhopadhyay T, Rangappa SM, Siengchin S, Kushvaha V (2021) Advances in Computational Intelligence of Polymer Composite Materials: Machine Learning Assisted Modeling, Analysis and Design. Preprints: 1-83. Doi:10.21203/rs.3.rs-471723/v1

305. LeCun Y, Bengio Y, Hinton G (2015) Deep learning. Nature 521: 436–44.

306. Hu C, Hau WNGJ, Chen W, Qin Q-H (2020) The fabrication of long carbon fiber reinforced polylactic acid composites via fused deposition modelling: Experimental analysis and machine learning. Journal of Composite Materials 55: 1459-72. Doi:10.1177/0021998320972172

307. Liu Z (2021) Machine learning based health monitoring of composite structures. Thesis and dissertation: Doctor of Philosophy, Université de Lyon: 77-126.

308. Boon YD, Joshi SC, Bhudolia SK, Gohel G (2020) Recent Advances on the Design Automation for Performance-Optimized Fiber Reinforced Polymer Composite Components. J Compos Sci 4: 61. Doi:10.3390/jcs4020061

309. Wang J, Ma Y, Zhang L, Gao RX, Wu D (2018) Deep learning for smart manufacturing: Methods and applications. Journal of Manufacturing Systems 48: 144-56. Doi:10.1016/j.jmsy.2018.01.003

310. Güemes A, Fernandez-Lopez A, Pozo AR, Sierra-Pérez J (2020) Structural Health Monitoring for Advanced Composite Structures: A Review. Journal of Composites Science 4: 13. Doi:10.3390/jcs4010013
311. Sha W, Li Y, Tang S, Tian J, Zhao Y, Guo Y, Zhang W, Zhang X, Lu S, Cao YC, Cheng S (2021) Machine learning in polymer informatics. InfoMat 3: 353-61. Doi:10.1002/inf2.12167
312. Liu Y, Farnsworth M, Tiwari A (2017) A review of optimisation techniques used in the composite recycling area: State-of-the-art and steps towards a research agenda. Journal of Cleaner Production 140: 1775-81. Doi:10.1016/j.jclepro.2016.08.038
313. Li Z (2015) Tension control system design of a filament winding structure based on fuzzy neural network. Engineering Review 35: 9-17.
314. Heider D, Piovoso MJ, Gillespie Jr. JW (2002) Application of a neural network to improve an automated thermoplastic tow-placement process. Journal of Process Control 12: 101-11.
315. Azimi M, Eslamlou AD, Pekcan G (2020) Data-Driven Structural Health Monitoring and Damage Detection through Deep Learning: State-of-the-Art Review. Sensors 20. Doi:10.3390/s20102778
316. Gu GX, Chen C-T, Richmond DJ, Buehler MJ (2018) Bioinspired hierarchical composite design using machine learning: simulation, additive manufacturing, and experiment. Materials Horizons 5: 939-45. Doi:10.1039/c8mh00653a
317. Pattnaik P, Sharma A, Choudhary M, Singh V, Agarwal P, Kukshal V (2021) Role of machine learning in the field of Fiber reinforced polymer composites: A preliminary discussion. Materials Today: Proceedings 44: 4703-8. Doi:10.1016/j.matpr.2020.11.026
318. Fernandes H, Zhang H, Figueiredo A, Malheiros F, Ignacio LH, Sfarra S, Ibarra-Castanedo C, Guimaraes G, Maldague X (2018) Machine Learning and Infrared Thermography for Fiber Orientation Assessment on Randomly-Oriented Strands Parts. Sensors 18: 1-16. Doi:10.3390/s18010288
319. Jiang F, Guan Z, Wang X, Li Z, Tan R, Qiu C (2021) Study on Prediction of Compression Performance of Composite Laminates After Impact Based on Convolutional Neural Networks. Applied Composite Materials 28: 1153-73. Doi:10.1007/s10443-021-09904-z
320. Mulenga TK, Ude AU, Vivekanandhan C (2021) Techniques for Modelling and Optimizing the Mechanical Properties of Natural Fiber Composites: A Review. Fibers 9: 1-17. Doi:10.3390/fib9010006
321. Ali MA, Guan Q, Umer R, Cantwell WJ, Zhang T (2021) Efficient processing of μCT images using deep learning tools for generating digital material twins of woven fabrics. Composites Science and Technology: 109091. Doi:10.1016/j.compscitech.2021.109091
322. Mendoza A, Trullo R, Wielhorski Y (2021) Descriptive modeling of textiles using FE simulations and deep learning. Composites Science and Technology 213: 108897. Doi:10.1016/j.compscitech.2021.108897

323. Li C, Wei X, He W, Guo H, Zhong J, Wu X, Xu H (2021) Intelligent recognition of composite material damage based on deep learning and infrared testing. Opt Express 29: 31739-53. Doi:10.1364/OE.435230

324. Xu C, Xie J, Wu C, Gao L, Chen G, Song G (2018) Enhancing the Visibility of Delamination during Pulsed Thermography of Carbon Fiber-Reinforced Plates Using a Stacked Autoencoder. Sensors 18: 2809. Doi:10.3390/s18092809

325. Chabaud G (2020) 3D and 4D printing of high performance continuous synthetic and natural fibre composites for structural and morphing applications. PhD thesis and dessertation, Université de Bretagne Sud: 190-204.

326. Xu F (2018) Quantitative characterization of deformation and damage process by digital volume correlation: A review. Theoretical and Applied Mechanics Letters 8: 83-96. Doi:10.1016/j.taml.2018.02.004

327. Mehdikhani M, Breite C, Swolfs Y, Soete J, Wevers M, Lomov SV, Gorbatikh L (2021) Digital volume correlation for meso/micro in-situ damage analysis in carbon fiber reinforced composites. Composites Science and Technology 213: 108944. Doi:10.1016/j.compscitech.2021.108944

328. Yang H, Kumara S, Bukkapatnam STS, Tsung F (2019) The internet of things for smart manufacturing: A review. IISE Transactions 51: 1190-216. Doi:10.1080/24725854.2018.1555383

329. Zhang Y, Xu X (2021) Machine learning tensile strength and impact toughness of wheat straw reinforced composites. Machine Learning with Applications 6: 100188. Doi:10.1016/j.mlwa.2021.100188



https://dspace.org/

Review of advanced techniques for manufacturing biocomposites: non-destructive evaluation and artificial intelligence assisted modeling

Preethikaharshini, J.; Naresh, K.; Rajeshkumar, G.; Arumugaprabu, V.; Khan, Muhammad A. ...

2022-08-30
Springer
https://doi.org/10.1007/s10853-022-07558-1
Preethikaharshini J, Naresh K, Rajeshkumar G, et al., (2022) Review of advanced techniques for manufacturing biocomposites: non-destructive evaluation and artificial intelligence assisted modeling, Journal of Materials Science, Volume 57, Issue 34, September 2022, pp. 16091-16146

Downloaded from a DSpace repository. https://dspace.org/